

Magnetism in Re-based ferrimagnetic double perovskites

A. Winkler,¹ N. Narayanan,¹ D. Mikhailova,¹ K. G. Bramnik,¹ H. Ehrenberg,¹ H. Fuess,¹
G. Vaitheeswaran,^{2,3} V. Kanchana,² F. Wilhelm,⁴ A. Rogalev,⁴ A. Kolchinskaya,¹ and L. Alff^{1,*}

¹*Technische Universität Darmstadt, Petersenstr. 23, 64287 Darmstadt, Germany*

²*Royal Institute of Technology(KTH), Brinellvägen 23, 10044 Stockholm, Sweden*

³*ACRHEM, University of Hyderabad, Hyderabad 500 046, India*

⁴*European Synchrotron Radiation Facility (ESRF),*

6 Rue Jules Horowitz, BP 220, 38043 Grenoble Cedex 9, France

(Dated: received 29 April 2009)

We have investigated spin and orbital magnetic moments of the Re $5d$ ion in the double perovskites $A_2\text{FeReO}_6$ ($A = \text{Ba}, \text{Sr}, \text{Ca}$) by X-ray magnetic circular dichroism (XMCD) at the Re $L_{2,3}$ edges. In these ferrimagnetic compounds an unusually large negative spin and positive orbital magnetic moment at the Re atoms was detected. The presence of a finite spin magnetic moment in a 'non-magnetic' double perovskite as observed in the double perovskite $\text{Sr}_2\text{ScReO}_6$ proves that Re has also a small, but finite *intrinsic* magnetic moment. We further show for the examples of Ba and Ca that the usually neglected alkaline earth ions undoubtedly also contribute to the magnetism in the ferrimagnetic double perovskites.

PACS numbers: 75.25.+z, 75.30.-m, 75.50.-y

I. INTRODUCTION

Ordered double perovskites of the composition A_2MNO_6 (with A an alkaline earth, M a magnetic transition metal ion, and N a non-magnetic ion) have come again into the focus of research because of their interesting magnetic properties. First, in $\text{Sr}_2\text{FeMoO}_6$ a large room-temperature magnetoresistance was observed [1]. Second, within the group of ferrimagnetic double perovskites materials with higher Curie-temperatures, T_C , than in the simple perovskites (e.g. doped manganites) can be obtained. At the moment the highest T_C values have been reported for $\text{Sr}_2\text{CrReO}_6$ ($T_C \approx 635\text{K}$) [2, 3, 4] and $\text{Sr}_2\text{CrOsO}_6$ ($T_C \approx 725\text{K}$) [5, 6, 7]. Third, the mechanism leading to magnetic coupling is believed to be associated with a strong tendency to a half-metallic nature of the charge carriers at the Fermi level [8, 9, 10]. Clearly, these materials are interesting candidates for spintronic applications [11], in particular when having in mind fully epitaxial structures based on perovskite materials.

Recently, Majewski *et al.* and Sikora *et al.* have proposed a simple scaling law between the Curie-temperature and the induced magnetic moment at the non-magnetic site in the double perovskite structure [4, 12, 13]. Philipp *et al.* have discussed that a high Curie-temperature is associated with a tolerance factor close to one for the corresponding crystal [14]. The only exception for this rule is found in the series $A_2\text{FeReO}_6$ ($A = \text{Ba}, \text{Sr}, \text{Ca}$). In this particular FeRe-system it is the strongly monoclinically distorted Ca-based compound having an anomalously high T_C , namely about 540 K [15, 16, 17] (comparing to about 400 K for $\text{Sr}_2\text{FeReO}_6$ [16] and 325 K for $\text{Ba}_2\text{FeReO}_6$ [18, 19]). The dimen-

sionless tolerance factor, f , in $A_2\text{FeReO}_6$ whose deviation from unity implies structural distortion varies from about $f = 1.057$ for $A = \text{Ba}$ over $f = 0.997$ for $A = \text{Sr}$ to $f = 0.943$ for $A = \text{Ca}$ [14]. In general, the Ba-based ferrimagnetic double perovskites are close to a structural transition into a hexagonal lattice where ferro(i)magnetism is not allowed for symmetry reasons; the Sr-based compounds are always close to a perfect cubic structure with maximal T_C , and the Ca-based double perovskites are orthorhombically or monoclinically distorted, with still a large but - due to the reduced exchange - clearly reduced ferrimagnetic transition temperature. The exceptional large T_C of $\text{Ca}_2\text{FeReO}_6$ is accompanied by an insulating state at low temperatures, in contrast to $\text{Sr}_2\text{FeReO}_6$ or even the similarly monoclinically distorted $\text{Ca}_2\text{FeMoO}_6$ which both are metallic [20]. The metal-insulator transition in $\text{Ca}_2\text{FeReO}_6$ has been reported to occur between 100 and 150 K [15, 16, 20]. This behavior has been attributed to strongly enhanced electron-electron correlations on the Re site due to a reduced transfer integral between Fe and Re corresponding to an extremely large effective Coulomb repulsion, U_{eff} , of about 4 eV on both ions [20]. This, however, is in some contradiction to the observed high Curie-temperature, which is believed to be a consequence of a kinetic energy gain due to the hybridization of the Fe $3d$ and Re $5d$ t_{2g} -orbitals. The prediction that a decreased band-filling is favorable for T_C [21], which could be used to conciliate a high T_C with a reduced Re-Re overlap, has turned out to be not valid: an increased band-filling actually leads to a strong T_C enhancement for both the FeMo-system [22] and the CrW-system [23]. Within the kinetically driven exchange model [8, 9, 10], the increase of T_C is more naturally explained as a consequence of increased band-filling. Note, that the cases of $\text{Ca}_2\text{FeReO}_6$ and $\text{Sr}_2\text{CrOsO}_6$, both being insulating and having a high T_C at the same time, are completely different: In the case of $\text{Sr}_2\text{CrOsO}_6$ having

*Electronic address: alff@oxide.tu-darmstadt.de

Table I: Summary of sample properties from x-ray diffraction at 300 K (calculated by Rietfeld-refinement) and SQUID magnetometry.

material	T_C (K)	symm.	lattice (Å)	antisites (%)
$\text{Ba}_2\text{FeReO}_6$	317	$\text{Fm}\bar{3}\text{m}$	$a = 8.0571(2)$	0.9
$\text{Sr}_2\text{FeReO}_6$	418	$\text{Fm}\bar{3}\text{m}$	$a = 7.8752(4)$	2.6
$\text{Ca}_2\text{FeReO}_6$	556	$\text{P}2_1/\text{n}$	$a = 5.3992(2)$ $b = 5.5269(2)$ $c = 7.6826(3)$	3.6
$\text{Sr}_2\text{ScReO}_6$	-	$\text{P}2_1/\text{n}$	$a = 5.6760(2)$ $b = 5.6534(2)$ $c = 7.9862(3)$	7

only a tiny rhombohedral distortion, the Os $5d t_{2g}$ band is completely filled, while for $\text{Ca}_2\text{FeReO}_6$ it is the structural distortion that drives the metal-insulator transition. Recently, it was suggested that in double perovskites with heavy ions as Re a large orbital contribution to the magnetic moment leads to an enhanced total magnetization above the integer value that is expected for a half-metallic material [25]. This elsewhere predicted and calculated [26] strong influence of spin-orbit coupling leads to a quasi-half metallicity which still is from the view point of applications in spintronics very high (above 90%). Another point of interest is the possibility of an *intrinsic* enhancement of the Re spin magnetic moment due to the peculiar Re^{5+} state in the ferrimagnetic double perovskites. In this study, we present the XMCD analysis of the system $A_2\text{FeReO}_6$ ($A = \text{Ba}, \text{Sr}, \text{Ca}$), compare the experimental data to theoretical predictions calculated within the full-potential linear muffin-tin orbital method (FP-LMTO) [27] with included spin-orbit coupling, and complete the so far suggested scaling law [4] by using the identical method to extract separately spin and orbital magnetic moments. Furthermore, we search for a contribution of the alkaline earth element to the magnetic behavior, and also look for an *intrinsic* Re moment in a suited double perovskite compound with M being a non-magnetic ion: $\text{Sr}_2\text{ScReO}_6$.

II. EXPERIMENTAL

A summary of the sample properties is given in Table I. All values where a comparison can be made to literature values are in good agreement with these data [2, 15]. Note that the small amount of antisite disorder does not affect our results. The XMCD measurements on the Re $L_{2,3}$ edges were performed at the European Synchrotron Radiation Facility (ESRF) at beam line ID12 [29]. The spectra were recorded within the total fluorescence yield detection mode. The XMCD spectra were obtained as direct difference between consecutive XANES

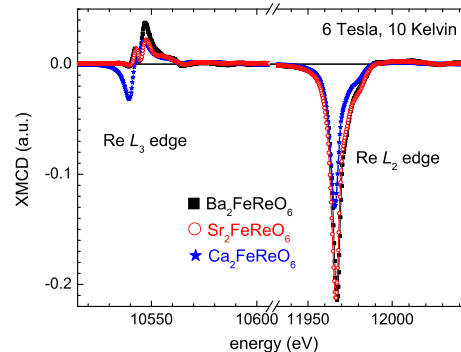


Figure 1: XMCD spectra for $A_2\text{FeReO}_6$ ($A = \text{Ba}, \text{Sr}, \text{Ca}$).

scans (X-ray Absorption Near Edge Spectrum) recorded with opposite helicities of the incoming x-ray beam. To ensure that the XMCD spectra are free from any experimental artefacts the data were collected for both directions of the applied magnetic field of 6 T (parallel and antiparallel to the x-ray beam). The degree of circular polarization of the monochromatic x-ray beam was 98%. The measurements were performed at about 10 K for all samples ($T \ll T_C$), if not indicated otherwise. Since the samples measured in backscattering geometry were very thick, the spectra were first normalized to the edge jump of unity and then corrected from self-absorption effects. The edge jump intensity ratio L_3/L_2 was then normalized to 2.19/1 [30]. This is different from the statistical 2:1 branching ratio due to the difference in the radial matrix elements of the $2p_{1/2}$ to $5d(L_2)$ and $2p_{3/2}$ to $5d(L_3)$ transitions. The XMCD measurement as a function of applied field suggests that our samples are closer to saturation at 6 T as is concluded by de Teresa *at al.* [25] from high-field SQUID measurements. This issue has to be clarified in future by high-field XMCD measurements.

III. RESULTS AND DISCUSSION

In this paper, the XANES spectra themselves are not further discussed. As shown in Fig. 1, for FeRe-compounds at both absorption edges we find a rather intense XMCD signal. This is a clear evidence for the existence of a magnetic moment at the Re $5d$ shell. For all three compounds, the XMCD spectra at the L_2 edge are largest (as expected for $m = 1$ orbitals) and similar in shape. In $\text{Ca}_2\text{FeReO}_6$ the size of the XMCD signal is by a factor of 2 smaller compared to the two other FeRe compounds. At the L_3 edge, the Ca-based double perovskite again stands out by a pronounced peak with negative XMCD signal which is absent for $\text{Sr}_2\text{FeReO}_6$ and $\text{Ba}_2\text{FeReO}_6$. The data at the L_3 edge look slightly different in amplitude as compared to previously published data [13]. However, the data are consistent in that the integrated XMCD intensity at the L_3 edge is negative only in the case of $\text{Ca}_2\text{FeReO}_6$. In this sense, all data support the unusual behavior of $\text{Ca}_2\text{FeReO}_6$, which cannot only be attributed to the different ionic size of the

Table II: Measured (exp., normalized to 5 K) and calculated (th., calculated within the generalized gradient approximation including spin-orbit coupling (GGA+SO)) magnetic moments at the Re site for different double perovskites at about 10 K. For a detailed discussion of the applied band-structure calculation see e.g. [26, 28]. Calculation in [31] is GGA *with* spin-orbit coupling. The number of *d*-holes was taken from the band-structure calculation. In our case this number was around 5.3. The error of the measured values is estimated as 2.5%.

material	m_S ($\mu_B/f.u.$)	m_L ($\mu_B/f.u.$)	$ m_L/m_S $
exp. Ba_2FeReO_6	-0.56	0.15	0.27
Sr_2FeReO_6	-0.74	0.21	0.28
Ca_2FeReO_6	-0.47	0.16	0.34
Sr_2CrReO_6 [4]	-0.68	0.25	0.37
Sr_2ScReO_6 (80 K)	0.013	-0.002	0.15
th. Ba_2FeReO_6	-0.65	0.19	0.29
Sr_2FeReO_6	-0.68	0.15	0.22
Sr_2FeReO_6 [31]	-0.85	0.23	0.27
Sr_2CrReO_6 [26]	-0.85	0.18	0.21

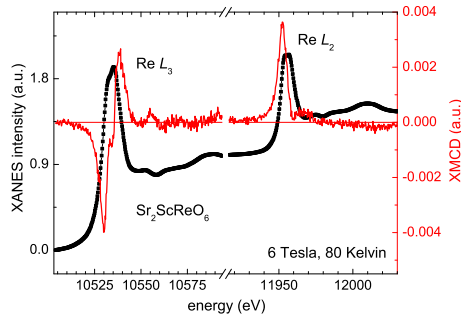


Figure 2: XANES and derived XMCD spectra at the Re L_2 and L_3 edges of Sr_2ScReO_6 .

A site ions.

In Fig. 2 we show XANES and XMCD spectra for the compound Sr_2ScReO_6 . This compound is important because the absence of any free electrons at Sc^{3+} which has a $3d^0$ configuration will lead to a complete breakdown of the *induced* magnetic moment at the Re site. This compound therefore allows the measurement of the *intrinsic* magnetic moment of Re^{5+} (also in contrast to Re^{6+} compounds as Sr_2MgReO_6). Previously, Kato *et al.* have calculated from a Curie-Weiss fit to the susceptibility an effective magnetic moment of Re in Sr_2ScReO_6 of about $1.1 \mu_B/f.u.$, as expected within the ionic picture [32]. In contrast, our data show the existence of a much smaller, but finite intrinsic moment at the Re site, indicating an increased tendency to magnetic ordering of Re^{5+} . Since this moment is present above the antiferromagnetic transition temperature, it is not related to spin glass behavior. The spin magnetic moment is about 50 times smaller than corresponding induced moments on

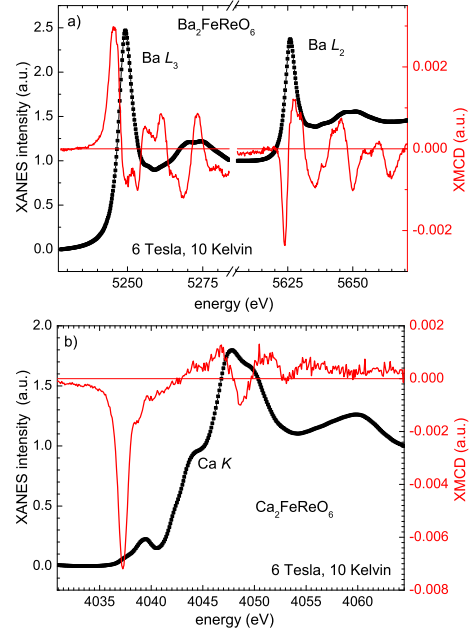


Figure 3: XANES and derived XMCD spectra at the a) Ba L_2 and L_3 edges of Ba_2FeReO_6 and b) at the Ca K edge of Ca_2FeReO_6 .

Re^{5+} , and the orbital magnetic moments even by a factor of 100. However, due to the high sensitivity of the set-up at ESRF, one can unambiguously prove the existence of this moment. In contrast to the opposite sign of the induced magnetic moment with respect to the applied field, the spin magnetic moment at the Re in Sr_2ScReO_6 is aligned with the field. This is expected because the kinetic exchange via fully polarized spin down is not at work. This intrinsic moment of Re^{5+} therefore has to be considered as an indicator of the tendency to unusually high magnetization of Re based double perovskites.

As a last point, we address magnetism in the earth alkaline ions itself, which usually are completely neglected in the magnetic scenario. The XANES and XMCD spectra of the Ba L_2 and L_3 edges of Ba_2FeReO_6 and of the Ca K -edge of Ca_2FeReO_6 are shown in Fig. 3. The $5d$ spin magnetic moment (calculated with 9 as the number of *d*-holes corresponding to the band-structure calculation) of Ba is $\mu_S = -0.0065$ and the $5d$ orbital magnetic moment $\mu_L = -0.0013$ (both in $\mu_B/f.u.$), $|\mu_L/\mu_S| \approx 0.2$. The theoretical predictions calculated as described elsewhere [26, 28] are $\mu_S = -0.0084$ and $\mu_L = -0.0014$ which is in fair agreement with our experimental data. For Ca_2FeReO_6 we can only qualitatively say that a finite magnetic moment is observed, because the K -edge probes only the $4p$ orbital magnetism. Since the L edges are experimentally not accessible, a quantitative analysis cannot be done. The observation of a magnetically polarized density of states gives clear evidence for a magnetic interaction of the earth alkaline ions with the other ions. The magnetic contribution of Ba in this case is a factor of 2 smaller than the contribution of the intrinsic Re moment. Naturally, one expects that the magnetic con-

tribution increases with ionic size due to the increased exchange with the neighboring ions. The clear orbital contribution in $\text{Ba}_2\text{FeReO}_6$ is not unexpected due to the heavy ionic mass. Our data provide a test for a detailed theoretical study of the magnetism in the double perovskites, and underlines the importance of taking spin-orbit coupling into account. Note, that for example in CrO_2 , where the importance of oxygen in the magnetic mechanism is undoubted, comparable values of spin and orbital moments of the oxygen ion have been measured [33] as compared to our results on Ba in $\text{Ba}_2\text{FeReO}_6$.

In Table II we summarize our results for the spin and orbital magnetic moments at the Re site as derived from the XMCD measurements by applying the standard sum rules [34, 35] and compare them to theoretical values. Also, the ratio $|m_L/m_S|$ is calculated, since this quantity is not affected by possible uncertainties in the calculated number of holes. In general, the calculated data are in surprisingly good agreement with the measured data. One of the main reasons certainly is, that spin-orbit coupling is taken into account from the beginning. Note, that in the hard x-ray range the sum rules apply with high validity due to the large spin-orbit splitting of the core level.

Let us finally discuss again our data for the three FeRe-based compounds. Our data are in good qualitative and quantitative agreement with literature data with one exception: $\text{Ca}_2\text{FeReO}_6$. While Sikora *et al.* [13] find, that the spin magnetic moment of Re in $\text{Ca}_2\text{FeReO}_6$ scales with the high T_C , in our case it has the lowest spin magnetic moment, letting $\text{Ca}_2\text{FeReO}_6$ stand out from the scaling law [4, 12, 13] which so far holds in all other cases. This behavior is certainly more natural, since one

expects that a reduced exchange will also lead to a reduced spin magnetic moment on the Re site. Note that the ratio of orbital and spin magnetic moments are consistent with the previous data. As suggested previously by Kato *et al.* [16], a Re t_{2g} orbital ordered state or its glass-state analog associated with the monoclinic lattice distortion occurs, pointing out the importance of correlation effects in this compound. Recently, Sikora *et al.* [36] proposed a scenario with a complex competition between two phases with different electronic and crystallographic structure. Our data give further indication that $\text{Ca}_2\text{FeReO}_6$ is exceptional among the double perovskites due to the strong octahedral-site distortions.

IV. SUMMARY

In summary, we have elucidated the Re magnetic moments in the FeRe-based series of double perovskites as a function of the earth alkaline ion, confirming the exceptional position of $\text{Ca}_2\text{FeReO}_6$. We have measured a finite *intrinsic* magnetic moment at the Re^{5+} site in $\text{Sr}_2\text{ScReO}_6$ indicating the tendency to enhanced magnetic moments observed in Re based double perovskites. Furthermore, for the first time we were able to measure by XMCD the magnetic moments directly at the alkaline earth site itself. Our result shows that the usually neglected Ca and Ba ions play a role in the magnetic scenario of the kinetically driven exchange model, comparable in size to the role of oxygen.

This work was supported by the ESRF (HE-2114/2115/2379).

-
- [1] Kobayashi K I, Kimura T, Sawada H, Terakura K and Tokura Y 1998 *Nature* **395** 677
 - [2] Kato H, Okuda T, Okimoto Y, Tomioka Y, Takenoya Y, Ohkubo A, Kawasaki M and Tokura Y 2002 *Appl. Phys. Lett.* **81** 328
 - [3] Asano H, Kozuka N, Tsuzuki A and Matsui M 2004 *Appl. Phys. Lett.* **85** 263
 - [4] Majewski P, Geprägs S, Sanganas O, Opel M, Gross R, Wilhelm F, Rogalev A and Alff L 2005 *Appl. Phys. Lett.* **87** 202503
 - [5] Krockenberger Y, Mogare K, Reehuis M, Tovar M, Jansen M, Vaitheeswaran G, Kanchana V, Bultmark F, Delin A, Wilhelm F, Rogalev A, Winkler A and Alff L 2007 *Phys. Rev. B* **75** 020404(R)
 - [6] Krockenberger Y, Reehuis M, Tovar M, Mogare K, Jansen M and Alff L 2007 *J. Magn. Magn. Mater.* **310** 1854
 - [7] Lee K-W and Pickett W E 2008 *Phys. Rev. B* **77** 115101
 - [8] Sarma D D, Mahadevan P, Saha-Dasgupta T, Ray Sugata and Kumar A 2000 *Phys. Rev. Lett.* **85** 2549; see also 2001 *it Curr. Opinion in Solid State Mat. Sci.* **5** 261
 - [9] Fang Z, Terakura K and Kanamori J 2001 *Phys. Rev. B* **63** 180407(R)
 - [10] Kanamori J and Terakura K 2001 *J. Phys. Soc. Jpn.* **70** 1433
 - [11] For a recent review see: Serrate D, De Teresa J M and Ibarra M B 2007 *J. Phys.: Condens. Matter* **19** 023201
 - [12] Majewski P, Geprägs S, Boger A, Opel M, Erb A, Gross R, Vaitheeswaran G, Kanchana V, Delin A, Wilhelm F, Rogalev A and Alff L 2005 *Phys. Rev. B* **72** 132402
 - [13] Sikora M, Kapusta Cz, Borowiec M, Oates C J, Prochazka V, Rybicki D, Zajac D, De Teresa J M, Marquina C and Ibarra M R 2006 *Appl. Phys. Lett.* **89** 062509
 - [14] Philipp J B, Majewski P, Alff L, Erb A, Gross R, Graf T, Brandt M S, Simon J, Walther T, Mader W, Topwal D and Sarma D D 2003 *Phys. Rev. B* **68** 144431
 - [15] Westerburg W, Lang O, Ritter C, Felser C, Tremel W and Jakob G 2002 *Solid State Comm.* **122** 201
 - [16] Kato H, Okuda T, Okimoto Y, Tomioka Y, Oikawa K, Kamiyama T and Tokura Y 2002 *Phys. Rev. B* **65** 144404
 - [17] Michalik J M, De Teresa J M, Blasco J, Algarabel P A, Ibarra M R, Kapusta Cz and Zeitler U 2007 *J. Phys.: Condens. Matter* **19** 506206
 - [18] Prellier W, Smolyaninova V, Biswas A, Galley C, Greene R L, Ramesha K and Gopalakrishnan J 2000 *J. Phys.: Condens. Matter* **12** 965

- [19] Azimonte C, Cezar J C, Granado E, Huang Q, Lynn J W, Campoy J C P, Gopalakrishnan J and Ramesha K 2007 *Phys. Rev. Lett.* **98** 017204
- [20] Iwasawa H, Saitoh T, Yamashita Y, Ishii D, Kato H, Hamada N, Tokura Y and Sarma D D 2005 *Phys. Rev. B* **71** 075106
- [21] Chattopadhyay A and Millis A J 2001 *Phys. Rev. B* **64** 024424
- [22] Navarro J, Frontera C, Balcells Ll, Martínez B and Fontcuberta J 2001 *Phys. Rev. B* **64** 092411
- [23] Geprägs S, Majewski P, Gross R, Ritter C and Alff L 2005 *J. Appl. Phys.* **99** 08J102
- [24] Philipp J B, Reisinger D, Schonecke M, Marx A, Erb A, Alff L, Gross R and Klein J 2002 *Appl. Phys. Lett.* **79** 3654
- [25] De Teresa J M, Michalik J M, Blasco J, Algarabel P A, Ibarra M R, Kapusta C and Zeitler U 2007 *Appl. Phys. Lett.* **90** 252514
- [26] Vaitheeswaran G, Kanchana V and Delin A 2005 *Appl. Phys. Lett.* **86** 032513
- [27] Wills J M, Eriksson O, Alouani M and Price O L 2000 *Electronic Structure and Physical Properties of Solids* Ed. Dreyssé H, Springer, Berlin
- [28] Vaitheeswaran G, Kanchana V and Delin A 2006 *J. of Phys.: Conf. Series* **29** 50
- [29] Rogalev A, Goulon J, Goulon-Ginet Ch and Malgrange C 2001 *Magnetism and Synchrotron Radiation* Eds. Beau-repaire E *et al* **565**, Springer, p 666
- [30] Wilhelm F, Pouloupoulos P, Wende H, Scherz A, Baberschke K, Angelakeris M, Flevaris N K and Rogalev A 2001 *Phys. Rev. Lett.* **87** 207202
- [31] Jeng Horng-Tay and Guo G Y 2003 *Phys. Rev. B* **67** 094438
- [32] Kato H, Okuda T, Okimoto Y, Tomioka Y, Oikawa K, Kamiyama T and Tokura Y 2004 *Phys. Rev. B* **69** 184412
- [33] Huang D J, Jeng H-T, Chang C F, Guo G Y, Chen J, Wu W P, Chung S C, Shyu S G, Wu C C, Lin H-J and Chen C T 2002 *Phys. Rev. B* **66** 174440
- [34] Thole B T, Carra P, Sette F and van der Laan G 1992 *Phys. Rev. Lett.* **68** 1943
- [35] Carra P, Thole B T, Altarelli M and Wang X 1993 *Phys. Rev. Lett.* **70** 694
- [36] Sikora M, Mathon O, van der Linden P, Michalik J M, de Teresa J M, Kapusta Cz and Pascarelli S 2009 *Phys. Rev. B* **79** 220402(R)