

Re-determination of the Pseudobinary System $\text{Li}_2\text{O} - \text{MoO}_3$

excerpt for copyright reasons, full article published:

Cryst. Res. Technol. 43, No. 4, 350–354 (2008) / DOI 10.1002/crat.200711106

M. Moser*, D. Klimm†, S. Ganschow, A. Kwasniewski, K. Jacobs
 Institute for Crystal Growth
 Max-Born-Str. 2, 12489 Berlin, Germany

21 December 2007

Results and Discussion

For the components Li_2O and MoO_3 just the following intermediate phases were confirmed independently by other authors using X-ray diffraction. It must be assumed that the phases $\text{Li}_2\text{Mo}_2\text{O}_7$ and $\text{Li}_2\text{Mo}_3\text{O}_{10}$, which are mentioned in Tab. 1, do not exist.

- Li_4MoO_5 : $\text{LiO}_{0.5} : \text{MoO}_3 = 4.2 : 1.0$ were annealed at 950°C for 28 days. Crystals are triclinic (disordered rocksalt type, $P\bar{1}$) with $a_0 = 5.1094(5)\text{ \AA}$, $b_0 = 7.7169(7)\text{ \AA}$, $c_0 = 6.0609(4)\text{ \AA}$, $\alpha = 101.804(8)^\circ$, $\beta = 101.78(1)^\circ$, $\gamma = 108.770(9)^\circ$ [11].
- Li_2MoO_4 : Single crystals can be obtained [9], belonging to the phenacite type structure type ($R\bar{3}$ with $a_0 = 14.330(2)\text{ \AA}$, $c_0 = 9.584(2)\text{ \AA}$) [13]. The substance crystallizes in anhydrous form from aqueous solution [8].
- $\text{Li}_4\text{Mo}_5\text{O}_{17}$: Single crystals of about 1 cm diameter can be grown by the Czochralski technique [9] ($P\bar{1}$ with $a_0 = 6.7775(1)\text{ \AA}$, $b_0 = 9.461(1)\text{ \AA}$, $c_0 = 10.802(2)\text{ \AA}$, $\alpha = 73.16(2)^\circ$, $\beta = 88.98(1)^\circ$, $\gamma = 69.760(2)^\circ$ [14]).
- $\text{Li}_2\text{Mo}_4\text{O}_{13}$: $40 \times 50 \times 60\text{ }\mu\text{m}^3$ sized crystals of the low- T form ($P\bar{1}$ with $a_0 = 8.578(5)\text{ \AA}$, $b_0 = 11.450(5)\text{ \AA}$, $c_0 = 8.225(5)\text{ \AA}$, $\alpha = 109.24(7)^\circ$, $\beta = 96.04(7)^\circ$, $\gamma = 95.95(7)^\circ$) were obtained by slow cooling of $\text{Li}_2\text{CO}_3/\text{MoO}_3$ melts [15]. $30 \times 30 \times 60\text{ }\mu\text{m}^3$ sized crystals of the high- T form ($P\bar{1}$ with $a_0 = 8.612(4)\text{ \AA}$, $b_0 = 11.562(6)\text{ \AA}$, $c_0 = 8.213(4)\text{ \AA}$, $\alpha = 94.45(7)^\circ$, $\beta = 96.38(7)^\circ$, $\gamma = 111.24(7)^\circ$) were prepared by annealing mixtures of Li_2MoO_4 and MoO_3 for 18 hours at 547°C . Besides, a monoclinic form was reported ($P2_1/m$ or $P2_1$) [16].

*Permanent address: Humboldt-Universität zu Berlin, Institut für Chemie, Brook-Taylor-Str. 2, 12489 Berlin, Germany

†Corresponding author: e-mail: klimm@ikz-berlin.de

Table 1: Crystalline Li–Mo^{VI}–O phases as reported by different authors. x is the molar fraction of MoO₃. “i” and “c” means incongruent or congruent melting, respectively, as reported in the given references.

Formula	x	T_f (°C)	melting	references	this study
Li ₂ O=LiO _{0.5}	0.000	1570	c	[12]	
Li ₄ MoO ₅	0.200	> 950		[11, 17]	i?
Li ₂ MoO ₄	0.333	705	?	[8]	$T_f = 698^\circ\text{C}$ (i)
Li ₂ Mo ₂ O ₇	0.500	530 – 535	i/c	[8, 10]	not found
Li ₄ Mo ₅ O ₁₇	0.556	544	c	[9]	$T_f = 547^\circ\text{C}$ (i)
Li ₂ Mo ₃ O ₁₀	0.600	549	i	[8]	not found
Li ₂ Mo ₄ O ₁₃	0.667	568 – 576	i	[8, 9, 10]	$T_f = 570^\circ\text{C}$ (i)
MoO ₃	1.000	795 – 801	c	[8, 9, 12, 18, 19]	$T_f = 782^\circ\text{C}$ (c)

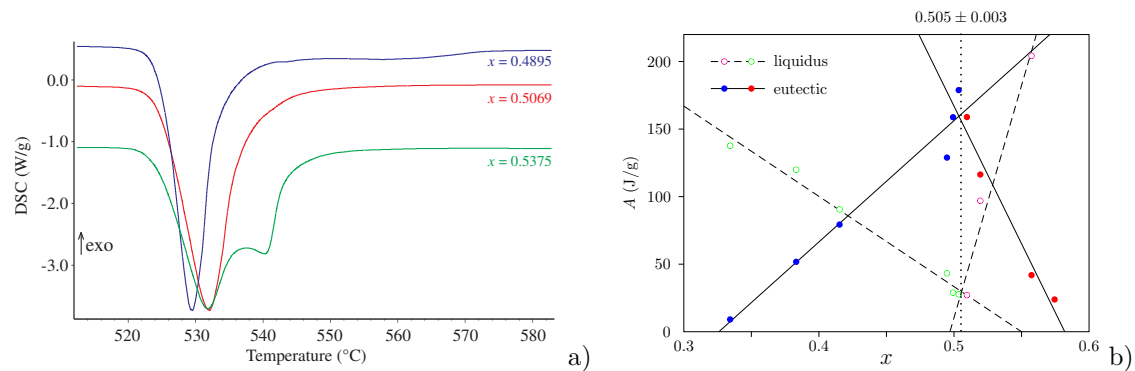


Figure 1:

a) From top to bottom: DSC heating curves on the Li₂O-rich side, in the vicinity of the eutectic composition $x_{\text{eut}} = 0.505$, and on the MoO₃-rich side.

b) Peak areas $A(x)$ for the eutectic peak and for the shoulder extending to the liquidus.

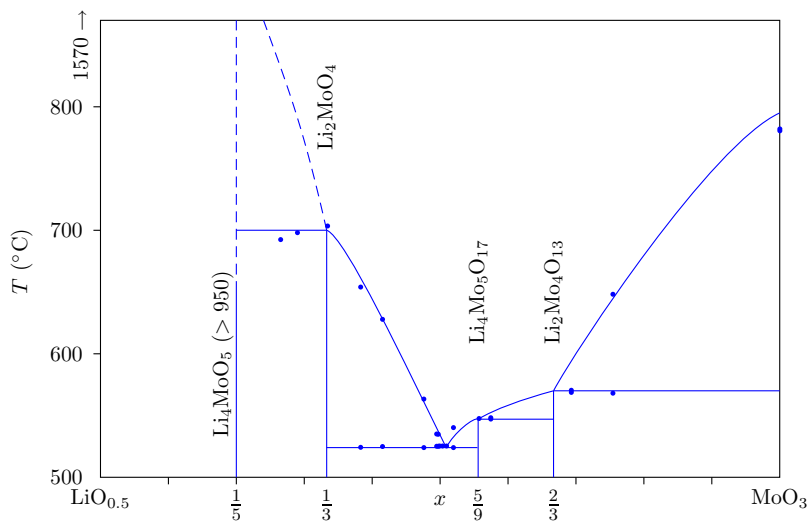


Figure 2: The phase diagram $\text{Li}_2\text{O}-\text{MoO}_3$ with some experimental points, as determined by DSC.

References

- [1] D. Elwell and H. J. Scheel, *Crystal Growth from High-Temperature Solutions*. Academic Press, London, 1975.
- [2] K.-Th. Wilke, *Kristallzüchtung*. Deutscher Verlag der Wissenschaften, Berlin, 1988.
- [3] M. Beaurain, P. Armand, and P. Papet, *J. Crystal Growth* **294**, 396 (2006). doi:10.1016/j.jcrysgro.2006.05.074.
- [4] P. Armand, M. Beaurain, B. Ruffle, B. Menaert, D. Balitsky, S. Clement, and P. Papet, *J. Crystal Growth* accepted (2008). doi:10.1016/j.jcrysgro.2007.11.049.
- [5] P. Hautefeuille and A. Perry, *Comptes Rendus de l'Academie des Sciences Paris* **106**, 1800 (1888).
- [6] H. Espig, *Chem. Techn.* **12**, 327 (1960).
- [7] ACerS-NIST, Phase equilibria diagrams, v. 3.0.1 (CD ROM database) (2004).
- [8] F. Hoermann, *Z. anorg. allg. Chem.* **177**, 145 (1929). doi:10.1002/zaac.19291770117.
- [9] W. S. Brower, H. S. Parker, R. S. Roth, and J. L. Waring, *J. Crystal Growth* **16**, 115 (1972).
- [10] M. Parmentier, J. M. Reau, C. Fouassier, and C. Gleitzer, *Bull. Soc. Chim. Fr.* **5**, 1743 (1972).
- [11] R. Hoffmann and R. Hoppe, *Z. anorg. allg. Chem.* **573**, 157 (1989).
- [12] GTT Technologies, Kaiserstr. 100, 52134 Herzogenrath, Germany, FactSage 5.5 (2007). <http://www.factsage.com/> .
- [13] U. Kolitsch, *Z. Krist.* **216**, 449 (2001). doi:10.1524/zkri.216.8.449.20358.
- [14] M. Wiesmann, H. Weitzel, I. Svoboda, and H. Fuess, *Z. Krist.* **212**, (1997).
- [15] B. M. Gatehouse and B. K. Miskin, *J. Solid State Chem.* **9**, 247 (1974). doi:10.1016/0022-4596(74)90081-4.
- [16] B. M. Gatehouse and B. K. Miskin, *J. Solid State Chem.* **15**, 274 (1975). doi:10.1016/0022-4596(75)90213-3.
- [17] G. Blasse, *Z. anorg. allg. Chem.* **331**, 44 (1964). doi:10.1002/zaac.19643310108.
- [18] V. V. Lisnyak, M. S. Slobodyanik, and V. S. Sudavtsova, *Powder Metallurgy and Metal Ceramics* **39**, 139 (2000). doi:10.1007/BF02678635.
- [19] Lee A. Cosgrove and Paul E. Snyder, *J. Am. Chem. Soc.* **75**, 1227 (1953). doi:10.1021/ja01101a063.