

Dependences on RE of Superconducting Properties of Transition Metal co-doped $(Ca,RE)FeAs_2$ with $RE = La-Gd$

H. Yakita^{a*}, H. Ogino^a, A. Sala^{a,b,c}, T. Okada^a, A. Yamamoto^a, K. Kishio^a,
A. Iyo^b, H. Eisaki^b, J. Shimoyama^a

^a*Department of Applied Chemistry, The University of Tokyo, 7-3-1 Hongo, Bunkyo, Tokyo, 113-8656, Japan*

^b*National Institute of Advanced Industrial Science and Technology (AIST), Tsukuba, Ibaraki, 05-8565, Japan*

^c*University of Genova and CNR-SPIN, 16146 Genova, Italy*

Abstract

Dependence of superconducting properties of $(Ca,RE)(Fe,TM)As_2$ [$(Ca,RE)112$, TM : Co, Ni] on RE elements ($RE = La-Gd$) was systematically investigated. Improvement of superconducting properties by Co or Ni co-doping was observed for all $(Ca,RE)112$, which is similar to Co-co-doped $(Ca,La)112$ or $(Ca,Pr)112$. T_c of Co-co-doped samples decreased from 38 K for $RE = La$ to 29 K for $RE = Gd$ with decreasing ionic radii of RE^{3+} . However, Co-co-doped $(Ca,Eu)112$ showed exceptionally low $T_c = 21$ K probably due to the co-existence of Eu^{3+} and Eu^{2+} suggested by longer interlayer distance d_{Fe-Fe} of $(Ca,Eu)112$ than other $(Ca,RE)112$.

Keywords: Iron-based conductors, co-doping

1. Introduction

After the discovery of superconductivity in $LaFeAs(O,F)$ ^[1], exploration of iron-based superconductors has been attempted extensively and various type of new superconductors, such as 11^[2], 111^[3] and 122^[4] systems, were discovered. Searches for new iron-based superconductors have been still continuing, resulted in a recent discovery of new series of iron-based superconductors $(Ca,RE)FeAs_2((Ca,RE)112)$ ^[5-9]. $(Ca,RE)112$ has several unique properties, such as monoclinic structure with space group of $P2_1$ or $P2_1/m$, and co-existence of As^{-1} and As^{-3} in the crystal lattice^[5,6]. Moreover, anisotropy of $(Ca,La)112$ was reported to be 2.0-4.2^[10], which is smaller than that of 1111 type superconductors, while interlayer distance between Fe layer (d_{Fe-Fe}) is longer in $(Ca,La)112$. More than 15 % substitution of La for Ca site is needed to form $(Ca,La)112$ phase, and T_c decreases with increasing La content^[11]. It suggests that $(Ca,La)112$ is basically in the overdoped state. Sala *et al.* reported RE dependence on T_c in $(Ca,RE)112$ with nominal RE composition of 15 % for Ca. A decrease in T_c with a decrease in ionic radii of RE^{3+} was observed except for $(Ca,Ce)112$ which did not show superconductivity. Kudo *et al.* reported the T_c of 47 K in Sb co-doped $(Ca,La)112$ ^[12]. Enhancement of T_c in Sb co-doped $(Ca,RE)112$ is achieved by optimization of As-Fe-As bond angle. In addition, we have recently reported Mn or Co-co-doping effects in $(Ca,La)112$ and $(Ca,Pr)112$ ^[13]. Analyzed substitution levels of Co in Co-co-doped $(Ca,RE)112$ were close to the nominal composition, though RE composition were higher than those of nominal compositions. Sharp superconducting transition in $(Ca,La)112$ and enhancement of T_c in $(Ca,Pr)112$ was induced by Co-co-doping, while Mn co-doping strongly suppressed superconductivity. These results indicates co-doping of transition metals (TM), such as Co, is promising way to improve superconducting properties of $(Ca,RE)112$.

In this paper, we report TM (Co, Ni) co-doping effect for $(Ca,RE)112$ ($RE = La-Gd$) with low RE doping level. RE element dependence on structural parameters as well as superconducting properties of TM co-doped $(Ca,RE)112$ are systematically investigated.

*Corresponding author at Room 502, Building 9, 2-11-16, Yayoi, Bunkyo, Tokyo, Japan, 113-8656. Tel.:+81-3-5841-7766
E-mail address: 8757570603@mail.ecc.u-tokyo.ac.jp.

2. Experiment

Samples with nominal compositions of $(\text{Ca}_{0.9}\text{RE}_{0.1})\text{FeAs}_2$ and $(\text{Ca}_{1-x}\text{RE}_x)\text{Fe}_{0.97}\text{TM}_{0.03}\text{As}_2$ ($\text{RE} = \text{La-Gd}$, $\text{TM} = \text{Co, Ni}$, $x = 0.075, 0.1$) were synthesized starting from $\text{FeAs}(3\text{N})$, $\text{As}(4\text{N})$, $\text{Ca}(2\text{N})$, $\text{REAs}(\text{RE} = \text{La, Pr, Nd, Sm, 3N})$, $\text{RE metals}(\text{RE} = \text{Ce, Eu, Gd, 3N})$, $\text{CoAs}(3\text{N})$, $\text{Ni}(3\text{N})$ powders. Starting powders were mixed and pelletized in an argon-filled glove box, filled in boron nitride(BN) crucible, and sintered at 1050-1200°C for 1 h under a high pressure of 2 GPa using a wedge-type cubic-anvil high-pressure apparatus (RIKEN CAP-07). Constituent phases and lattice constants were studied by powder XRD measurements using a RIGAKU Ultima-IV diffractometer, and the intensity data were collected in the 2θ range of 5-80° in increments of 0.02° using $\text{Cu K}\alpha$ radiation. Microstructure observation and compositional analysis were performed using a scanning electron microscopy (SEM; Hitachi High-Technologies TM3000) equipped with energy dispersive X-ray spectrometry (EDX; Oxford Instruments SwiftED 3000). The magnetic susceptibility was measured by a SQUID magnetometer (Quantum Design MPMS-XL5s).

3. Results and discussion

Figures 1(a)-(c) show XRD patterns of TM -free or TM co-doped $(\text{Ca,RE})112$ samples for $\text{RE} = \text{Ce, Nd, Sm, Eu}$ and Gd . $(\text{Ca,RE})112$ phase formed as main phase in all samples, and impurity FeAs were always detected. BN detected in some samples is contaminated from high pressure media. The intensity of 002 peaks ($\sim 17^\circ$) of Ce, Nd, Sm doped samples are higher or almost same compared to that of main peaks ($\sim 37^\circ$), probably due to plate-like $(\text{Ca,RE})112$ crystals. Figure 1(d) shows a typical surface image of Co-co-doped $(\text{Ca,Sm})112$ bulk sample. The bulk is composed by plate-like crystals. Similar images were obtained for other RE doped samples.

Figures 2(a)-(d) show the temperature dependences of the zero-field cooled (ZFC) and field cooled (FC) magnetization curves of TM -free, Co or Ni co-doped $(\text{Ca,RE})112$ ($\text{RE} = \text{La-Gd}$) samples. Ni co-doping for $(\text{Ca,La})112$ decreased T_c from 38 K to 36 K, while superconducting transition became sharp similar to that of Co-co-doped samples^[13].

On the other hand, increases in T_c by Co-co-doping were observed in other $(\text{Ca,RE})112$ samples. T_c of Co-co-doped $(\text{Ca,RE})112$ was 31, 36, 34, 33, 21 and 29 K for $\text{RE} = \text{Ce, Pr, Nd, Sm, Eu}$ and Gd , respectively. T_c exceeds 30 K for $\text{RE} = \text{La-Sm}$ in spite of direct substitution of Co for Fe site. Ni co-doping also increased T_c of $(\text{Ca,RE})112$ but their T_c were slightly lower compared to Co-co-doped samples. These results suggest that Ni co-doped samples are in overdoped state.

As shown in Figs. 2(a) and (d), increases of T_c by TM doping were also confirmed for $(\text{Ca,Ce})112$ and $(\text{Ca,Eu})112$, while their T_c values were relatively low compared to the other $(\text{Ca,RE})112$. These low T_c in Ce and Eu doped samples are consistent with that of RE 15% doped samples reported by Sala *et al.*^[7].

The low T_c of $(\text{Ca,Ce})112$ might be due to higher Ce concentration in the samples than that of other RE doped samples. To confirm the idea, Co 3% doped $(\text{Ca}_{0.925}\text{RE}_{0.075})112$ ($\text{RE} = \text{La, Ce}$) were synthesized under same conditions. Figures 3(a)-(c) show XRD patterns and ZFC and FC magnetization curves of the samples. Co-co-doped $(\text{Ca,RE})112$ phase formed as main phase in spite of low nominal doping level of RE in both samples. Decreasing nominal Ce composition increased T_c from 31 K to 35 K. On the other hand, T_c did not change by decreasing La composition in Co-co-doped $(\text{Ca,La})112$. These results suggest that the low T_c of $(\text{Ca}_{0.9}\text{Ce}_{0.1})112$ and $(\text{Ca}_{0.85}\text{Ce}_{0.15})112$ ^[7] is due to relatively higher Ce substitution level for Ca site in the resulting samples. Compositional analysis by EDX revealed that actual Ce composition at Ca site was 14.8 % in Ce 7.5% doped sample while it was 19.3% and 26% in Ce 10% and Ce 15%^[7] doped samples, respectively. The high Ce composition levels for Ca site is possibly due to ionic radii of Ce^{3+} (1.143 Å; C.N. = 8), which is closer to that of Ca^{2+} (1.120 Å) than that of La^{3+} (1.160 Å).

Figure 4(a) shows dependence of T_c on ionic radii of RE^{3+} of TM -free and TM co-doped $(\text{Ca,RE})112$, including the data of RE 15% doped samples^[7]. For TM -free compounds, a trend that T_c decrease according to decrease of ionic radii of RE^{3+} was found except for Ce and Eu doped samples showing exceptionally low T_c . Same tendency was observed for Co or Ni co-doped samples. On the other hand, T_c of the Co-co-doped $(\text{Ca}_{0.925}\text{Ce}_{0.075})112$ was close to that of Co-co-doped $(\text{Ca}_{0.9}\text{La}_{0.1})112$ and $(\text{Ca}_{0.9}\text{Pr}_{0.1})112$. Figure 4 (b) shows relationship between interlayer distance between Fe planes $d_{\text{Fe-Fe}}$ values analyzed from XRD results and ionic radii of RE^{3+} of TM -free and Co 3% co-doped $(\text{Ca,RE})112$ samples. The values of $d_{\text{Fe-Fe}}$ decreased following decrease of ionic radii of RE^{3+} . However, those of Eu doped samples were relatively large considering ionic radii of Eu^{3+} (1.066 Å; C.N. = 8). Exceptionally

large $d_{\text{Fe-Fe}}$ in (Ca,Eu)112 was also reported in *RE* 15% doped samples by Sala *et al.*^[7]. Co-existence of Eu^{2+} (1.25 Å: C.N. = 8) and Eu^{3+} (1.066 Å) can be considered as the reason for relatively low T_c and the enlarged $d_{\text{Fe-Fe}}$ of (Ca,Eu)112. Stürzer *et al.* have reported *RE* (*RE* = Y, La-Nd, Sm-Lu) doping effect for $\text{Ca}_{10}(\text{Pt}_3\text{As}_8)(\text{Fe}_2\text{As}_2)_5$ (10-3-8)^[14], which have similar crystal structure to (Ca,*RE*)112. In these compounds, larger unit cell than other *RE* doped 10-3-8 and absence of superconductivity were observed in Eu doped 10-3-8. These are similar to that of (Ca,Eu)112, though superconductivity above 12 K was observed in (Ca,Eu)112. In addition, $d_{\text{Fe-Fe}}$ values are decreased by Co-co-doping with 0.01-0.02 Å compared to *TM*-free samples. This result is similar to the decrease in *c*-axis length by Co doping in LaFeAsO ^[15] and CaFeAsH ^[16], indicating that Co-co-doping also accompanies electron doping in (Ca,*RE*)112. Further careful studies are needed to clarify the reason of relatively high T_c by direct *TM* doping to Fe site which increases electron carrier in already electron overdoped (Ca,*RE*)112^[11].

4. Summary

In summary, Co or Ni co-doped (Ca,*RE*)112 have been synthesized for *RE* = La-Gd and their superconducting properties were investigated. Co or Ni co-doping improved superconducting properties of all (Ca,*RE*)112 samples. T_c s exceeding 30 K were observed in Co-co-doped (Ca,*RE*)112 (*RE* = La-Sm) in spite of direct *TM* doping to Fe site. T_c was found to decrease with a decrease in ionic radii of RE^{3+} except for Ce and Eu doped samples. In the case of (Ca,Ce)112, T_c increased by decreasing nominal Ce composition and T_c of Co-co-doped ($\text{Ca}_{0.925}\text{Ce}_{0.075}$)112 almost followed the T_c trend. On the other hand, exceptionally low T_c and long $d_{\text{Fe-Fe}}$ was found in (Ca,Eu)112, suggesting the co-existence of Eu^{2+} and Eu^{3+} . Slight decrease in $d_{\text{Fe-Fe}}$ by Co-co-doping was also confirmed.

Acknowledgements

This work was partly supported by the JSPS KAKENHI Grant Number 26390045, Izumi Science and Technology Foundation, and European Union-Japan project SUPER-IRON (grant agreement No. 283204).

References

- [1] Y. Kamihara, T. Watanabe, M. Hirano, H. Hosono, *J. Am. Chem. Soc.* 130 (2008) 3296–3297.
- [2] F.C. Hsu, J.Y. Luo, K.W. Yeh, T.K. Chen, T.W. Huang, P. M. Wu, Y.C. Lee, Y.L. Huang, Y.Y. Chu, D.C. Yan, M.K. Wu, *Proc. Natl. Acad. Sci. U.S.A.* 23 (2008) 14262-14264.
- [3] M.J. Pitcher, D.R. Parker, P. Adamson, S.J.C. Herkelrath, A.T. Boothroyd, R.M. Ibberson, M. Brunelli, S.J. Clarke, *Chem. Commun.* (2008) 5918-5920.
- [4] M. Rotter, M. Tegel, D. Johrendt, *Phys. Rev. Lett.* 101 (2008) 107006.
- [5] N. Katayama, K. Kudo, S. Onari, T. Mizukami, K. Sugawara, Y. Sugiyama, Y. Kitahama, K. Iba, K. Fujimura, N. Nishimoto, M. Nohara, H. Sawa, *J. Phys. Soc. Jpn.* 82 (2013) 123702
- [6] H. Yakita, H. Ogino, T. Okada, A. Yamamoto, K. Kishio, T. Tohei, Y. Ikuhara, Y. Gotoh, H. Fujihisa, K. Kataoka, H. Eisaki, J. Shimoyama, *J. Am. Chem. Soc.* 136 (2014) 846–849.
- [7] A. Sala, H. Yakita, H. Ogino, T. Okada, A. Yamamoto, K. Kishio, S. Ishida, A. Iyo, H. Eisaki, M. Fujioka, Y. Takano, M. Putti, J. Shimoyama, *Appl. Phys. Express* 7 (2014) 073102.
- [8] X. Wu, C. Le, Y. Liang, S. Qin, H. Fan, J. Hu, *Phys. Rev. B* 89 (2014) 205102.
- [9] G. Wang, X. Shi, L. Zhang, X. Yi, *Solid State Commun.* 200 (2014) 61-65.
- [10] W. Zhou, J. Zhuang, F. Yuan, X. Li, X. Xing, Y. Sun, Z. Shi, *Appl. Phys. Express* 7 (2014) 063102.
- [11] K. Kudo, T. Mizukami, Y. Kitahama, D. Mitsuoka, K. Iba, K. Fujimura, N. Nishimoto, Y. Hiraoka, M. Nohara, *J. Phys. Soc. Jpn.* 83 (2014) 025001.
- [12] K. Kudo, Y. Kitahama, K. Fujimura, T. Mizukami, H. Ota, M. Nohara, *J. Phys. Soc. Jpn.* 83 (2014) 093705.
- [13] H. Yakita, H. Ogino, A. Sala, T. Okada, A. Yamamoto, K. Kishio, A. Iyo, H. Eisaki, J. Shimoyama, submitted to *Supercond. Sci. Technol.*
- [14] T. Stürzer, G. Derondeau, E.M. Bertschler, D. Johrendt, *Solid State Commun.* 201 (2015) 36-39.
- [15] C. Wang, Y.K. Li, Z.W. Zhu, S. Jiang, X. Lin, Y.K. Luo, S. Chi, L.J. Li, Z. Ren, M. He, H. Chen, Y.T. Wang, Q. Tao, G.H. Cao, Z.A. Xu, *Phys. Rev. B* 79 (2009) 054521
- [16] P. Cheng, Z.J. Xiang, G.J. Ye, X.F. Lu, B. Lei, A.F. Wang, F. Chen, X. G. Luo, *Supercond. Sci. Technol.* 27 (2014) 065012

Fig.1. XRD patterns of (a) $(\text{Ca}_{0.9}\text{RE}_{0.1})\text{FeAs}_2$, (b) $(\text{Ca}_{0.9}\text{RE}_{0.1})\text{Fe}_{0.97}\text{Co}_{0.03}\text{As}_2$ and (c) $(\text{Ca}_{0.9}\text{RE}_{0.1})\text{Fe}_{0.97}\text{Ni}_{0.03}\text{As}_2$ ($\text{RE} = \text{Ce, Nd, Sm, Eu, Gd}$) sintered for 1 h under 2 GPa, and (d) secondary electron image of Co-co-doped (Ca,Sm)112 bulk sample

Fig.2. Temperature dependence of the ZFC and FC magnetization curves of $(\text{Ca}_{0.9}\text{RE}_{0.1})\text{FeAs}_2$, $(\text{Ca}_{0.9}\text{RE}_{0.1})\text{Fe}_{0.97}\text{Co}_{0.03}\text{As}_2$ and $(\text{Ca}_{0.9}\text{RE}_{0.1})\text{Fe}_{0.97}\text{Ni}_{0.03}\text{As}_2$ with (a) $\text{RE} = \text{La, Ce}$ (b) $\text{RE} = \text{Pr, Nd}$, (c) $\text{RE} = \text{Sm, Gd}$ and (d) $\text{RE} = \text{Eu}$

Fig.3. (a) XRD patterns and temperature dependence of the ZFC and FC magnetization curves of (b) $(\text{Ca}_{1-x}\text{La}_x)\text{Fe}_{0.97}\text{Co}_{0.03}\text{As}_2$ and (c) $(\text{Ca}_{1-x}\text{Ce}_x)\text{Fe}_{0.97}\text{Co}_{0.03}\text{As}_2$ ($x = 0.075, 0.1$)

Fig.4. (a) T_c and (b) $d_{\text{Fe-Fe}}$ for the high pressure synthesized samples as a function of ionic radii of the RE^{3+} ions in a coordination number (C. N.) of 8

Figure 1

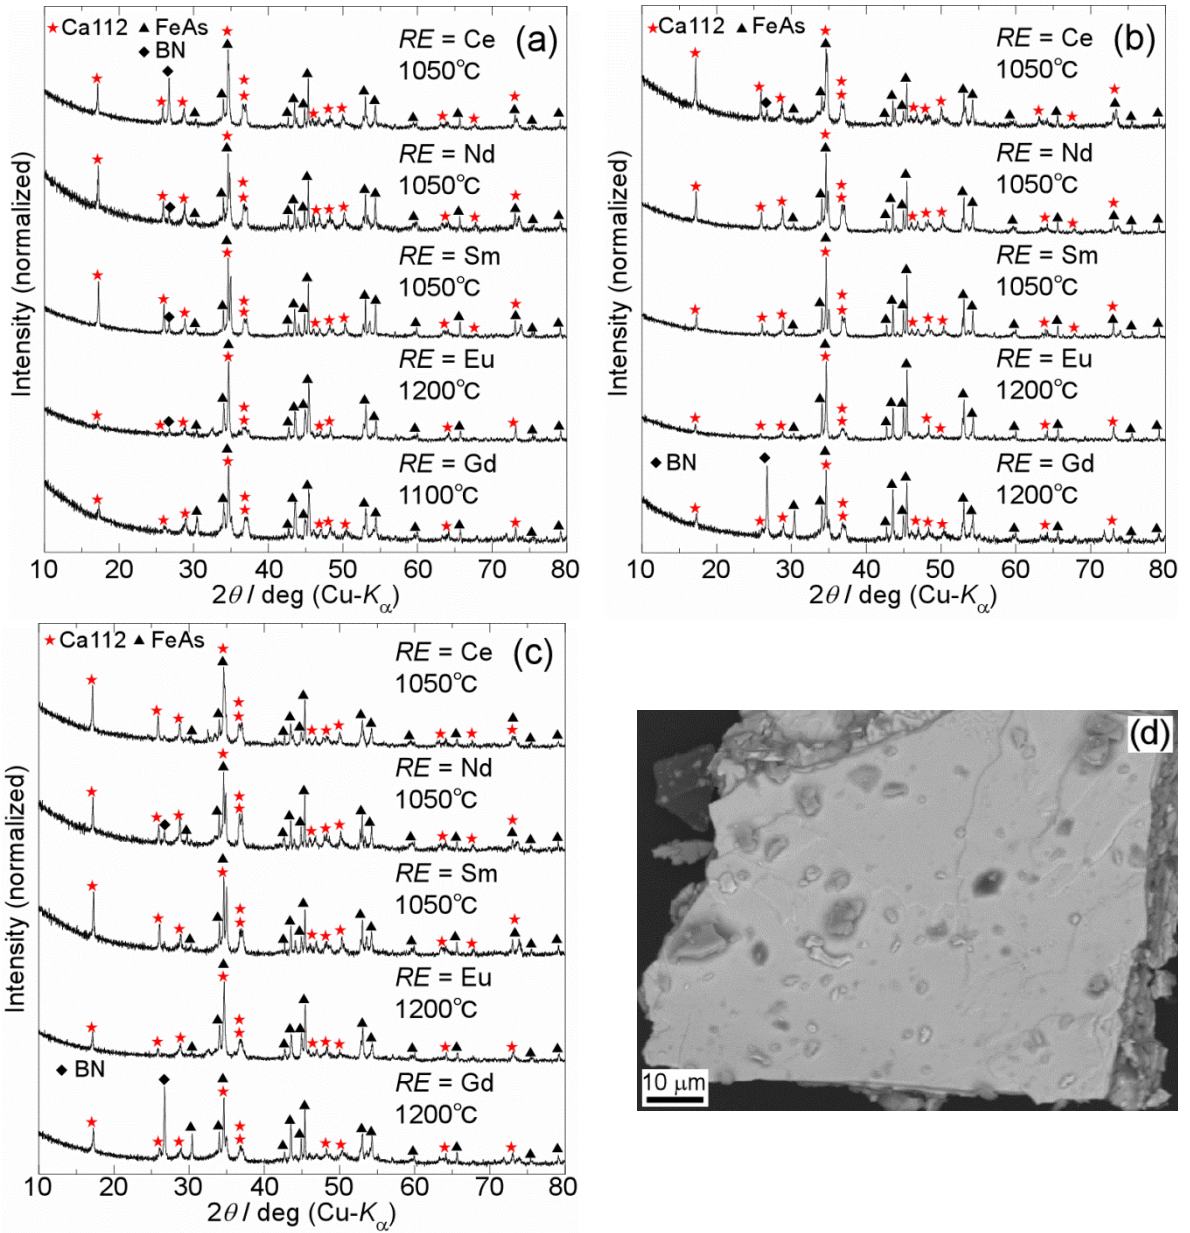


Figure 2

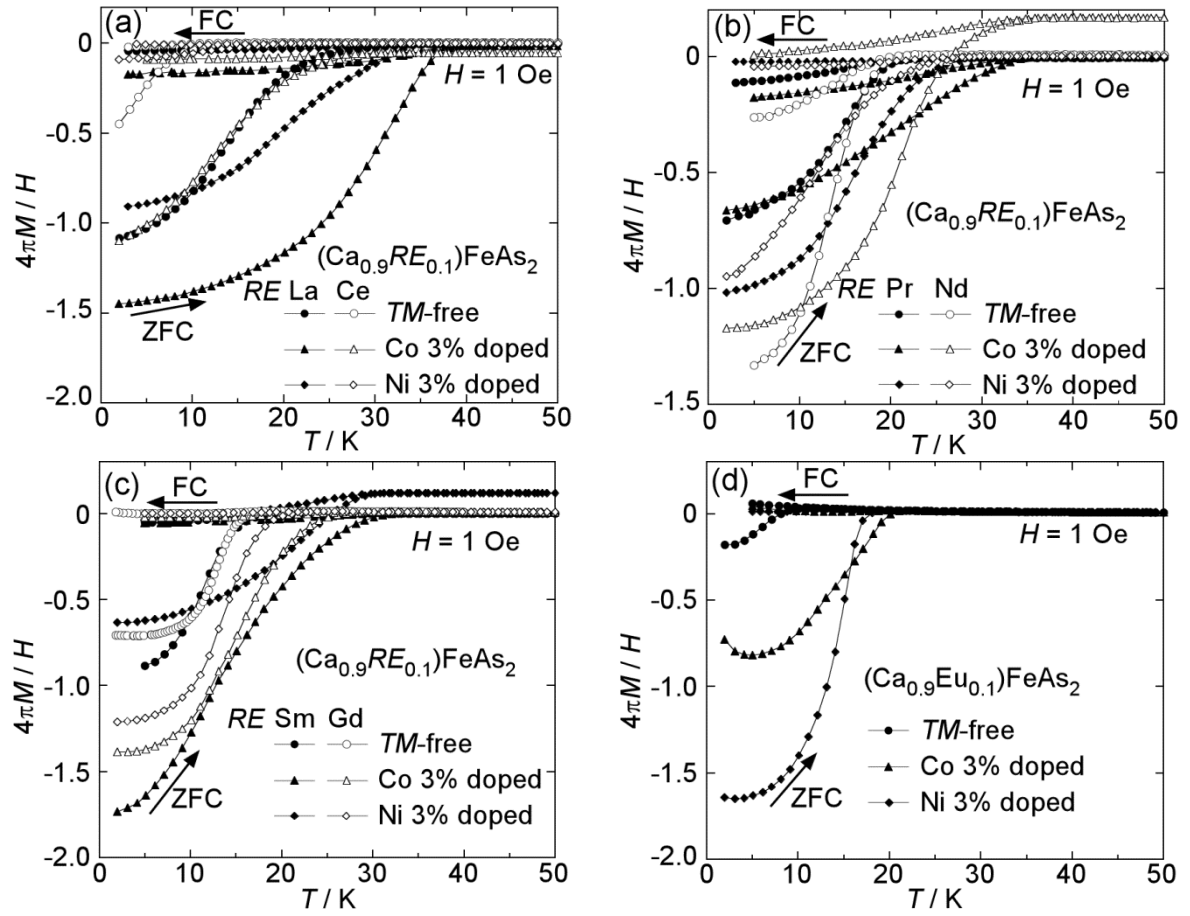


Figure 3

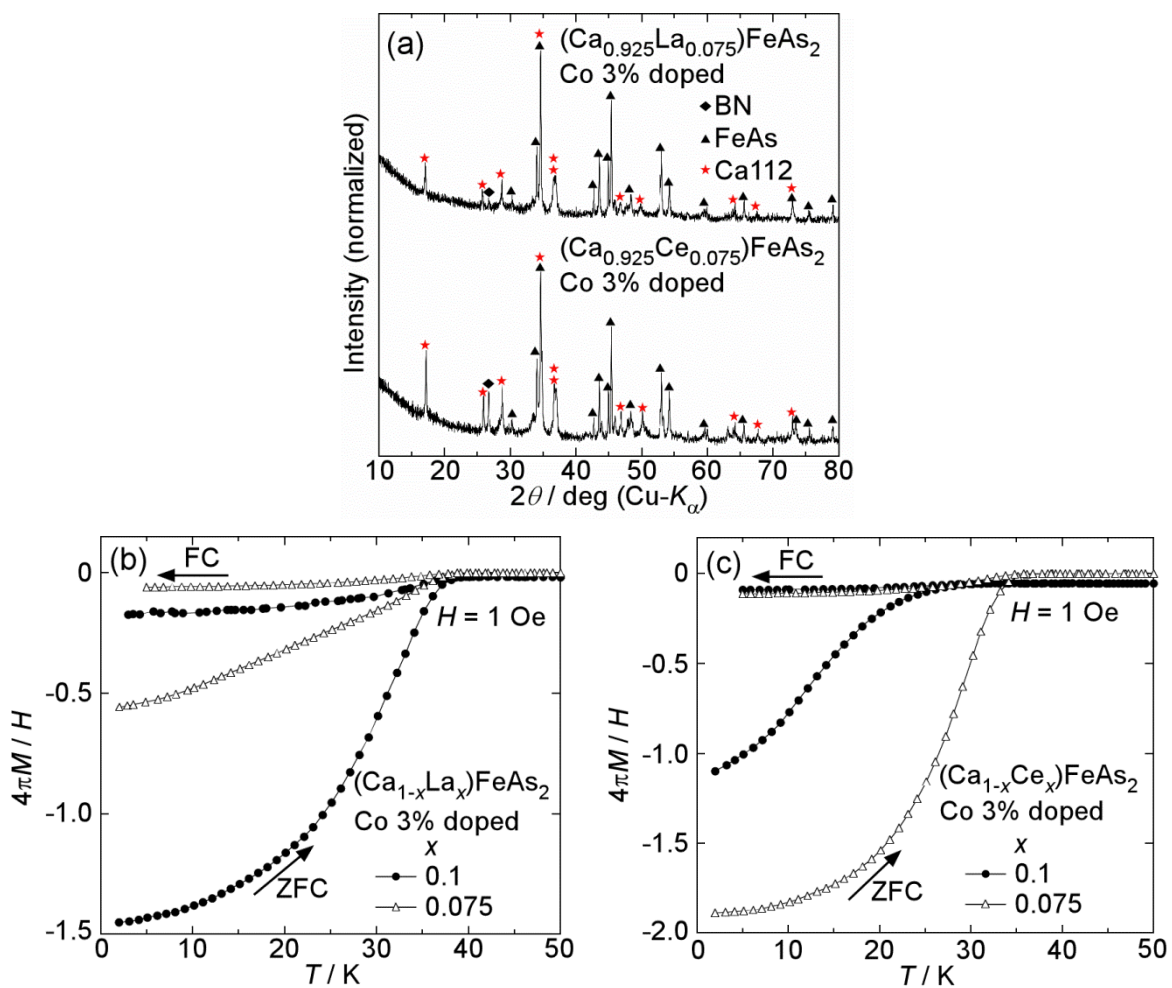


Figure 4

