

Ab initio calculation of the spin lattice relaxation time T_1 for nitrogen-vacancy centers in diamond

J.Gugler,¹ T.Astner,² A. Angerer,² J. Schmiedmayer,² J.Majer,² and P. Mohn¹

¹*Institute of Applied Physics, TU Wien, Wiedner Hauptstr. 8-10/134, 1040 Vienna, Austria**

²*Vienna Center for Quantum Science and Technology, Atominstitut, TU Wien, Stadionallee 2, 1020 Vienna, Austria*

We investigate the fundamental mechanism of spin phonon coupling in the negatively charged nitrogen vacancy center (NV^-) in diamond in order to calculate the spin lattice relaxation time T_1 and its temperature dependence from first principles. Starting from the dipolar spin-spin interaction between two electrons, we couple the spins of the electrons to the movements of the ions and end up with an effective spin-phonon interaction potential V_{s-ph} . Taking this time dependent potential as a perturbation of the system, a Fermi's golden rule expression for transition rates is obtained which allows to calculate the spin lattice relaxation time T_1 . We find that the temperature dependence of T_1 is determined by the zero temperature transition rate Γ_0 . We simulate the color center *ab initio* to extract the figures necessary to quantify Γ_0 . We calculate the local phonon modes of the color center within the harmonic approximation using the small displacement method and extract the phononic density of states and bandstructure by diagonalizing the dynamical matrix. We show that our model allows to calculate T_1 in good agreement with experimental observations.

PACS numbers: 63.20.kd, 76.30.Mi

I. INTRODUCTION

The negatively charged nitrogen vacancy center (NV^-) is an important colour center in diamond¹ that consists of a substitutional nitrogen atom adjacent to a vacant lattice site. Six electrons are located at the center, which exhibits C_{3v} -symmetry, and they form an electronic ground state spin triplet transforming according to the A_2 representation. This state is further split by the dipolar spin-spin interaction into a $m_s = 0$ ground state and two degenerate excited $m_s = \pm 1$ states with a zero field splitting constant $D/h = 2.88$ GHz.^{2,3} The spin of the system can be prepared and read out optically⁴ which leads to many applications in magnetometry,⁵⁻⁸ biolabelling,⁹ nano-sensing^{10,11} and makes it a promising candidate for a solid state quantum bit.¹²⁻¹⁴ Since the spin is the quantity to be manipulated in applications, a proper understanding of spin relaxation is of utmost importance. In this paper we deal with the longitudinal spin relaxation in the 3A_2 ground state triplet caused by the interaction of the electron spins with the phonons of the crystal. Experimental studies^{15,16} have suggested that the temperature dependence of the spin-lattice relaxation rate in a range between 10 K to 500 K is well described by a two-phonon Raman process and an Orbach process,¹⁷ however there are measurements where a different behaviour was observed.¹⁸ Also, the measured relaxation rates differ by one order of magnitude for different samples. To un-

derstand and predict spin-lattice relaxation times quantitatively in this system the fundamental mechanism of spin-phonon coupling has to be investigated. Insight into this coupling mechanism is most easily achieved by considering first-order processes, which are dominant at low temperatures around the spin transition energy D of the spins ($T = 138$ mK). At these temperatures the phonon spectrum is frozen out and thus higher-order processes are suppressed. In a recent paper¹⁹ a direct single phonon relaxation process and spin lattice relaxation times T_1 of up to 8 h in this temperature regime were observed using a cavity QED protocol. Since no higher order processes were observed, the measured data are suitable to obtain a fundamental understanding of the spin-phonon coupling mechanism in this system.

This paper is organized as follows: In Sec. II we derive an effective spin-phonon interaction V_{s-ph} starting from the dipolar spin-spin interaction between two electrons and we give an expression for the spin-lattice relaxation rate Γ_1 . In Sec. III we explain the computational methods used to calculate Γ_1 *ab initio* by modelling both the electronic and phononic properties of the center by means of density functional theory. In Sec. IV the influence of lattice defects on Γ_1 is investigated and a comparison of our results with experimental data is presented followed by the conclusion in Sec. V.

II. THEORY

The idea to couple the spins to the phonons starting from the dipolar spin-spin interaction goes back to Waller²⁰ and was the first impact on spin-lattice relaxation in general. It was later neglected because most of the systems show a spin-orbit driven spin relaxation.²¹⁻²⁵ The NV^- center containing only low Z elements has a small spin-orbit coupling and the ground state triplet fine structure is given by the spin-spin interaction, which motivates an investigation of the spin-spin interaction as the driving source of spin lattice relaxation. The relaxation mechanism is depicted in

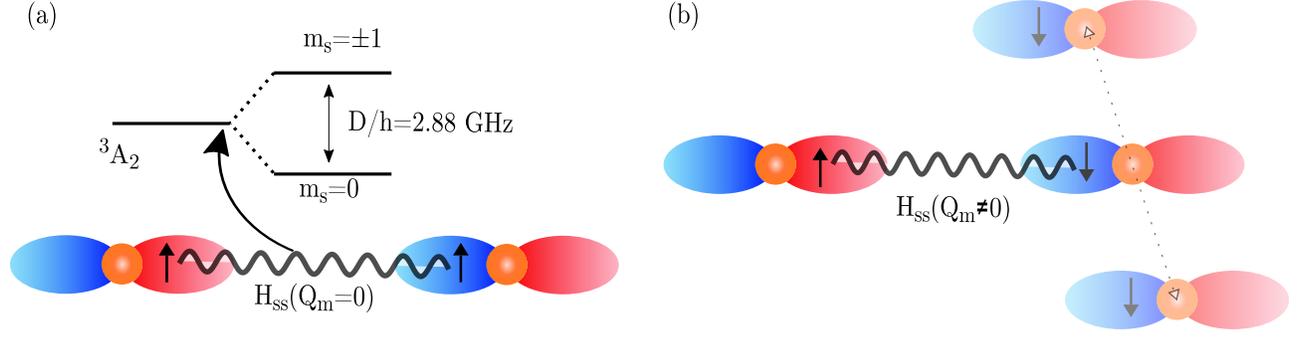


FIG. 1: (a) In the static case (no phonons in the system) the spins (\uparrow / \downarrow) of the NV^- center interact via the static spin-spin interaction (wiggly line), which is responsible for the fine structure splitting of the 3A_2 ground state. (b) In the case the electron positions are coupled to phonons (right side of (b)), H_{ss} becomes phonon dependent and can induce a spin flip. This allows to exchange energy between the spin system and the lattice and therefore allows the spin-system to equilibrate with the phonon bath.

Fig. 1. If a phonon is excited, the dipolar spin-spin interaction

$$H_{ss} = - \underbrace{\frac{\mu_0 g_e^2 \mu_B^2}{4\pi}}_{:=\alpha} \frac{3(\mathbf{r}_{ij} \cdot \mathbf{S}_i)(\mathbf{r}_{ij} \cdot \mathbf{S}_j) - (\mathbf{S}_i \cdot \mathbf{S}_j)r_{ij}^2}{|\mathbf{r}_{ij}|^5} \quad (1)$$

between the i -th and j -th electron is altered, because the electronic distance vector \mathbf{r}_{ij} depends on the displacements of the ions $\{\mathbf{Q}_m\}$. Here μ_0 denotes the vacuum permeability, g_e the g-factor²⁶ of the electron which is close to that of a free electron in the NV^- center with a value of 2.0028, μ_B is the Bohr magneton and \mathbf{S}_i and \mathbf{S}_j are the spin vectors of the i -th and j -th electron. In his original work Waller neglected the orbital character of the electrons and treated them as point sources located at the positions of ions. This assumption will be dropped in the following derivation. The change of the position of the electron with the ionic motion has to be modelled to couple the electronic spin vectors in H_{ss} to the ionic movements. This is achieved by defining a region Ω around each ion, in which the electronic orbital follows the movement of the ions rigidly, resulting in the electronic distance vector

$$\mathbf{r}_{ij}(\{\mathbf{Q}_m\}) = \mathbf{r}_{ij}(\{\mathbf{Q}_m = 0\}) + \sum_m \mathbf{Q}_m \underbrace{(\Theta(\mathbf{r}_i \in \Omega_m) - \Theta(\mathbf{r}_j \in \Omega_m))}_{:=\Delta\Theta_{ij}^m}, \quad (2)$$

where $\Theta(\mathbf{r} \in \Omega)$ is 1, if the electron is inside Ω and 0 otherwise. For our calculations we use the Wigner-Seitz cell for Ω , dividing space geometrically. Since the ionic displacements in the low temperature regime are very small (mean square displacements are in the order of 10^{-4} \AA^{-2}), a Taylor expansion to first order in \mathbf{Q}_m is sufficient to calculate the transition rates between a $m_s = \pm 1$ and a $m_s = 0$ state. Thus, the spin-phonon interaction reads:

$$V_{s-ph}(\{\mathbf{Q}_m\}) = \sum_m \mathbf{Q}_m \frac{\partial H_{ss}}{\partial \mathbf{R}_m} = \alpha \sum_m \Delta\Theta_{ij}^m \left(\frac{3((\mathbf{Q}_m \cdot \mathbf{S}_i)(\mathbf{r}_{ij} \cdot \mathbf{S}_j) + (\mathbf{r}_{ij} \cdot \mathbf{S}_i)(\mathbf{Q}_m \cdot \mathbf{S}_j))}{|\mathbf{r}_{ij}|^5} - \frac{15(\mathbf{r}_{ij} \cdot \mathbf{S}_i)(\mathbf{r}_{ij} \cdot \mathbf{S}_j)}{|\mathbf{r}_{ij}|^7} (\mathbf{r}_{ij} \mathbf{Q}_m) + \frac{3(\mathbf{S}_i \cdot \mathbf{S}_j)}{|\mathbf{r}_{ij}|^5} (\mathbf{r}_{ij} \mathbf{Q}_m) \right) \quad (3)$$

To extract the relevant matrix elements responsible for a transition between the 3A_2 levels, the spin operators \mathbf{S} are expanded in raising and lowering operators. The Hamiltonian in (3) contains terms $(\mathbf{a} \cdot \mathbf{S}_i)(\mathbf{b} \cdot \mathbf{S}_j)$, where \mathbf{a} and

\mathbf{b} are elements of $\{\mathbf{r}_{ij}, \mathbf{Q}_m\}$, and a term $\mathbf{S}_i \mathbf{S}_j$, which can be rewritten as

$$\begin{aligned}
(\mathbf{a} \cdot \mathbf{S}_i)(\mathbf{b} \cdot \mathbf{S}_j) &= (a^x S_i^x + a^y S_i^y + a^z S_i^z)(b^x S_j^x + b^y S_j^y + b^z S_j^z) = \\
&= \frac{1}{2} \left(\underbrace{S_i^+(a^x - ia^y)S_j^z b^z + S_i^-(a^x + ia^y)S_j^z b^z + S_i^z a^z S_j^+(b^x - ib^y) + S_i^z a^z S_j^-(b^x + ib^y)}_{\text{single spin flip events}} \right) + \\
&+ \frac{1}{4} \left(S_i^+(a^x - ia^y)S_j^+(b^x - ib^y) + S_i^-(a^x + ia^y)S_j^-(b^x + ib^y) + \right. \\
&\left. + S_i^+(a^x - ia^y)S_j^-(b^x + ib^y) + S_i^-(a^x + ia^y)S_j^+(b^x - ib^y) \right) + S_i^z a^z S_j^z b^z
\end{aligned} \tag{4}$$

and

$$\mathbf{S}_i \mathbf{S}_j = \frac{1}{2} (S_i^+ S_j^- + S_i^- S_j^+) + S_i^z S_j^z. \tag{5}$$

The only matrix elements, which can cause a transition in the ground state triplet, are those, that contain only a single raising or lowering operator and are underbraced in Eq. (4), the remaining terms account for double spin-flip or no spin-flip events. Taking only the spin-flip matrix elements of $V_{s\text{-ph}}$ in Eq. 3 into account we obtain the spin-flip potential

$$\begin{aligned}
V_{s\text{-ph}}^{\text{flip}} &= \alpha \sum_m \Delta \Theta_{ij}^m \left(\frac{3 \left((S_i^\pm S_j^z + S_i^z S_j^\pm) \left((r_{ij}^x \mp ir_{ij}^y) Q_m^z + (Q_m^x \mp iQ_m^y) r_{ij}^z \right) \right)}{2 |\mathbf{r}_{ij}|^5} \right. \\
&\quad \left. - \frac{15 \left((S_i^\pm S_j^z + S_i^z S_j^\pm) (r_{ij}^x \mp ir_{ij}^y) r_{ij}^z \right) (\mathbf{r}_{ij} \cdot \mathbf{Q}_m)}{2 |\mathbf{r}_{ij}|^7} \right)
\end{aligned} \tag{6}$$

Likewise the ionic displacements \mathbf{Q}_m are written in second quantized form²⁷

$$\mathbf{Q}_m = i \sum_{\mathbf{q}, \rho} \sqrt{\frac{\hbar}{2M_m N \omega_{\mathbf{q}, \rho}}} (a_{-\mathbf{q}, \rho}^\dagger e^{i\omega_{\mathbf{q}, \rho} t} + a_{\mathbf{q}, \rho} e^{-i\omega_{\mathbf{q}, \rho} t}) \boldsymbol{\epsilon}_{\mathbf{q}, \rho}^m e^{i\mathbf{q} \mathbf{R}_m^0}. \tag{7}$$

Here M_m denotes the mass of the ion, N the number unit cells, a^\dagger/a the raising/lowering operator, $\boldsymbol{\epsilon}_{\mathbf{q}, \rho}^m$ the polarization vector of the m -th ion in the mode and \mathbf{R}_m^0 is the equilibrium position of the ion. Substituting Eq. (7) into Eq. (3) and taking $V_{s\text{-ph}}$ as a time dependent perturbation of the system leads to a Fermi's golden rule expression for a transition between the $m_s = \pm 1$ and the $m_s = 0$ states. The overall transition rate $\Gamma_{f \leftarrow i}$ from an initial to a final electronic state is obtained by a summation of the matrix elements of all final phonon states obeying energy conservation

$$\begin{aligned}
\Gamma_{f \leftarrow i} &= \frac{2\pi}{\hbar} \sum_f |\langle \tilde{N}_f, m_s^f | V_{s\text{-ph}}^{\text{flip}} | N_i, m_s^i \rangle|^2 \delta(E_f - E_i - h\nu) \\
&= \frac{2\pi}{\hbar} \sum_{\mathbf{k}, \lambda} |\langle m_s^f | \alpha \sum_m i \sum_{\mathbf{q}, \rho} \sqrt{\frac{\hbar}{2M_m N \omega_{\mathbf{q}, \rho}}} e^{i\mathbf{q} \mathbf{R}_m^0} \Delta \Theta_{ij}^m \cdot \\
&\quad \left(\frac{3 \left((S_i^\pm S_j^z + S_i^z S_j^\pm) (r_{ij}^x \mp ir_{ij}^y) \langle \tilde{N}_f | (a_{-\mathbf{q}, \rho}^\dagger + a_{\mathbf{q}, \rho}) \boldsymbol{\epsilon}_{\mathbf{q}, \rho}^{m,z} | N_i \rangle \right)}{2 |\mathbf{r}_{ij}|^5} + \frac{3 \langle \tilde{N}_f | (a_{-\mathbf{q}, \rho}^\dagger + a_{\mathbf{q}, \rho}) (\boldsymbol{\epsilon}_{\mathbf{q}, \rho}^{m,x} \mp i\boldsymbol{\epsilon}_{\mathbf{q}, \rho}^{m,y}) | N_i \rangle r_{ij}^z}{2 |\mathbf{r}_{ij}|^5} \right) \\
&\quad \left. - \frac{15 \left((S_i^\pm S_j^z + S_i^z S_j^\pm) (r_{ij}^x \mp ir_{ij}^y) r_{ij}^z \right) (\mathbf{r}_{ij} \cdot \langle \tilde{N}_f | (a_{-\mathbf{q}, \rho}^\dagger + a_{\mathbf{q}, \rho}) \boldsymbol{\epsilon}_{\mathbf{q}, \rho}^m | N_i \rangle)}{2 |\mathbf{r}_{ij}|^7} \right) |m_s^i\rangle|^2 \delta(E_f - E_i - h\nu).
\end{aligned} \tag{8}$$

The raising and lowering operators acting on the initial phononic state $|N_i\rangle$ give $\sqrt{N_{\text{ph}} + 1}$ and $\sqrt{N_{\text{ph}}}$ as eigenvalues of the particular state, where N_{ph} is the occupation number of the phonons. We assume N_{ph} to be the thermal occupations following the Bose-Einstein distribution. Putting everything together and considering the fact that only phonons with a single frequency at the spin-transition energy D can take part in this process, the transition rates for

emission and absorption of a phonon $\Gamma_{f \leftarrow i}$ read

$$\Gamma_{f \leftarrow i} = \frac{\alpha^2 [N_{\text{ph}} + 1]^{emission} [N_{\text{ph}}]^{absorption}}{\hbar 2N\omega} \sum_{\mathbf{k}, \lambda} |\langle m_s^f | \sum_m \sqrt{\frac{1}{M_m}} \Delta \Theta_{ij}^{m_s} e^{i\mathbf{k}\mathbf{R}_0^m} \left(\frac{3(S_i^\pm S_j^z + S_i^z S_j^\pm)(r_{ij}^x \mp ir_{ij}^y) \epsilon_{\mathbf{k}, \lambda}^{m, z}}{2|\mathbf{r}_{ij}|^5} + \frac{3(\epsilon_{\mathbf{k}, \lambda}^{m, x} \mp i\epsilon_{\mathbf{k}, \lambda}^{m, y}) r_{ij}^z}{2|\mathbf{r}_{ij}|^5} - \frac{15((S_i^\pm S_j^z + S_i^z S_j^\pm)(r_{ij}^x \mp ir_{ij}^y) r_{ij}^z)(\mathbf{r}_{ij} \epsilon_{\mathbf{k}, \lambda}^m)}{2|\mathbf{r}_{ij}|^7} \right) |m_s^i \rangle|^2 \delta(\nu = 2.88 \text{ GHz}) \quad (9)$$

To emphasize the temperature dependence of the relaxation rate this is rewritten as

$$\Gamma_{f \leftarrow i} = \begin{cases} (N_{\text{ph}} + 1)\Gamma_0 & \text{for emission of a phonon} \\ N_{\text{ph}}\Gamma_0 & \text{for absorption of a phonon} \end{cases} \quad (10)$$

with Γ_0 being the transition rate at zero temperature. To simulate an ensemble of spins relaxing from a non-equilibrium spin-distribution to equilibrium with the environment, both deexcitations and excitations of spins have to be considered²⁸ and the following rate equations for the occupations N_{m_s} have to be solved for our system with a degenerate excited state:

$$\begin{aligned} \dot{N}_{m_s \pm 1} &= -\Gamma_0(N_{\text{ph}} + 1)N_{m_s \pm 1} + 2\Gamma_0 N_{\text{ph}} N_{m_s=0} \\ \dot{N}_{m_s=0} &= -\dot{N}_{m_s \pm 1} \end{aligned} \quad (11)$$

The solution is straightforward by introducing the occupation difference $\Delta N = N_{m_s=\pm 1} - N_{m_s=0}$, since it obeys a simple exponential decay law to its thermal equilibrium value ΔN_{th} according to

$$\frac{d}{dt} \Delta N = - \underbrace{(3N_{\text{ph}} + 1)\Gamma_0}_{\Gamma_1 = 1/T_1} (\Delta N - \Delta N_{\text{th}}). \quad (12)$$

The calculation of the zero temperature transition rate Γ_0 between the 3A_2 sublevels is sufficient to extract the transition rates in the low temperature regime, where single phonon processes are dominating over two phonon-processes.

III. METHODS

The calculation of Γ_0 requires the spin-polarized electronic orbitals as well as the phononic bandstructure, density of states and the polarization vectors for all the modes. We perform *ab initio* calculations using density functional theory on supercells containing 64,128 and 512 lattice sites with one NV^- center employing the Vienna Ab initio Simulation Package (VASP²⁹) using projector augmented wave pseudopotentials.³⁰ We use the local density approximation and a generalized gradient approximation included in the PBE³¹ exchange correlation potential for structural relaxations and force calculations. The electron properties in the relaxed structure are also calculated using the SCAN³² and HSE functional.^{33,34} Plane waves up to a cutoff of 700 eV are included and the first Brillouin zone is sampled with a $4 \times 4 \times 4$ Monkhorst Pack grid.³⁵ A subtle relaxation of the ions resulting in forces on the atoms of less than $1 \frac{\text{meV}}{\text{\AA}}$ shows that the neighbouring carbon atoms and the nitrogen atom move away from the vacancy, where the nitrogen atom is further displaced in accordance with an earlier study.³⁶ Since we are interested in the spin-polarized

orbitals, we use the relaxed positions to calculate the electronic band structure. It is found that the a_{1, e_x} and e_y orbitals are located inside the bandgap and that e_x and e_y are the spin-polarized orbitals (see Fig. 2a). This familiar result^{26,36-38} allows to extract these orbitals by applying the wannier90 package^{39,40} to obtain the maximally localized orbitals on the nearest neighbour atoms of the vacancy. By considering the symmetry of the defect we add up the maximally localized orbitals to fulfill the C_{3v} symmetry constraints and end up with the spin polarized e_x and e_y orbitals of the 3A_2 groundstate shown in Fig. 2b. Building Slater determinants with these orbitals we calculate the electronic matrix elements $\langle m_s^f | \frac{r_{ij}^x \mp ir_{ij}^y}{|\mathbf{r}_{ij}|^5} |m_s^i \rangle$, $\langle m_s^f | \frac{r_{ij}^z}{|\mathbf{r}_{ij}|^5} |m_s^i \rangle$, $\langle m_s^f | \frac{(r_{ij}^x \mp ir_{ij}^y) r_{ij}^z r_{ij}^{x/y/z}}{|\mathbf{r}_{ij}|^7} |m_s^i \rangle$, which occur for every phononic polarization in Eq. (10). The phonons are modelled by using the small displacement method within the harmonic approximation similar to a previous study.⁴¹ We use the PHONOPY package⁴² to extract the necessary displacements to build the dynamical matrix and apply it to the diagonaliza-

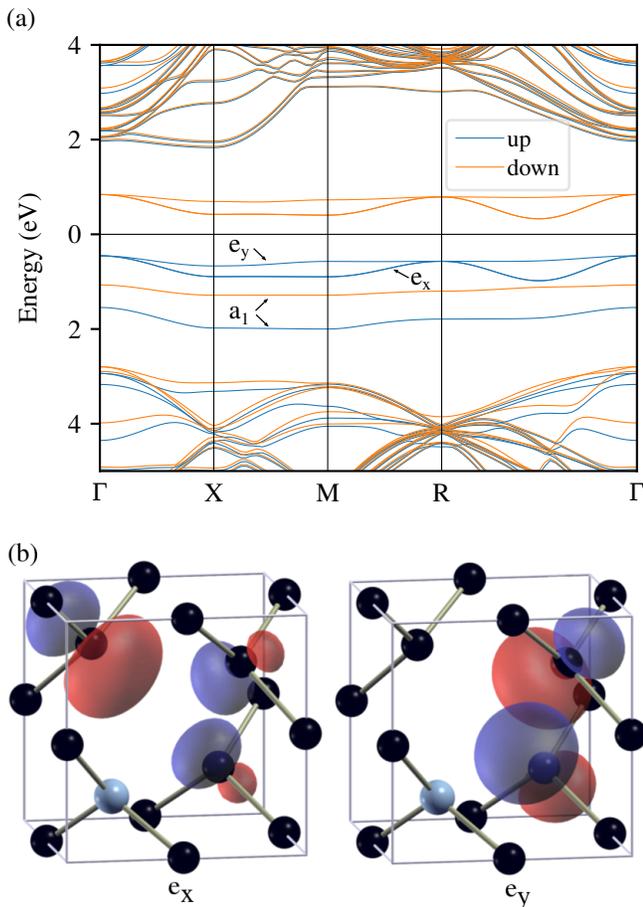


FIG. 2: (a) The spin-polarized bandstructure calculated with HSE in a supercell containing 64 atoms. 4 electrons of the NV^- center are located inside the bandgap and occupy the three orbitals a_1, e_x and e_y . The blue lines denote spin up bands, the orange ones spin down bands. The electrons in the e_x and e_y orbitals are responsible for spin-polarization. (b) The isosurfaces of the spin-polarized e_x and e_y orbitals. The maximally localized orbitals c_1, c_2, c_3 and n on the 4 adjacent atoms next to the vacancy were added up to fulfill the C_{3v} symmetry constraints^{26,38} resulting in $e_x \propto 2c_3 - c_1 - c_2$ and $e_y \propto c_1 - c_2$. It is evident, that the spin density is mainly located at the carbon atoms adjacent to the vacancy.

tion thereof. We sample the Brillouin zone with a very dense mesh to extract 10 000 phonon polarization vectors at the transition frequency per band and the respective local group velocities for any particular \mathbf{k} -point. The phononic density of states is calculated according to a Debye-model where we take the \mathbf{k} -dependence of the group velocity into account. With the polarization vectors $\{\epsilon_{\mathbf{k},\lambda}^m\}$ and the density of states in hand, we have sufficient data to perform the summation over all the final phonon modes and calculate the numerical value of the spin-lattice relaxation rate Γ_0 .

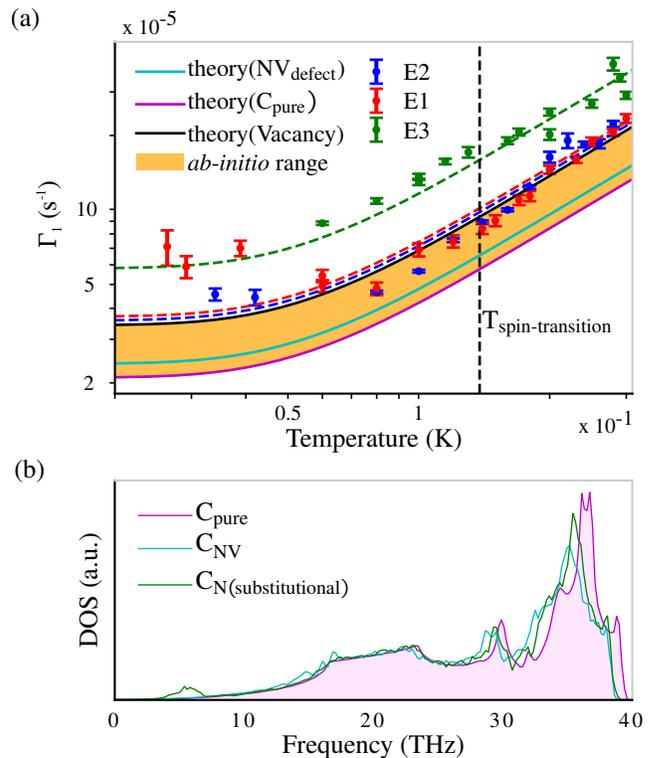


FIG. 3: (a) The measured spin-lattice relaxation rates for 3 different samples ($E1$, $E2$ and $E3$ [data taken from¹⁹]). Dashed lines are least square fits for the temperature dependence according to Eq. (12). The theoretical results (yellow range) depend on the phononic density of states: The magenta line denotes the calculated relaxation rate, if a Debye-model with the velocity of sound of a pure diamond is applied, the cyan line represents the case, where the \mathbf{k} -dependent sound velocity of the simulated cell with 1 NV^- center was used and the black line results for the DOS of a 64 lattice site diamond cell containing a vacancy. (b) Difference in the phononic density of states between a perfect diamond crystal (red) and diamond crystals with point defects. If a point defect is present the DOS is shifted towards lower energy excitations.

IV. RESULTS

After carrying out the calculations, we end up with a theoretically predicted temperature dependent relaxation rate Γ , which can be compared to the experiment. As shown in Fig. 3a we find a direct single phonon process^{28,43} at temperatures above the spin-transition $T \gg D/k_B$ where thermal phonons excite and deexcite the spins by induced emission or absorption resulting in a linear dependence of Γ on T . This temperature dependence stems from the high temperature limit of the Bose-Einstein distribution, where $N_{ph} \propto T$ in Eq. (12). At temperatures below the spin-transition the 2.88 GHz

phonons start to freeze out and the only decay channel left for a spin-transition is the temperature independent spontaneous emission of a phonon occurring with a rate Γ_0 which results in the observed plateau in the low temperature regime. To compare the calculated rates with experiment, the treatment of the samples has to be explained: To create NV^- centers in diamond, samples with a high initial nitrogen concentration (type Ib diamond) are irradiated by electrons, neutrons or ions in order to obtain vacancies followed by an annealing procedure.^{44–46} The influence of the radiation damage on the phononic density of states is essentially unknown, but irradiation will create point defects, which can shift the phononic density of states towards lower energy excitations.⁴⁷ We simulate this effect and calculate the density of states for diamond crystals with defects and compare them with a perfect crystal. Introducing point defects (substitutional nitrogens and vacancies) in the diamond structure the phononic density of states indeed shifts towards lower frequencies as illustrated in Fig. 3b. However, we can only estimate the phononic density of states in the irradiated crystals. We model the phonons using the phononic densities of states for the simulated cells and the calculated relaxation rates $\Gamma_{0,ab \textit{ initio}} = 2 \times 10^{-5} \text{ s}^{-1}$ to $3 \times 10^{-5} \text{ s}^{-1}$ are close to the lowest experimental values ($\Gamma_{0,exp} = 3.47(16) \times 10^{-5} \text{ s}^{-1}$).¹⁹

V. CONCLUSION

In this paper we have shown that the very low spin-lattice relaxation rates of the NV^- center in diamond can be explained by the change of the dipolar spin-spin inter-

action induced by the movement of the ions as proposed originally by Waller in 1932.²⁰ We coupled the electronic distance vector \mathbf{r}_{ij} to the ionic movement by a first order Taylor expansion in the ionic displacement vectors $\{\mathbf{Q}_m\}$ and ended up with an effective spin-phonon interaction V_{s-ph} . We applied this interaction as a perturbation of the system to calculate the transition rates between the 3A_2 ground state spin triplet *ab initio* using density functional theory by modelling the electronic wavefunctions and the phonons in a supercell containing 512 atoms. The calculated relaxation rates are comparable to the ones measured for samples that show little crystal damage. We propose that the deviation to samples with a strong irradiation damage is caused by the difference in the phononic density of states due to the irradiation treatment. Knowing the fundamental mechanism of spin-phonon interaction in this system will allow us to further investigate on higher order two phonon Raman processes and Orbach processes at higher temperatures for the spins of the NV^- center in diamond. In this work we show that the predictive power of modern *ab initio* calculations allows the identification of critical phonon modes, which could lead to tailoring the relaxation time in future applications.

ACKNOWLEDGMENTS

J.G. and P.M. were supported by the FWF SFB VI-COM (Project F4109-N28), T.A. and A.A. acknowledge support by the Doctoral School Building Solids for Function (FWF Project W1243), J.M. has been supported by the TOP grant of TU Wien and J.S. by the WWTF project SEQUEx (Project MA16-066).

* jg@cms.tuwien.ac.at

¹ M. W. Doherty, N. B. Manson, P. Delaney, F. Jelezko, J. Wrachtrup, and L. C. L. Hollenberg, *Physics Reports* **528**, 1 (2013).

² V. M. Acosta, E. Bauch, M. P. Ledbetter, A. Waxman, L. S. Bouchard, and D. Budker, *Phys. Rev. Lett.* **104**, 1 (2010).

³ V. Ivády, T. Simon, J. R. Maze, I. A. Abrikosov, and A. Gali, *Physical Review B* **90**, (2014).

⁴ A. Gruber, *Science* **276**, 2012 (1997).

⁵ G. Balasubramanian, I. Y. Chan, R. Kolesov, M. Al-Hmoud, J. Tisler, C. Shin, C. Kim, A. Wojcik, P. R. Hemmer, A. Krueger, T. Hanke, A. Leitenstorfer, R. Bratschitsch, F. Jelezko, and J. Wrachtrup, *Nature* **455**, 648 (2008).

⁶ L. Rondin, J.-P. Tetienne, T. Hingant, J.-F. Roch, P. Maletinsky, and V. Jacques, *Reports on Progress in Physics* **77**, 056503 (2014).

⁷ S. Hong, M. S. Grinolds, L. M. Pham, D. Le Sage, L. Luan, R. L. Walsworth, and A. Yacoby, *MRS Bulletin* **38**, 155 (2013).

⁸ J. F. Barry, M. J. Turner, J. M. Schloss, D. R. Glenn, Y. Song, M. D. Lukin, and R. L. Walsworth, *Proceedings*

of the National Academy of Sciences of the United States of America **113**, (2016).

⁹ C.-C. Fu, H.-Y. Lee, K. Chen, T.-S. Lim, H.-Y. Wu, P.-K. Lin, P.-K. Wei, P.-H. Tsao, H.-C. Chang, and W. Fann, *Proceedings of the National Academy of Sciences* **104**, 727 (2007).

¹⁰ F. Dolde, H. Fedder, M. W. Doherty, T. Nöbauer, F. Rempp, G. Balasubramanian, T. Wolf, F. Reinhard, L. C. L. Hollenberg, F. Jelezko, and J. Wrachtrup, *Nature Physics* **7**, 459 (2011).

¹¹ P. Neumann, I. Jakobi, F. Dolde, C. Burk, R. Reuter, G. Waldherr, J. Honert, T. Wolf, A. Brunner, J. H. Shim, D. Suter, H. Sumiya, J. Isoya, and J. Wrachtrup, *Nano Letters* **13**, 2738 (2013).

¹² J. Wrachtrup, S. Y. Kilin, and A. P. Nizovtsev, *Optics and Spectroscopy* **91**, 429 (2001).

¹³ A. P. Nizovtsev, *Optics and Spectroscopy* **99**, 233 (2005).

¹⁴ L. Robledo, L. Childress, H. Bernien, B. Hensen, P. F. A. Alkemade, and R. Hanson, *Nature* **477**, 574 (2011).

¹⁵ D. a. Redman, S. Brown, R. H. Sands, and S. C. Rand, *Phys. Rev. Lett.* **64**, 3420 (1991).

¹⁶ A. Jarmola, V. M. Acosta, K. Jensen, S. Chemerisov, and D. Budker, *Phys. Rev. Lett.* **108**, 197601 (2012).

- ¹⁷ R. Orbach, Proc. Phys. Soc. **77** (1961).
- ¹⁸ S. Takahashi, R. Hanson, J. Van Tol, M. S. Sherwin, and D. D. Awschalom, Physical Review Letters **101**, 1 (2008).
- ¹⁹ T. Astner, J. Gugler, A. Angerer, S. Wald, S. Putz, N. J. Mauser, M. Trupke, H. Sumiya, S. Onoda, J. Isoya, J. Schmiedmayer, P. Mohn, and J. Majer, **2**, 1 (2017).
- ²⁰ I. Waller, Zeitschrift für Physik **79**, 370 (1932).
- ²¹ J. H. Van Vleck, Phys. Rev. **57**, 426 (1940).
- ²² J. H. Van Vleck, Phys. Rev. **59**, 724 (1941).
- ²³ A. W. Overhauser, Phys. Rev. **89**, 689 (1953).
- ²⁴ R. J. Elliott, Phys. Rev. **96**, 266 (1954).
- ²⁵ Y. Yafet, Solid State Physics **14**, 1 (1963).
- ²⁶ J. H. N. Loubser and J. A. van Wyk, Reports on Progress in Physics **41**, 1201 (1978).
- ²⁷ G. Mahan, *Many-Particle Physics*, Physics of Solids and Liquids (Springer, 2000).
- ²⁸ P. L. Scott and C. D. Jeffries, Physical Review **127**, 32 (1962).
- ²⁹ G. Kresse and J. Furthmüller, Phys. Rev. B **54**, 11169 (1996).
- ³⁰ G. Kresse and D. Joubert, Phys. Rev. B **59**, 1758 (1999).
- ³¹ J. P. Perdew, K. Burke, and M. Ernzerhof, Phys. Rev. Lett. **77**, 3865 (1996).
- ³² J. Sun, A. Ruzsinszky, and J. Perdew, Phys. Rev. Lett. **115**, 1 (2015).
- ³³ J. Heyd, G. E. Scuseria, and M. Ernzerhof, Journal of Chemical Physics **118**, 8207 (2003).
- ³⁴ A. V. Krukau, O. A. Vydrov, A. F. Izmaylov, and G. E. Scuseria, Journal of Chemical Physics **125**, (2006).
- ³⁵ H. Monkhorst and J. Pack, Phys. Rev. B **13**, 5188 (1976).
- ³⁶ A. Gali, M. Fyta, and E. Kaxiras, Phys. Rev. B **77**, 1 (2008).
- ³⁷ J. P. Goss, R. Jones, S. J. Breuer, P. R. Briddon, and S. Öberg, Phys. Rev. Lett. **77**, 3041 (1996).
- ³⁸ A. Lenef and S. C. Rand, Phys. Rev. B **53**, 13441 (1996).
- ³⁹ N. Marzari, A. A. Mostofi, J. R. Yates, I. Souza, and D. Vanderbilt, Reviews of Modern Physics **84**, 1419 (2012).
- ⁴⁰ A. A. Mostofi, J. R. Yates, G. Pizzi, Y.-S. Lee, I. Souza, D. Vanderbilt, and N. Marzari, Computer Physics Communications **185**, 2309 (2014).
- ⁴¹ A. Gali, T. Simon, and J. E. Lowther, New Journal of Physics **13**, 025016 (2011).
- ⁴² A. Togo and I. Tanaka, Scr. Mater. **108**, 1 (2015).
- ⁴³ K. N. Shrivastava, Physica Status Solidi (B) **117**, 437 (1983).
- ⁴⁴ G. Davies and M. F. Hamer, Proceedings of the Royal Society A: Mathematical, Physical and Engineering Sciences **348**, 285 (1976).
- ⁴⁵ A. Mainwood, Phys. Rev. B **49**, 7934 (1994).
- ⁴⁶ T. Nöbauer, K. Buczak, A. Angerer, S. Putz, G. Steinhauser, J. Akbarzadeh, H. Peterlik, J. Majer, J. Schmiedmayer, and M. Trupke, arXiv (2013), 1309.0453.
- ⁴⁷ O. N. Bedoya-Martnez, A. Hashibon, and C. Elssser, physica status solidi (a) **213**, 684 (2016).