

Pressure-induced monotonic enhancement of T_c to over 30 K in the superconducting $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin films

N. N. Wang^{1,2=}, M. W. Yang^{1,2=}, Z. Yang^{1,2=}, K. Y. Chen^{1,2}, H. Zhang^{1,2}, Q. H. Zhang^{1,2}, Z. H. Zhu^{1,2}, Y. Uwatoko³, L. Gu^{1,2}, X. L. Dong^{1,2}, J. P. Sun^{1,2*}, K. J. Jin^{1,2*} and J.-G. Cheng^{1,2*}

¹*Beijing National Laboratory for Condensed Matter Physics and Institute of Physics, Chinese Academy of Sciences, Beijing 100190, China*

²*School of Physical Sciences, University of Chinese Academy of Sciences, Beijing 100190, China*

³*Institute for Solid State Physics, University of Tokyo, Kashiwa, Chiba 277-8581, Japan*

= These authors contributed equally to this work.

Emails: jpsun@iphy.ac.cn; kjjin@iphy.ac.cn; jgcheng@iphy.ac.cn

Abstract

The successful synthesis of superconducting infinite-layer nickelate thin films with the highest $T_c \approx 15$ K has reignited great enthusiasms on this family of potential analogue to high- T_c cuprates. Pursuing a higher T_c is always an imperative task in studying a new superconducting material system. Here we report high-quality $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin films with $T_c^{\text{onset}} \approx 17$ K synthesized by carefully tuning the amount of CaH_2 in the topological chemical reduction and the effect of pressure on its superconducting properties by measuring electrical resistivity under various pressures in a cubic anvil cell apparatus. We find that the onset temperature of the superconductivity, T_c^{onset} , can be enhanced monotonically from ~ 17 K at ambient pressure to ~ 31 K at 12.1 GPa without showing signatures of saturation upon increasing pressure. This encouraging result indicates that the T_c of infinite-layer nickelates superconductors still has room to go higher and it can be further boosted by applying higher pressures or strain engineering in the heterostructure films.

Keywords: high pressure, superconductivity, infinite-layer nickelates

Introduction

Since the discovery of the high- T_c superconductivity in cuprates (1), numerous experimental and theoretical investigations have been carried out aiming at finding more superconductors with higher T_c and unveiling the mysterious mechanisms. After over 30 years of endeavor, the highest T_c in cuprates, ~ 135 K at ambient (2) and ~ 164 K under pressure (3), remains to be lower than room temperature, and the mechanism is still an enigma. As the nearest neighbor to copper in the periodic table, the infinite-layer nickelates showing the great similarities in crystal structures and electronic configurations to cuprates have been considered as potential high- T_c superconductors ever since the early 1990s (4-13). Unfortunately, superconductivity was not observed in the synthesized powder and thin film nickelates until very recently.

In 2019, Li *et al.* reported the experimental observation of the superconductivity with $T_c = 9-15$ K in the hole-doped infinite-layer $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$ thin films obtained by soft-chemistry topotactic reduction from the corresponding perovskite phase (14). From the experimentally constructed superconducting phase diagram, the observed $T_c(x)$ has a non-monotonic evolution with doping x , similar to the hole-doped cuprates (15-17). This discovery has reignited the enthusiasms on the nickelates and immediately attracted extensive investigations recently (for a review, see Ref. (18)). For the parent LaNiO_2 and NdNiO_2 , X-ray absorption spectroscopy (XAS) and resonant inelastic X-ray scattering (RIXS) confirmed the nominal $3d^9$ electronic configuration but revealed a reduced hybridization between Ni $3d$ and O $2p$ orbitals, and an enhanced coupling between Ni $3d$ and La/Nd $5d$ states (19). Notably, the electron energy loss spectroscopy (EELS), high-resolution XAS and RIXS experiments further revealed that the doped holes reside on the Ni sites, forming the low-spin d^8 state (20, 21). These observations are different from those in cuprates (22, 23). Recent STM experiments uncovered a mixed s - and d -wave superconducting gap feature on the rough surface of $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$ thin films (24), and these results were reproduced by employing *ab initio* treatment on different terminated surfaces (25, 26). From the theoretical point of view, three main perspectives on nickelates have been proposed, including the cuprate-like correlated single-Ni-orbital $d_{x^2-y^2}$ band (23, 25, 27-32), the Ni- $3d$ -multiorbital effects (33-37), and the Kondo physics between Ni- $3d$ and Nd- $5d$ orbitals (38-40). So far, consensus has not yet been reached about the superconducting mechanism of nickelates. This is partially attributed to the great challenges in the materials' synthesis, the relatively poor quality of these infinite-layer nickelates, and the limited techniques for regulating their physical properties. In contrast to the superconducting thin-film samples, the bulk samples exhibit an insulating ground

state, and no indication of superconductivity was observed even under pressures up to 50 GPa (41). It has raised the question whether the observed superconductivity correlates intimately with the heterostructure or epitaxy strain between the thin films and the substrate.

In addition to $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$ thin films, superconductivity has also been achieved in other doped rare-earth nickelates, such as $\text{La}_{1-x}(\text{Ca}/\text{Sr})_x\text{NiO}_2$ (42, 43) and $\text{Pr}_{1-x}\text{Sr}_x\text{NiO}_2$ (44). The phase diagrams of $(\text{La}/\text{Pr}/\text{Nd})_{1-x}\text{Sr}_x\text{NiO}_2$ and $\text{La}_{1-x}\text{Ca}_x\text{NiO}_2$ thin films are all featured by the superconducting phase adjacent to the weakly insulating state in the underdoped and over-doped regimes (16, 17, 42-44). In addition, the doping-dependent generalized superconducting dome was found to shift upon changing the rare-earth cations. However, a local T_c valley structure of the superconducting phase was not observed in the $\text{Pr}_{1-x}\text{Sr}_x\text{NiO}_2$ (44), which is different from the situations in $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$ and $\text{La}_{1-x}(\text{Ca}/\text{Sr})_x\text{NiO}_2$ (16, 17, 42, 43). These comparisons highlight the important role of rare-earth cations played in addition to the lattice strain applied by the SrTiO_3 substrate in regulating the superconducting state of the nickelates. Despite of much recent effort, the reported highest T_c^{onset} of the infinite-layer nickelates remains lower than 15 K (14, 16, 17, 42-48); it thus becomes an important issue to further enhance the T_c of the superconducting nickelates to higher temperatures. In this regard, the application of high pressure which has been widely employed to raise T_c of cuprates (3) and iron-based unconventional superconductors (49-52) should be a primary choice. To the best of our knowledge, however, this approach has not been applied to the superconducting nickelate thin films so far. We are thus motivated to investigate the effect of pressure on the superconducting properties of the infinite-layer nickelates.

In this work, we first synthesized high-quality $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin films with a high $T_c^{\text{onset}} \approx 17$ K, and then performed transport measurements by using the palm-type cubic anvil cell (CAC) apparatus under various pressures up to 12.1 GPa. We observe a positive pressure effect on the superconducting transition temperature, $T_c(P)$, which increases monotonically from ~ 17 K at ambient pressure to ~ 31 K at 12.1 GPa without leveling off. This result is quite encouraging and should promote further endeavors to raise the T_c of this new class of superconductors.

Results and Discussions

The single-crystalline infinite-layer $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin films were synthesized by two steps. First, the precursor perovskite phase $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_3$ films were deposited on TiO_2 -terminated SrTiO_3 (001) substrates and then capped with the SrTiO_3 epitaxial

layer by using the pulsed laser deposition system (53, 54). Subsequently, the thin films were vacuum-sealed with CaH_2 in a glass tube for the ex-situ topotactic reduction process to obtain the infinite-layer films. Details about the sample syntheses can be found in the Supplementary Materials (SM). As we can see, Fig. 1(a) shows the X-ray diffraction (XRD) θ - 2θ symmetric scans of thin-film samples for perovskite $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_3$ (blue) and infinite-layer $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ (red), showing only (001) and (002) peaks for both phases. After reduction, the rightward shift of the (001) and (002) peaks in the infinite-layer phase corresponds to a compression of the out-of-plane lattice constant, which is calculated to be 3.36 Å. As seen from the reciprocal space mappings in Fig. 1(b, c), both films are closely fixed to the in-plane SrTiO_3 lattice. To further characterize the infinite-layer thin films, we performed the cross-sectional scanning transmission electron microscopy (STEM), Fig. 1(d). The infinite-layer structure of the $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin film can be intuitively seen from the atomic-resolution high-angle annular dark-field (HAADF) images, elaborating the high-quality of the synthesized samples.

Figure 1(e) shows the temperature-dependent resistivity $\rho(T)$ for both the perovskite $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_3$ and infinite-layer $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin films. For $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_3$, the $\rho(T)$ shows a metallic behavior but a weak temperature dependence over the whole temperature range. $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ also displays a typical metallic behavior upon cooling down and exhibits a pronounced superconducting transition below $T_c^{\text{onset}} \approx 17$ K, which is defined as the temperature where the resistivity deviates from the linear extrapolation of normal-state resistivity, inset of Fig. 1(e). Zero resistance is achieved at $T_c^{\text{zero}} \approx 11$ K, which is in good agreement with previous reports (44).

To further raise T_c and tune the physical properties of this new superconducting family, we studied the pressure effect on the $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ films by measuring resistivity under various hydrostatic pressures. The experimental details can be found in the SM. Figure 2(a, b) shows the $\rho(T)$ of two $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin films (No. 1 and 2) measured under various pressures in the presence of Daphne 7373 and glycerol as the liquid pressure transmitting medium (PTM), respectively. As seen in Fig. 2(a), the magnitude of normal-state resistivity shows complex and non-monotonic evolutions with increasing pressure. At $P > 1.7$ GPa, a broad hump feature appears in $\rho(T)$ between 100 and 300 K, which is similar to the situation seen in the Fe-based superconductors due to the incoherent-to-coherent crossover of the $3d$ electrons (55-58). When we further increase pressure to 6.6 GPa, an obvious upturn in $\rho(T)$ appears below ~ 50 K, and the superconducting transition emerges at $T_c^{\text{onset}} \approx 26$ K. Moreover, we can see that the residual resistivity at 1.5 K exhibits a prominent enhancement

with increasing pressure above 2.4 GPa; it increases to the value that is about half of the normal-state value at 6.6 GPa. Such a large enhancement should be induced by the solidification of the Daphne 7373 at high pressures and low temperatures as discussed below. For the sample No. 2 in the glycerol PTM, the normal-state $\rho(T)$ and the residual resistivity show similar evolutions with pressure as sample No. 1; it first decreases considerably from 0 to 2.5 GPa, increases gradually until 6.8 GPa, and then decreases again at higher pressures. These high-pressure results resemble the observations in the Sr/Ca-doped infinite-layer nickelate thin films (14, 16, 17, 42-44), in which the defects or cation-site disorders dominate the scattering processes in resistivity. As discussed below, the delicate thin films are partially deteriorated upon compression, which produces more disorders and defects that enhance the carrier scatterings. In the presence of liquid PTM, the superconducting transition remains visible up to at least 12.1 GPa, the highest pressure in the present study.

To highlight the evolutions with pressure of the superconducting transition, we vertically shifted the $\rho(T)$ curves below 100 K for the samples No. 1 and No. 2, as displayed in Figs. 2(c) and 2(d). We can clearly see that the T_c increases monotonically with pressure in the studied pressure range. In addition to T_c^{onset} (red arrow, as defined above), here we also define the $T_c^{90\%Rn}$ as the temperature where the resistivity drops to 90% of $\rho(T_c^{\text{onset}})$ [T_c^{onset} and $T_c^{90\%Rn}$ correspond to the temperatures where the superconducting state (or Cooper pairs) just appears and grows up quickly], and T_c^{offset} as shown in Fig. 2(c). The $\rho(T)$ at ambient pressure (AP) shows a high $T_c^{\text{onset}} \approx 18$ K and $T_c^{90\%Rn} \approx 17.3$ K. These values are a little bit higher than those in the previous report (44), which may attribute to the different reduction conditions. For sample No. 1 at AP, a small residual resistance below $T_c^{\text{offset}} \approx 12.2$ K is noted, which should be ascribed to the inhomogeneity of the small-sized sample for high-pressure measurements. Upon application of high pressure, we observed perfect zero resistivity for sample No. 1 below 2.4 GPa and for sample No. 2 below 4.6 GPa, respectively. At 2.4 GPa, the superconducting transition of sample No. 1 increases to $T_c^{\text{onset}} \approx 22.5$ K, $T_c^{90\%Rn} \approx 20.4$ K, and $T_c^{\text{offset}} \approx 16.5$ K. Upon further increasing pressure to 6.6 GPa, although zero resistivity cannot be achieved, the superconducting transition remains relatively sharp and is further enhanced to $T_c^{\text{onset}} \approx 26$ K, and $T_c^{90\%Rn} \approx 23.5$ K. In contrast, the superconducting transition of sample No. 2 is broadened up considerably featured by a long tail with a large residual resistivity when increasing pressure from 6.8 to 12.1 GPa, Fig. 2(d). As discussed below, this should be attributed to the degradation of the delicate thin-file samples in the presence of substantial stress/strain accompanying the sonification of PTM upon compression and cooling down.

Fortunately, we can still monitor the onset of superconducting transition that continues to increase with pressure. The T_c^{onset} and $T_c^{90\%Rn}$ are enhanced gradually from 26 K and 22.7 K at 6.8 GPa to 31 K and 27.2 K at 12.1 GPa.

To check the reproducibility of the above results, we have measured three more samples (Nos. 3, 4, and 5) with thicker SrTiO₃ capping layer by using different liquid PTM: mineral oil, silicone oil and glycerol, respectively. All $\rho(T)$ data are shown in Fig. S2 of SM. We confirm that the superconducting transition T_c^{onset} for all samples shows positive pressure effect. However, the superconducting transition of these three samples is broadened up significantly under pressure, which can be ascribed to the thicker capping layer that induces stronger stress/strain to the Pr_{0.82}Sr_{0.18}NiO₂ thin films.

Figure 3 shows the pressure dependences of T_c^{onset} and $T_c^{90\%Rn}$ obtained from the above resistivity measurements on the five samples. The positive pressure effect on T_c can be visualized clearly, and the T_c^{onset} is raised up monotonically from below 20 K at ambient to above 30 K at 12.1 GPa without showing any sign of saturation. This means that T_c of these nickelate superconductors can be further enhanced by higher pressures, and the present study has pushed the T_c limit of superconducting nickelates to over 30 K. A linear fitting to $T_c^{\text{onset}}(P)$ for all the measured samples yields a positive slope of 0.96 K/GPa, the dashed line in Fig. 3. Such an enhancement of T_c will draw more attention and efforts to further boost the superconducting transition temperature of the infinite-layer nickelates superconductors.

To further characterize the superconducting properties of the Pr_{0.82}Sr_{0.18}NiO₂ thin films under pressure, we studied the effect of magnetic fields on resistivity at each fixed pressure. Fig. 4(a) shows the $\rho(T)$ curves under various magnetic fields at 12.1 GPa. All $\rho(T)$ data under different pressures for sample No. 1 up to 6.6 GPa and for sample No. 2 up to 12.1 GPa are shown in Figs. S3 and S4, respectively. As seen in Figs. 4(a), S3 and S4, the superconducting transition is gradually suppressed to lower temperatures and the transition width is broaden up with increasing magnetic fields. Here, we used the criteria of $T_c^{90\%Rn}$ and plotted the temperature dependences of $\mu_0 H_{c2}(T_c^{90\%Rn})$ in Fig. 4(b). Then, we estimate the zero-temperature upper critical field $\mu_0 H_{c2}(0)$ by employing the empirical Ginzburg-Landau (G-L) formula, i.e., $\mu_0 H_{c2}(T) = \mu_0 H_{c2}(0)(1-t^2)/(1+t^2)$, where $t = T/T_c$ represents the reduced temperature. The fitting results are indicated by the broken lines in Fig. 4(b). Unlike the monotonic enhancement of $T_c(P)$, the $\mu_0 H_{c2}^{\text{GL}}(0)$ exhibits a non-monotonic evolution with pressure. As show in Fig. 4(c), the obtained $\mu_0 H_{c2}^{\text{GL}}(0)$ first increases quickly from ~ 100.7 T at 0 GPa to 141.5 T at 2.5 GPa with a slope of about ~ 16 T/GPa, and then it

increases nearly linearly to ~ 173 T with a smaller slope of 4 T/GPa up to 10.1 GPa. When $P \geq 10.1$ GPa, the $\mu_0 H_{c2}(0)$ declines continuously, which might be correlated with the degradation of the superconducting state.

The main finding of the present study is the observation of positive pressure effect on $T_c(P)$, which shows the potential to reach higher than 30 K in the $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin films. Below we briefly discuss the mechanism and its implications.

First, the contraction of the lattice parameter under pressure should favor a higher T_c when comparing to the effect of chemical pressure at similar optimal hole doping level. For the reported nickelate thin films, the in-plane lattice constants $a \sim 3.91$ Å seems to be locked by the SrTiO_3 substrate (14, 42-44), but the c -axis constant shows an inverse correlation to the optimal T_c , as illustrated in Fig. 4(d), $T_c = 9$ K for $\text{La}_{0.8}\text{Sr}_{0.2}\text{NiO}_2$ ($c \approx 3.44$ Å) (42), $T_c = 10$ K for $\text{La}_{0.82}\text{Ca}_{0.18}\text{NiO}_2$ ($c \approx 3.385$ Å) (43), $T_c = 11$ K for $\text{Nd}_{0.775}\text{Sr}_{0.225}\text{NiO}_2$ ($c \approx 3.375$ Å) (14, 16, 17), and $T_c = 14$ K for $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ ($c \approx 3.36$ Å) (44). If this trend is followed under physical pressure, the contraction of c -axis under pressure should lead to an enhancement of T_c , as indeed observed here from ~ 17 K at AP to ~ 31 K at 12.1 GPa. From a linear extrapolation in Fig. 3, a higher T_c over ~ 40 K can be achieved at about 20 GPa. The shrinkage of c -axis under pressure will enhance the hybridization between the $3d$ orbitals of nickel and $5d$ orbitals of rare-earth-layer, and thus the Kondo coupling. Following the Kondo picture, the non-monotonic evolution of normal-state resistivity under high pressures can be interpreted as the magnification of enhanced Kondo effect (39, 40). Moreover, a superconducting phase diagram based on the generalized K - t - J model has been established by incorporating the Kondo coupling K to the t - J model, and an evolution from d -wave dominant phase to s -wave dominant phase can be achieved by tuning the coupling parameter K at the optimal hole-doping (40). Therefore, the enhancement of T_c may originate from this proposed picture that the gap magnitude of s -wave coming from the hybridized orbitals increases under high pressures.

Secondly, based on the single-band model, the initial slope of $\mu_0 H_{c2}(T)$ is related to the effective mass m^* of charge carriers via the relationship $-(1/T_c)[d\mu_0 H_{c2}/dT]|_{T_c} \propto (m^*)^2$ (59, 60). From a linear fitting to $\mu_0 H_{c2}(T)$, we can extract the normalized slope $-(1/T_c)[d\mu_0 H_{c2}/dT]|_{T_c}$, which decreases from ~ 0.42 T/K² at 0 GPa to ~ 0.26 T/K² at 10.1 GPa, Fig. 4(c). Such a pressure-induced reduction of effective mass m^* or the electron correlations should correlate with the changes of bandwidth under high pressures. As indicated by the theoretical calculations based on the one-band Hubbard model, the superconducting T_c can be further enhanced by fine tuning the second- and third-nearest neighbor hopping parameters t' and t'' on a square lattice other than hole-

doping (32). In this sense, our high-pressure results are consistent with the theoretical predictions that high pressure can create the compressive strain which broadens the bandwidth with a slight interaction-to-bandwidth ratio (32, 61). On the other hand, a continuous increase of T_c from ~ 20 to ~ 35 K is observed in calculations by reducing the onsite interaction U from $9t$ to $7t$ (32), which is in good agreement with our experimental results. Further theoretical studies on the electronic structures under pressure are needed to have a better understanding on the importance of electronic correlations, hybridization between Ni-3*d* and rare-earth 5*d* electrons.

Finally, we would like to briefly comment the influence of pressure environment on the superconducting nickelate thin films, which are found to be very sensitive to the pressure conditions or the used PTM during this study. To confirm our assumption, we performed the STEM measurements on the $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin film (No. 2) after decompression. As shown in Fig. S5(a), we can clearly see that the atomic-resolution image of infinite-layer structure of $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin film before we perform the high-pressure resistivity measurements. However, the infinite-layer structure is partially destroyed, producing considerable amount of dislocations and defects in a large scale after the high-pressure measurements, Fig. S5(b-d). Obviously, the broaden of the superconducting transition at high pressures has direct correlation with the cracked infinite-layer structure. Moreover, this can explain why the bulk materials don't show the superconducting transition at ambient pressure and high pressures. For bulk polycrystalline samples, although they have infinite-layer structure, there is no ideal infinite-layer structure in a large-scale as seen in the thin films. To further verify the above hypothesis about the influence of extrinsic disorders and/or stress, we performed comparative high-pressure resistivity measurements on the $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin film (No. 6) in CAC by using the solid h-BN as the PTM, which is expected to produce a stronger stress/strain than the liquid one. As shown in Fig. S6, the $\rho(T)$ is immediately altered to an insulating-like behavior under pressure of 2 GPa, and the magnitude of resistivity increases significantly with further increasing pressure to 4 GPa, which reproduces the insulating behavior of the bulk polycrystalline samples. This comparison also highlights that the liquid PTM, though solidified under pressure, remains relatively soft so that it can preserve the metallic behavior and allows us to see the evolution of the superconducting transition.

Conclusion

In summary, we have performed a high-pressure study on the superconducting $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin films by employing the cubic anvil cell apparatus. Our results

reveal that its T_c increases from ~ 17 K at 0 GPa to ~ 31 K at 12.1 GPa without showing any signature of saturation. This result indicates that there is still much room for further raising the T_c of the superconducting nickelates. We have explained the positive pressure effect of $T_c(P)$ in terms of the lattice contraction and enhanced hybridization between the Ni-3d and Pr-5d orbitals considering the theoretical calculations. This finding is encouraging and should promote more studies to explore superconducting nickelates with higher T_c .

Acknowledgments

This work is supported by the National Key R&D Program of China (2018YFA0305700 and 2019YFA0308500), the Beijing Natural Science Foundation (Z190008), the National Natural Science Foundation of China (12025408, 11904391, 11921004, 11888101, 11834016, 11874400, 12174424, and 11721404), the Strategic Priority Research Program and Key Research Program of Frontier Sciences of the Chinese Academy of Sciences (XDB25000000, XDB33000000 and QYZDB-SSW-SLH013), the Users with Excellence Program of Hefei Science Center CAS (Grant No. 2021HSC-UE008) and the CAS Interdisciplinary Innovation Team. U.W. is supported by the JSPS KAKENHI Grant No. JP19H00648.

References

1. J. G. Bednorz, K. A. Müller, Possible high T_c superconductivity in the Ba-La-Cu-O system. *Z. Phys. B* **64**, 189 (1986).
2. L. Gao *et al.*, Study of superconductivity in the Hg-Ba-Ca-Cu-O system. *Physica C* **213**, 261 (1993).
3. L. Gao *et al.*, Superconductivity up to 164 K in $\text{HgBa}_2\text{Ca}_{m-1}\text{Cu}_m\text{O}_{2m+2+\delta}$ ($m=1, 2, \text{ and } 3$) under quasihydrostatic pressures. *Phys. Rev. B* **50**, 4260 (1994).
4. M. Crespin, P. Levitz, L. Gatinéau, Reduced forms of LaNiO_3 perovskite. Part 1.—Evidence for new phases: $\text{La}_2\text{Ni}_2\text{O}_5$ and LaNiO_2 . *J. Chem. Soc. Faraday Trans. II* **79**, 1181-1194 (1983).
5. M. A. Hayward, M. A. Green, M. J. Rosseinsky, J. Sloan, Sodium hydride as a powerful reducing agent for topotactic oxide deintercalation: synthesis and characterization of the nickel(I) oxide LaNiO_2 . *J. Am. Chem. Soc.* **121**, 8843-8854 (1999).
6. M. A. Hayward, M. J. Rosseinsky, Synthesis of the infinite layer Ni(I) phase NdNiO_{2+x} by low temperature reduction of NdNiO_3 with sodium hydride. *Solid State Sci.* **5**, 839 (2003).
7. M. O. Crespin, O. Isnard, F. F. Dubois, J. Choisnet, P. Odier, LaNiO_2 :

- Synthesis and structural characterization. *J. Solid State Chem.* **178**, 1326–1334 (2005).
8. D. Kaneko, K. Yamagishi, A. Tsukada, T. Manabe, M. Naito, Synthesis of infinite-layer LaNiO_2 films by metal organic decomposition. *Physica C* **469**, 936 (2009).
 9. M. Kawai *et al.*, Reversible changes of epitaxial thin films from perovskite LaNiO_3 to infinite-layer structure LaNiO_2 . *Appl. Phys. Lett.* **94**, 082102 (2009).
 10. M. Kawai *et al.*, Orientation Change of an Infinite-Layer Structure LaNiO_2 Epitaxial Thin Film by Annealing with CaH_2 . *Cryst. Growth Des.* **10**, 2044–2046 (2010).
 11. A. V. Boris *et al.*, Dimensionality control of electronic phase transitions in nickel-oxide superlattices. *Science* **332**, 937–940 (2011).
 12. A. Ikeda, T. Manabe, M. Naito, Improved conductivity of infinite-layer LaNiO_2 thin films by metal organic decomposition. *Physica C* **495**, 134–140 (2013).
 13. A. Ikeda, Y. Krockenberger, H. Irie, M. Naito, H. Yamamoto, Direct observation of infinite NiO_2 planes in LaNiO_2 films. *Appl. Phys. Express* **9**, 061101 (2016).
 14. D. F. Li *et al.*, Superconductivity in an infinite-layer nickelate. *Nature* **572**, 624–627 (2019).
 15. B. Keimer, S. A. Kivelson, M. R. Norman, S. Uchida, J. Zaanen, From quantum matter to high-temperature superconductivity in copper oxides. *Nature* **518**, 179–186 (2015).
 16. D. F. Li *et al.*, Superconducting Dome in $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$ Infinite Layer Films. *Phys. Rev. Lett.* **125**, 027001 (2020).
 17. S. Zeng *et al.*, Phase diagram and superconducting dome of infinite-layer $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$ thin films. *Phys. Rev. Lett.* **125**, 147003 (2020).
 18. Q. Q. Gu, H. H. Wen, Superconductivity in nickel-based 112 systems. *The Innovation* **3**, 100202 (2022).
 19. M. Hepting *et al.*, Electronic structure of the parent compound of superconducting infinite-layer nickelates. *Nat. Mater.* **19**, 381–385 (2020).
 20. B. H. Goodge *et al.*, Doping evolution of the Mott-Hubbard landscape in infinite-layer nickelates. *Proc. Natl. Acad. Sci. USA* **118**, e2007683118 (2021).
 21. M. Rossi *et al.*, Orbital and Spin Character of Doped Carriers in Infinite-Layer Nickelates. *Proc. Natl. Acad. Sci. USA* **118**, e2007683118 (2021).
 22. K. W. Lee, W. E. Pickett, Infinite-layer LaNiO_2 : Ni^{1+} is not Cu^{2+} . *Phys. Rev. B* **70**, 165109 (2004).
 23. A. S. Botana, M. R. Norman, Similarities and Differences between LaNiO_2 and CaCuO_2 and Implications for Superconductivity. *Phys. Rev. X* **10**, 011024 (2020).
 24. Q. Q. Gu *et al.*, Single particle tunneling spectrum of superconducting $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$ thin films. *Nat. Commun.* **11**, 6027 (2020).
 25. X. X. Wu *et al.*, Robust $d_{x^2-y^2}$ -wave superconductivity of infinite-layer nickelates. *Phys. Rev. B* **101**, 060504(R) (2020).

26. X. X. Wu *et al.*, Surface s -wave superconductivity for oxide-terminated infinite-layer nickelates. arXiv: 2008.06009 (2020).
27. M. Hirayama, T. Tadano, Y. Nomura, R. Arita, Materials design of dynamically stable d^9 layered nickelates. *Phys. Rev. B* **101**, 075107 (2020).
28. H. Zhang *et al.*, Effective Hamiltonian for nickelate oxides $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$. *Phys. Rev. Research* **2**, 013214 (2020).
29. M. Jiang, M. Berciu, G. A. Sawatzky, Critical Nature of the Ni Spin State in Doped NdNiO_2 . *Phys. Rev. Lett.* **124**, 207004 (2020).
30. F. Lechermann, Late transition metal oxides with infinite-layer structure: Nickelates versus cuprates. *Phys. Rev. B* **101**, 081110 (2020).
31. J. Karp *et al.*, Many-Body Electronic Structure of NdNiO_2 and CaCuO_2 . *Phys. Rev. X* **10**, 021061 (2020).
32. M. Kitatani *et al.*, Nickelate superconductors—a renaissance of the one-band Hubbard model. *npj Quantum Materials* **5**, 59 (2020).
33. L. H. Hu, C. J. Wu, Two-band model for magnetism and superconductivity in nickelates. *Phys. Rev. Research* **1**, 032046 (2019).
34. F. Petocchi, V. Christiansson, F. Nilsson, F. Aryasetiawan, P. Werner, Normal State of $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$ from Self-Consistent GW +EDMFT. *Phys. Rev. X* **10**, 041047 (2020).
35. Y. Wang, C. J. Kang, H. Miao, G. Kotliar, Hund's metal physics: From SrNiO_2 to LaNiO_2 . *Phys. Rev. B* **102**, 161118(R) (2020).
36. Y. H. Zhang, A. Vishwanath, Type-II t - J model in superconducting nickelate $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$. *Phys. Rev. Research* **2**, 023112 (2020).
37. P. Werner, S. Hoshino, Nickelate superconductors: Multiorbital nature and spin freezing. *Phys. Rev. B* **101**, 041104 (2020).
38. F. Lechermann, Multiorbital Processes Rule the $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$ Normal State. *Phys. Rev. X* **10**, 041002 (2020).
39. Z. Wang, G. M. Zhang, Y. F. Yang, F. C. Zhang, Distinct pairing symmetries of superconductivity in infinite-layer nickelates. *Phys. Rev. B* **102**, 220501(R) (2020).
40. G. M. Zhang, Y. F. Yang, F. C. Zhang, Self-doped Mott insulator for parent compounds of nickelate superconductors. *Phys. Rev. B* **101**, 020501(R) (2020).
41. Q. Li *et al.*, Absence of superconductivity in bulk $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_2$. *Commun. Mater.* **1**, 16 (2020).
42. M. Osada *et al.*, Nickelate superconductivity without rare-earth magnetism (La,Sr) NiO_2 . arXiv: 2105.13494 (2021).
43. S. W. Zeng *et al.*, Superconductivity in infinite-layer lanthanide nickelates. arXiv: 2105.13492 (2021).
44. M. Osada, B. Y. Wang, K. Lee, D. F. Li, H. Y. Hwang, Phase diagram of infinite layer praseodymium nickelate $\text{Pr}_{1-x}\text{Sr}_x\text{NiO}_2$ thin films. *Phys. Rev. Materials* **4**, 121801(R) (2020).
45. G. A. Pan *et al.*, Superconductivity in a quintuple-layer square-planar nickelate. *Nat. Mater.* **21**, 160-164 (2021).
46. X. L. Ren *et al.*, Superconductivity in infinite-layer $\text{Pr}_{0.8}\text{Sr}_{0.2}\text{NiO}_2$ films on

- different substrates. arXiv: 2109.05761 (2021).
47. Q. Gao, Y. C. Zhao, X. J. Zhou, Z. H. Zhu, Preparation of Superconducting Thin Films of Infinite-Layer Nickelate $\text{Nd}_{0.8}\text{Sr}_{0.2}\text{NiO}_2$. *Chin. Phys. Lett.* **38**, (2021).
 48. D. F. Li, The discovery and research progress of the nickelate superconductors. *Sci. Sin-Phys Mech Astron* **51**, 047405 (2021).
 49. H. Takahashi *et al.*, Superconductivity at 43 K in an iron-based layered compound $\text{LaO}_{1-x}\text{F}_x\text{FeAs}$. *Nature* **453**, 376-378 (2008).
 50. P. Shahi *et al.*, High- T_c superconductivity up to 55 K under high pressure in a heavily electron doped $\text{Li}_{0.36}(\text{NH}_3)_y\text{Fe}_2\text{Se}_2$ single crystal. *Phys. Rev. B* **97**, 020508(R) (2018).
 51. J. P. Sun *et al.*, Dome-shaped magnetic order competing with high-temperature superconductivity at high pressures in FeSe. *Nat. Commun.* **7**, 12146 (2016).
 52. J. P. Sun *et al.*, Reemergence of high- T_c superconductivity in the $(\text{Li}_{1-x}\text{Fe}_x)\text{OHFe}_{1-y}\text{Se}$ under high pressure. *Nat. Commun.* **9**, 380 (2018).
 53. K. J. Jin *et al.*, Positive colossal magnetoresistance from interface effect in p - n junction of $\text{La}_{0.9}\text{Sr}_{0.1}\text{MnO}_3$ and $\text{SrNb}_{0.01}\text{Ti}_{0.99}\text{O}_3$. *Phys. Rev. B* **71**, 184428 (2005).
 54. K. J. Jin, K. Zhao, H. B. Lu, L. Liao, G. Z. Yang, Dember effect induced photovoltage in perovskite p - n heterojunctions. *Appl. Phys. Lett.* **91**, 081906 (2007).
 55. F. Hardy *et al.*, Evidence of Strong Correlations and Coherence-Incoherence Crossover in the Iron Pnictide Superconductor KFe_2As_2 . *Phys. Rev. Lett.* **111**, 027002 (2013).
 56. K. Haule, G. Kotliar, Coherence-incoherence crossover in the normal state of iron oxypnictides and importance of Hund's rule coupling. *New J. Phys.* **11**, 025021 (2009).
 57. S. Iimura, S. Matsuishi, H. Hosono, Heavy electron doping induced antiferromagnetic phase as the parent for the iron oxypnictide superconductor $\text{LaFeAsO}_{1-x}\text{H}_x$. *Phys. Rev. B* **94**, 024512 (2016).
 58. Y. P. Wu *et al.*, Emergent Kondo Lattice Behavior in Iron-Based Superconductors AFe_2As_2 ($\text{A}=\text{K}, \text{Rb}, \text{Cs}$). *Phys. Rev. Lett.* **116**, 147001 (2016).
 59. V. G. Kogan, R. Prozorov, Orbital upper critical field and its anisotropy of clean one- and two-band superconductors. *Rep. Prog. Phys.* **75**, 114502 (2012).
 60. U. S. Kaluarachchi *et al.*, Nonmonotonic pressure evolution of the upper critical field in superconducting FeSe. *Phys. Rev. B* **93**, 064503 (2016).
 61. I. Leonov, Effect of lattice strain on the electronic structure and magnetic correlations in infinite-layer $(\text{Nd},\text{Sr})\text{NiO}_2$. *J. Alloy Compd.* **883**, 160888 (2021).

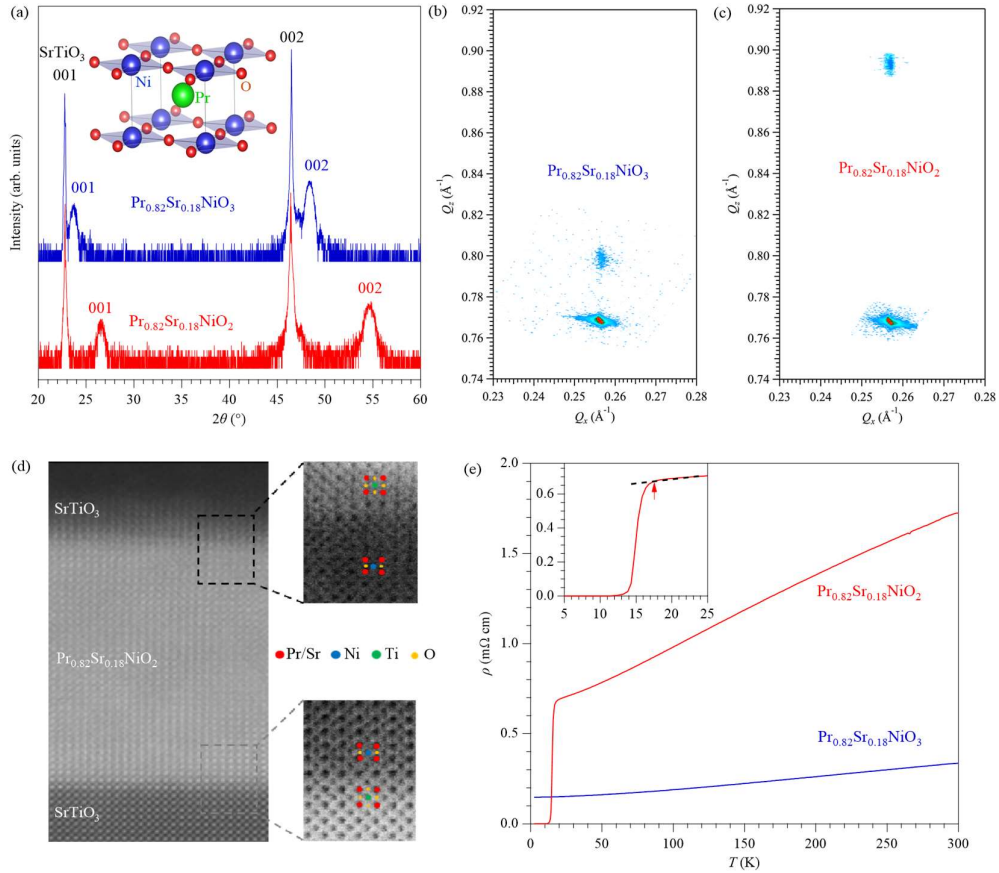


Figure 1. (a) X-ray diffraction θ - 2θ symmetric scans of perovskite $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_3$ thin film (blue) and infinite-layer $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin film (red). Reciprocal space mappings (RSM) of (b) perovskite $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_3$ thin film and (c) infinite-layer $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin film, respectively. (d) The atomic-resolution HAADF-STEM imaging of infinite-layer samples in (a). (e) Temperature-dependent resistivity for perovskite $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_3$ thin film (blue) and infinite-layer $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin film (red) which shows a high superconducting transition temperature $T_c^{\text{onset}} \approx 17$ K. Inset of (a) shows the crystal structure of PrNiO_2 .

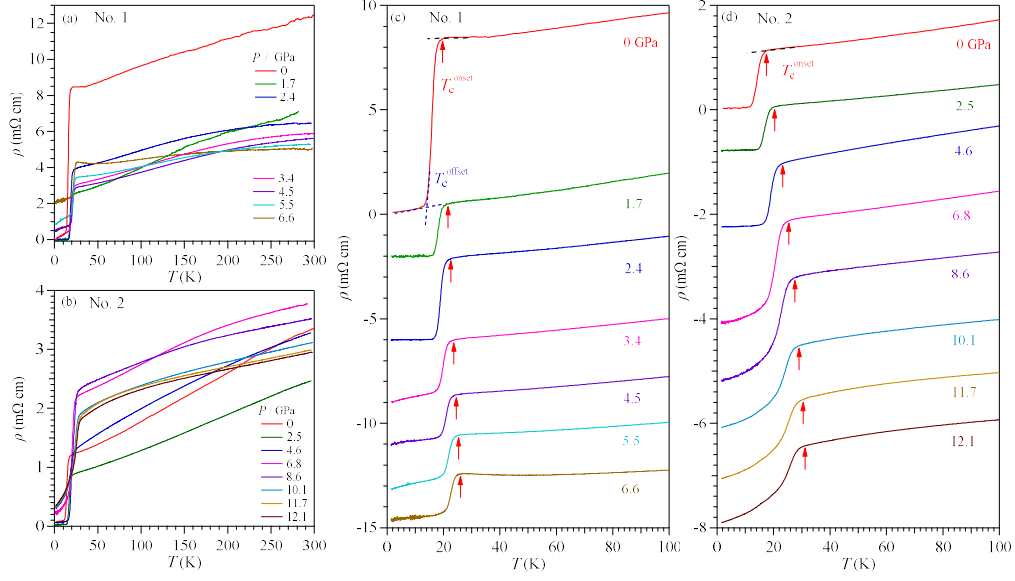


Figure 2. Temperature dependence of resistivity $\rho(T)$ of $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin films under various pressures (a) up to 6.6 GPa for sample No. 1 with Daphne 7373 and (b) up to 12.1 GPa for sample No. 2 with glycerol as PTM. The resistivity $\rho(T)$ curves below 100 K (c) for No. 1 and (d) for No. 2, illustrating the variation of the superconducting transition temperatures with pressure. Except for data at 0 GPa, all other curves in (c) and (d) have been vertically shifted for clarity. The T_c^{onset} (up-pointing arrow) was determined as the temperature where resistivity starts to deviate from the extrapolated normal-state behavior and the T_c^{offset} (crossing point) was defined as the interception between two straight lines below and above the superconducting transition.

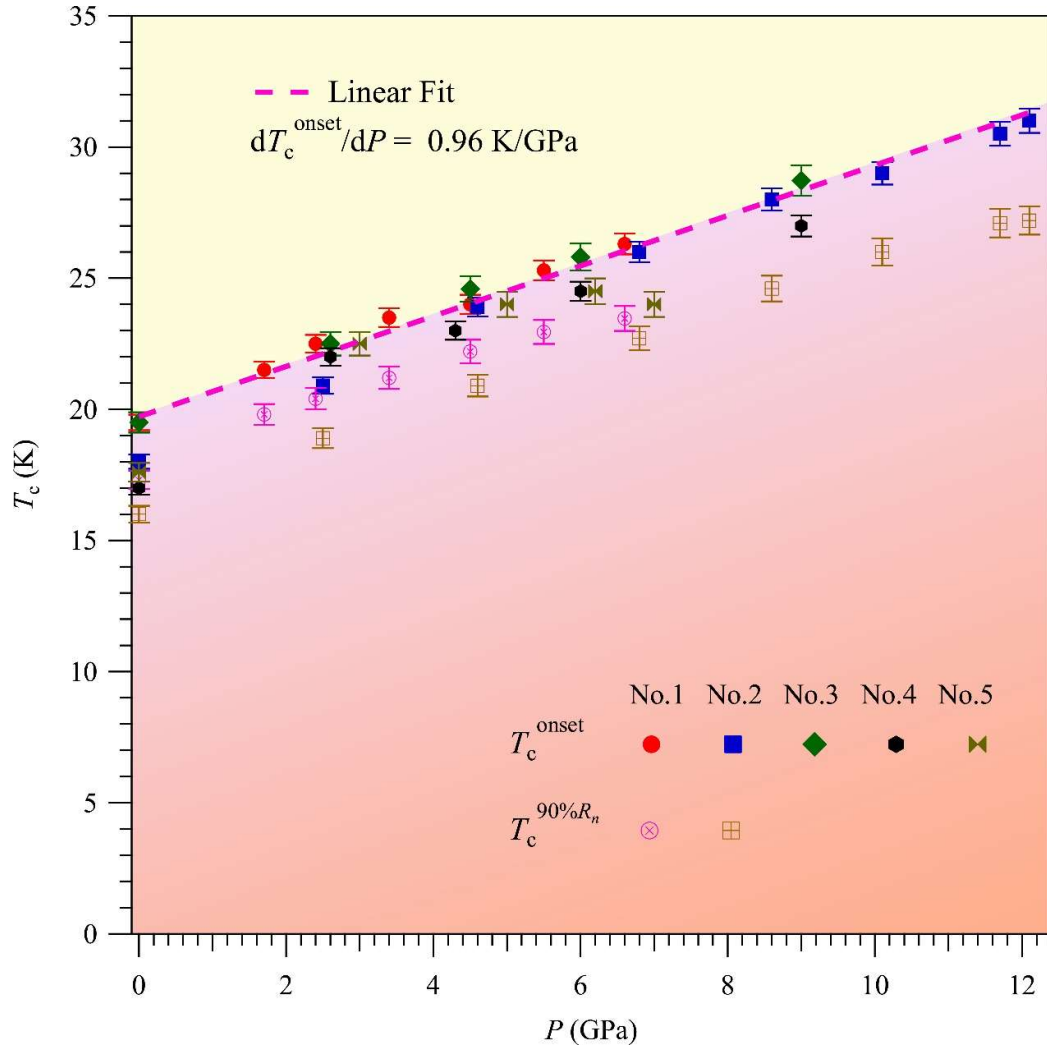


Figure 3. Temperature-pressure phase diagram of $\text{Pr}_{0.82}\text{Sr}_{0.18}\text{NiO}_2$ thin films. Pressure dependences of the superconducting transition temperatures T_c^{onset} and $T_c^{90\%R_n}$ determined from the $\rho(T)$ measurements. Linear fit to the T_c^{onset} gives the relation $T_c(P) = 19.7 + 0.96 \times P$.

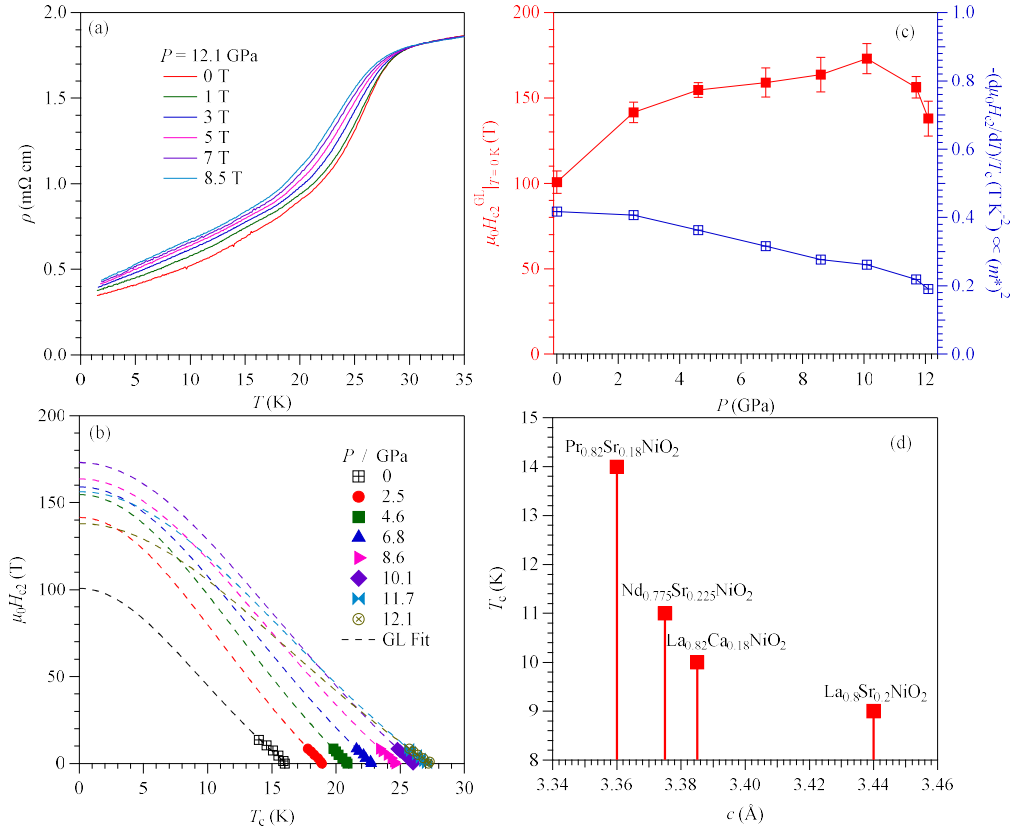


Figure 4. (a) Temperature dependences of the resistivity with magnetic fields up to 8.5 T at 12.1 GPa. (b) Temperature dependences of the upper critical field $\mu_0 H_{c2}$ at different pressures, where $\mu_0 H_{c2}$ values are determined by using the criteria of 90% ρ_n . The broken lines represent the Ginzburg–Landau (G-L) fitting curves. (c) Pressure dependence of the zero-temperature upper critical field $\mu_0 H_{c2}(0)$ obtained from the empirical G-L fitting and the normalized slope $-(1/T_c)[d\mu_0 H_{c2}/dT]|_{T_c}$. (d) c -axis dependence of T_c in the series of infinite nickelates superconducting thin films.