

Optical, luminescence, and scintillation properties of advanced ZnWO₄ crystal scintillators

P. Belli ^{a,b}, R. Bernabei ^{a,b,2}, Yu.A. Borovlev ^{c,d}, F. Cappella ^{e,f}, V. Caracciolo ^{a,b}, R. Cerulli ^{a,b}, F.A. Danevich ^g, V.Ya. Degoda ^h, A. Incicchitti ^{e,f}, D.V. Kasperovych ^g, Ya.P. Kogut ^h, A. Leoncini ^{a,b}, G.P. Podust ^h, A.G. Postupaeva ^d, V.N. Shlegel ^c

^a INFN, sezione di Roma “Tor Vergata”, I-00133 Rome, Italy

^b Dipartimento di Fisica, Università di Roma “Tor Vergata, I-00133 Rome, Italy

^c Nikolaev Institute of Inorganic Chemistry, 630090 Novosibirsk, Russia

^d CML Ltd, 630090 Novosibirsk, Russia

^e INFN, sezione di Roma, I-00185 Rome, Italy

^f Dipartimento di Fisica, Università di Roma “La Sapienza”, I-00185 Rome, Italy

^g Institute for Nuclear Research of NASU, 03028 Kyiv, Ukraine

^h Taras Shevchenko National University of Kyiv, 01601 Kyiv, Ukraine

Abstract

Zinc tungstate (ZnWO₄) crystal scintillators are promising detection material for the experiments searching for double beta decay, dark matter, and investigating rare alpha decays. An extended R&D was performed to develop advanced quality ZnWO₄ crystal scintillators. The R&D programme included the selection of the initial materials, the variation of the compound stoichiometry, the application of single and double crystallization, and the annealing of the crystal boules. The optical transmittance of the produced boules was measured, and the luminescence under X-ray excitation in the temperature region from 85 K to room temperature was studied (thermally stimulated luminescence was measured till 350 K). The energy resolution and the relative scintillation pulse amplitude were measured with gamma-sources demonstrating high scintillation properties of the samples produced by single crystallization from deeply purified zinc and tungsten oxides, with stoichiometric composition, annealed in air atmosphere.

Keywords: ZnWO₄ scintillators, Crystal scintillators development, Luminescence under X-ray excitation, Optical transmission, Scintillation response

1. Introduction

The zinc tungstate (ZnWO₄) is a crystal luminescent material well-known since more than seventy years [1]. The ZnWO₄ crystal growth techniques were developed, and the luminescence and the scintillation properties of the material were studied taking into account its high stopping power and high scintillation efficiency [2, 3, 4, 5, 6, 7, 8, 9]. Effects of doping by different elements to increase ZnWO₄ crystals light yield were investigated too [10, 11, 12, 13, 14, 15, 16, 17].

The material was considered for the first time in the 1980s as possible detector to search for double beta decay of Zn and W isotopes [18]. The first low-background measurements with a small 4.5 g scintillator were performed at the Solotvina Underground Laboratory to demonstrate applicability of ZnWO₄ crystal scintillators for double beta decay and dark matter experiments [19]. Further development of the material was also motivated by attempts for increasing the crystals

² e-mail: rita.bernabei@roma2.infn.it (corresponding author)

volume, for improving the optical and the scintillation characteristics [20, 21, 22] and for utilizing as low-temperature scintillation bolometer [23, 24]. Consequently, high sensitivity double beta decay experiments were realized by using large volume and high optical quality ZnWO_4 crystal scintillators [25, 26, 27]. The results were obtained thanks to the very high level of radiopurity of the material [28, 29, 30].

Anisotropic properties of the ZnWO_4 scintillators offer an interesting possibility to exploit the directionality approach to investigate the presence of dark matter candidates that induce nuclear recoils [31, 32]. The goal of the ADAMO project is the development of ZnWO_4 crystal scintillators with extremely low radioactive contamination and very high optical and scintillation properties capable to provide as low as possible energy threshold and background level at low energies. The R&D of advanced large volume ZnWO_4 crystal scintillators for low-counting experiments is in progress [33].

The development of high scintillation efficiency ZnWO_4 scintillators requires a clear understanding of the scintillation process, emission nature and mechanisms, study of the production technology, quality, and composition of the raw materials for the crystals' growth on the optical and scintillation properties of the material. The production of several samples of ZnWO_4 crystals will be described in the next Section. Experimental techniques, measurements, results, and discussion of optical, luminescence and scintillation measurements are presented in Section 3. The main results of the study are summarised in the Conclusions Section.

2. Development of advanced ZnWO_4 crystal scintillators

High quality large volume ZnWO_4 crystal scintillators have been developed in the Nikolaev Institute of Inorganic Chemistry (NIIC, Novosibirsk, Russia) with the help of the low-thermal gradient Czochralski technique (LTG Cz) [33, 34, 35, 36, 37]. The samples studied in the present work were produced by the Crystal Manufacturing Laboratory Ltd. (CML, Novosibirsk, Russia) in air atmosphere in a platinum crucible 50 mm in diameter and 100 mm height installed into three zone resistance heater. The ratio between ZnO and WO_3 in the initial powder for the crystal growth was chosen according to the phase diagram of the $\text{ZnO}-\text{WO}_3$ system. The powder was synthesized by using reaction $\text{WO}_3 + \text{ZnO} \rightarrow \text{ZnWO}_4$. High purity grade zinc oxide (99.995%) produced by Umicore (Belgium) was used for the R&D. Several samples of tungsten oxide of different origin were utilized:

- synthesized at the NIIC with Si concentration <50 ppm and concentration of transition metals no more than 1 ppm, the material development is described in [35] (denoted hereafter as “ WO_3 NIIC I”);
- purified at the NIIC using an additional process of sublimation of tungsten chlorides (denoted as “ WO_3 NIIC II”);
- manufactured by Nippon Tungsten Co., Ltd. (Japan);
- manufactured by Japan New Metals Co., Ltd (JNM, 4N grade CWO) with a maximum Fe content <1 ppm and a maximum Mo content less than 10 ppm.

The rotation speed during the crystal growth was in the range from 3 rpm to 6 rpm, the crystallization rate was 1.5 mm / h, all crystals were grown in the [010] direction by using oriented crystal seeds. The single crystallization samples were grown from the initial powder, while the double crystallization samples were grown by recrystallization of the single crystallization crystalline material. In addition to the crystals produced from stoichiometric ZnWO_4 compound, some amount

of ZnO or WO₃ (see Table 1) was added to study dependence of the material properties on its composition. After the crystal growth process, the crystal boules were annealed in air atmosphere over 24 h (except the boules produced by double crystallization, see Table 1).

Table 1. The samples of ZnWO₄ crystals used in the present study and the boules of origin.

Crystal boule	Sample size (mm ³)	Number of crystallizations	WO ₃	Compound stoichiometry
No. 75	10 × 10 × 2 Ø30 × 60	Double	NIIC II	+ 0.3 % of WO ₃
No. 76	10 × 10 × 2 Ø30 × 60	Double	Nippon Tungsten Co., Ltd	+ 0.25 % of ZnO
No. 83	10 × 10 × 2 Ø30 × 60	Single, annealed	NIIC I	+ 0.15 % of WO ₃
No. 84	10 × 10 × 2 Ø30 × 60	Single, annealed	NIIC I	stoichiometric
No. 85	10 × 10 × 2 Ø30 × 60	Single, annealed	Japan New Metals Co., Ltd	stoichiometric
No. 91	Ø30 × 67	Single, annealed	NIIC I	stoichiometric
No. 94	Ø30 × 31 Ø30 × 32	Single, annealed	NIIC I	stoichiometric

The crystalline boules are shown in Fig. 1. One can see that, while the boules No. 75 and 76 have the typical pink colour of ZnWO₄ crystals, the optical quality of the crystals No. 83–85 and 91 is rather high.

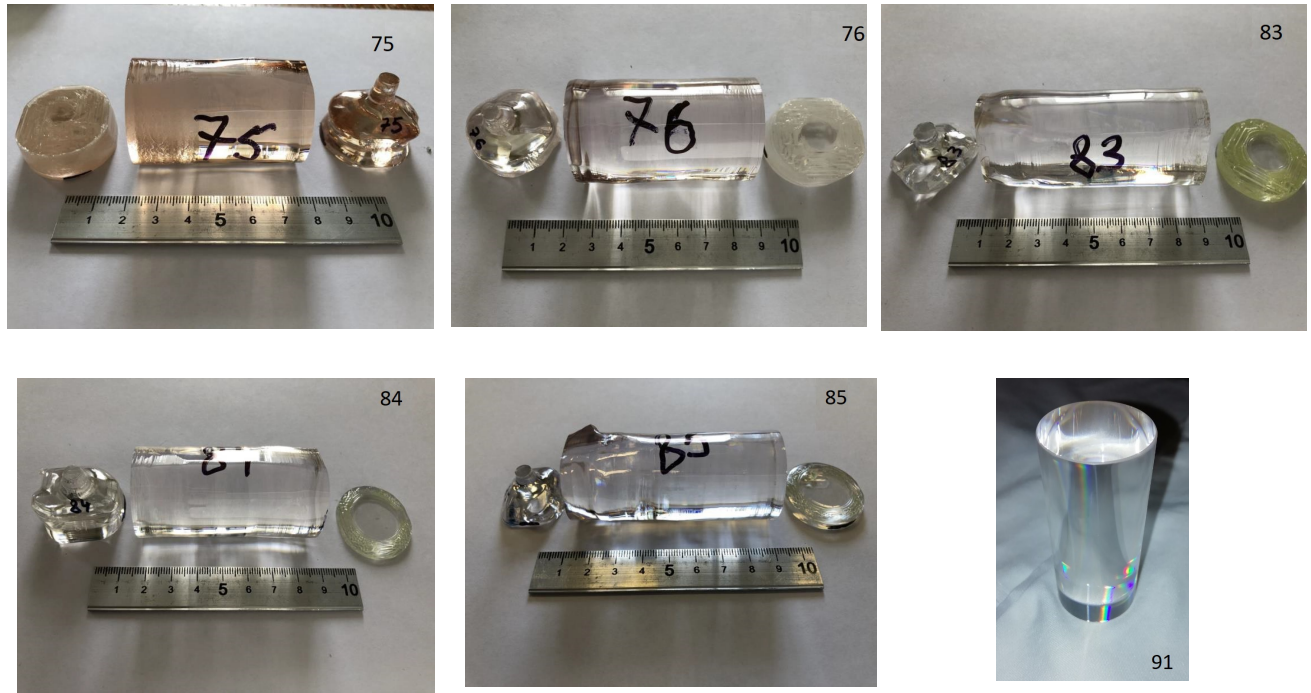


Fig. 1. Photographs of the crystalline boules 75, 76, 83–85 and sample with sizes $\text{Ø}30 \times 67 \text{ mm}^3$ produced from the crystalline boule No. 91 used in the present study. The crystal boules numbers are given on the photographs.

Samples with sizes $\text{Ø}30 \times 60 \text{ mm}^3$ with optically polished faces were cut from the boules for optical transmission measurements. One more sample for optical measurements was cut from the boule No. 91 with sizes $\text{Ø}30 \times 67 \text{ mm}^3$ (the sample is shown in Fig. 1 too). Samples with sizes $10 \times 10 \times 2 \text{ mm}^3$ were cut from the boules for the luminescence investigations. The samples surfaces were optically polished. Two samples of cylindrical shape with sizes $\text{Ø}30 \times 31 \text{ mm}^3$ and $\text{Ø}30 \times 32 \text{ mm}^3$ were produced from the boule No. 94. One was used for energy resolution, and both are now used for low-background tests (the low-background measurements are in progress and will be described in a separate report). All the samples are listed in Table 1.

3. Measurements, results, and discussion

3.1. Optical transmission

The optical transmission of the ZnWO_4 cylindrical-shaped samples with sizes $\text{Ø}30 \times 60 \text{ mm}^3$ produced from the crystal boules No. 75, 76, 83–85 was measured by using a UV-2201 Double-beam UV-spectrophotometer from Shimadzu. The face surfaces of the samples for the transmission measurements were optically polished. In order to compensate the light losses at the surfaces of the samples due to the Fresnel reflection caused by the high refraction index (that depends on the wavelength), a 1-mm-thick polished ZnWO_4 disk was installed in the reference channel of the spectrophotometer. The optical transmission of the ZnWO_4 sample No. 91 was measured using a Perkin Elmer UV/VIS spectrometer Lambda 18. A thin (1.8 mm) sample of the ZnWO_4 crystal was placed in the reference beam of the instrument to correct the reflection losses. The results of the measurements are presented in Fig. 2. In general, the transmission spectra agree with the literature data [14, 20, 21, 23, 38]. However, the transmission varies substantially depending on the sample

production protocol. In particular, the samples produced by double crystallization are definitely of worse optical quality.

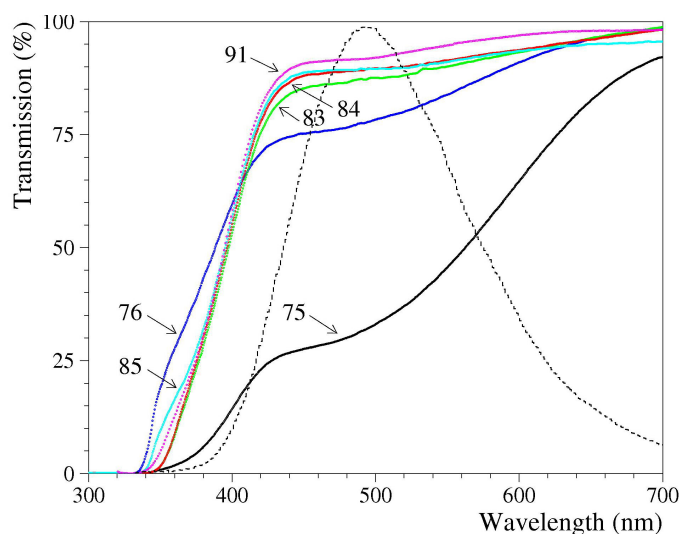


Fig. 2. Optical transmission spectra of single (samples 83–85, 91) and double crystallization (samples 75 and 76) ZnWO_4 crystals. Emission spectrum of one of the samples at room temperature is shown by dashed line (see Section 3.2).

3.2. Luminescence under X-ray excitation

3.2.1. Experimental

To measure the luminescence of ZnWO_4 crystals under X-ray excitation (XRL) the samples with sizes $10 \times 10 \times 2 \text{ mm}^3$ were installed on a copper holder inside a vacuum cryostat and irradiated by X-ray through a beryllium window. The temperature of the crystal holder was controlled by using a chromel-copel thermocouple and a semiconductor silicon sensor. An X-ray tube with a copper anode operated at 20 kV, with current 25 mA and flux of 0.25 mW/cm^2 was used as an X-ray source. XRL of the ZnWO_4 samples was measured in a wide region where the spectral sensitivity of the set-up was determined by the used photomultiplier tube (PMT, FEU-106, sensitive in a wide wavelength region of 350–820 nm). The emission spectra were registered by a second PMT FEU-106 after selection of a narrow spectral range by using a monochromator MDR-2 with a 600 nm^{-1} diffraction grating.

3.2.2. Emission spectra

The emission spectra of the ZnWO_4 crystal samples under X-ray irradiation at 85 K and 295 K, corrected for the spectral sensitivity of the set-up, are shown in Fig. 3. The spectra are peaked at $\approx 494 \text{ nm}$ at room temperature and at $\approx 502 \text{ nm}$ at 85 K. The results are in a reasonable agreement with the reported values 479–502 nm for ZnWO_4 crystals under X-ray excitation [3, 4, 14, 15, 39, 40]. A certain shift of the emission spectral maximum is observed in all the samples. One can see a clear difference in the XRL intensity of the samples³. The spread of the XRL intensity is bigger at room temperature. The difference can be explained by presence of nonradiative recombination centres

³ The uncertainty of the measured XRL intensity does not exceed 3% and is determined by the PMTs dark current of the registration-system amplifiers noise.

(caused by defects of different nature) that compete with the radiative recombination centres. It is natural to assume that the concentration of defects depends on the crystals production technology.

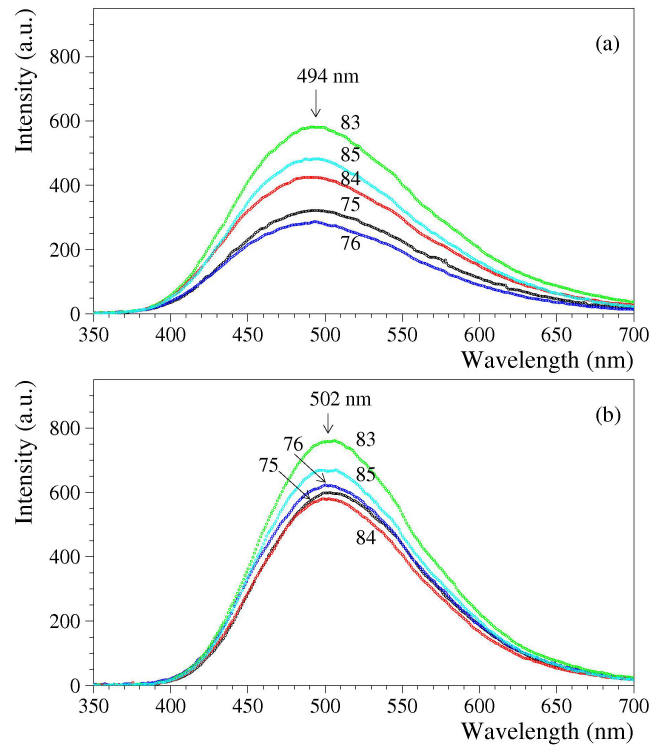


Fig. 3. Emission spectra of the ZnWO₄ samples under X-ray irradiation at 295 K (a) and 85 K (b). The labels “75”, “76”, “83”, “84”, “85” correspond to the sample numbers.

3.2.3. Temperature and dose dependence of XRL intensity

The dependence of the ZnWO₄ samples XRL intensity on temperature was measured at the sample cooling from (278 – 293) K to \approx 90 K. The dependence is shown in Fig. 4. The luminescence intensity increased with temperature decrease, in agreement with the data of other studies [40, 41]. It should be stressed that increase of the scintillation signals amplitude with decrease of temperature is higher, roughly by a factor 2 [5, 22, 23]. It can be explained by different nature of scintillation and luminescence response (see also Fig. 9 and related discussion in Section 3.3).

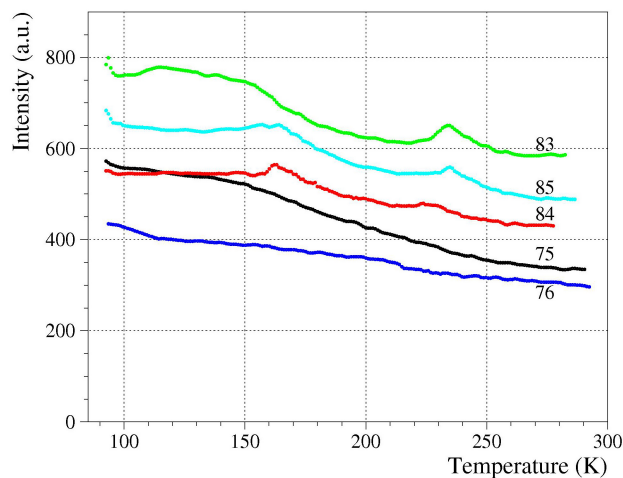


Fig. 4. Temperature dependency of the ZnWO₄ crystal samples XRL intensity. The curves variations can be explained by uneven cooling rate of the samples.

The dose dependences of the XRL intensity was measured under constant intensity X-ray radiation. The XRL intensity decreases with accumulation of dose (see Fig. 5). A decrease of a ZnWO₄ scintillator light output under X-ray irradiation was also reported in [42].

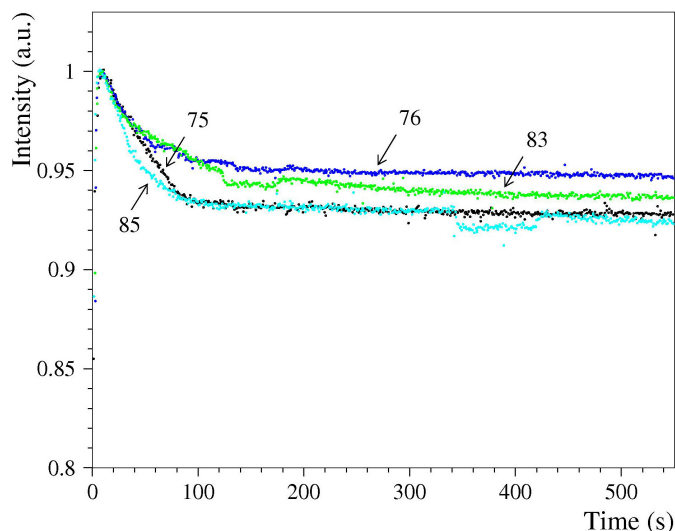


Fig. 5. Dose dependence of the ZnWO₄ samples XRL intensity measured at room temperature. The data are normalised on the maxima values 7–9 sec after measurement start. The jumps on the curves are due to unstable operation of the X-ray tube.

3.2.4. Phosphorescence

The ZnWO₄ samples phosphorescence have been measured for ≈ 8 min after irradiation of 20 min at 85 K with an exposure dose of 0.30 J/cm². Rather intensive slowly decaying phosphorescence component is observed after X-ray irradiation at 85 K (see Fig. 6). The observation indicates a noticeable number of different traps in the ZnWO₄ crystal samples. It should be noted that the sensitivity of the recording system to register the phosphorescence was increased by two orders of magnitude. This means that the concentration of the traps that cause phosphorescence are orders of magnitude lower than the concentration of the radiative recombination centres in the ZnWO₄ crystals.

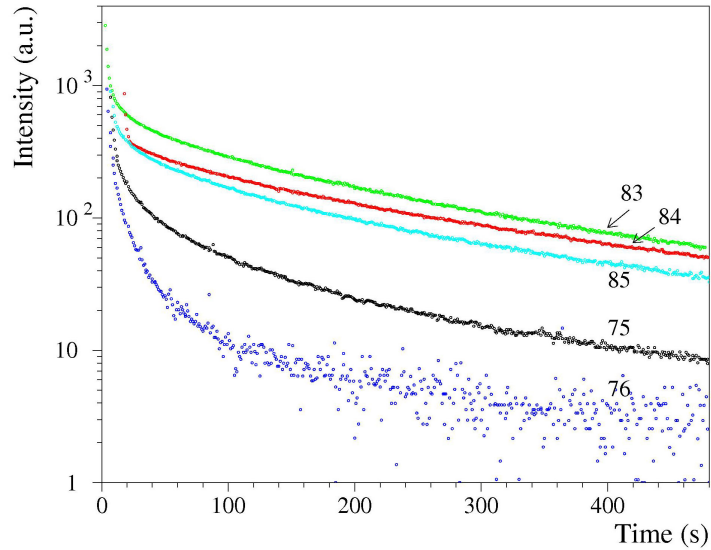


Fig. 6. XRL phosphorescence of the ZnWO_4 samples measured at 85 K after X-ray irradiation over 20 min.

3.2.5. Thermally stimulated luminescence

After the phosphorescence measurements the samples were heated with a rate (0.30 ± 0.02) K/s to study the thermally stimulated luminescence (TSL). TSL was observed in the ZnWO_4 crystal samples after irradiation by high energy γ -rays at low temperature [17, 14]. In the present study TSL was registered after X-ray irradiation over 20 min (that corresponds to a dose 0.30 J/cm^2) at 85 K. The TSL curves are presented in Fig. 7. It should be noted that no detectable TSL and phosphorescence were observed after the sample irradiation at 295 K.

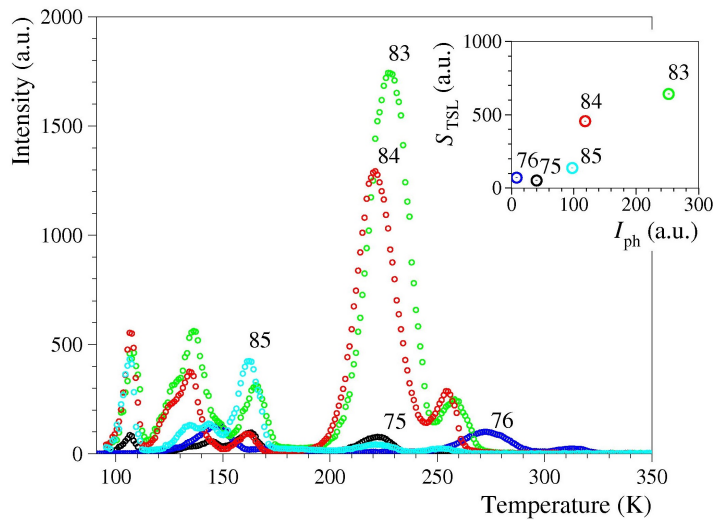


Fig. 7. Thermally stimulated luminescence of ZnWO_4 crystal measured after X-ray irradiation over 20 min at temperature 85 K. Inset: area of TSL curves in the temperature interval 95-320 C (S_{TSL}) versus phosphorescence intensity at 200 sec after the X-ray irradiation termination (I_{ph}).

From the TSL data one can conclude that all the crystal samples have similar set of traps, however with different concentration. For instance, the concentration of traps in the samples No. 83, 84 and 85 (produced by single crystallization) is much higher than in the samples No. 75 and 76 (grown by double crystallization).

Areas of the TSL curves in the temperature interval 95-320 C (S_{TSL}) versus phosphorescence intensities at 200 sec after the X-ray irradiation termination (I_{ph}) are presented in Inset of Fig. 7. It should be stressed that phosphorescence and TSL appear due to different traps. Thus, some correlation between the TSL and phosphorescence intensities indicates that the concentration of all kinds of traps in the crystal varies depending on the growing technology.

3.3. Scintillation properties

Scintillation measurements of the $10 \times 10 \times 2$ mm samples produced from the crystal boules No. 75, 76, 83 – 85 were performed by using a 3 in. photomultiplier tube Hamamatsu model R6233-100 with a bialkali photocathode with a spectral response in the wavelength interval from 300 nm to 650 nm, with a peak sensitivity at 420 nm. The crystal samples were optically coupled to the PMTs photocathode with the help of a Dow Corning Q2-3067 optical couplant and covered by Teflon tape to improve the scintillation light collection. The signals from the PMT entered a SAMP-04 spectroscopy amplifier with a 15 μ s shaping time and then were processed by a peak sensitive analog-to-digital converter (both units produced by the Intelligent Electronic Systems, Kharkiv, Ukraine). The crystals surface was diffused by sanding paper with an average grain size 20 μ m. The energy spectrum of γ -ray quanta of ^{137}Cs , ^{207}Bi , and ^{241}Am γ -sources measured with the ZnWO_4 crystal sample No. 84 (showing the highest light output) is presented in Fig. 8. It should be stressed that so high energy resolution (R , full-width half-maximum over peak position) was never reported for ZnWO_4 crystal scintillators.

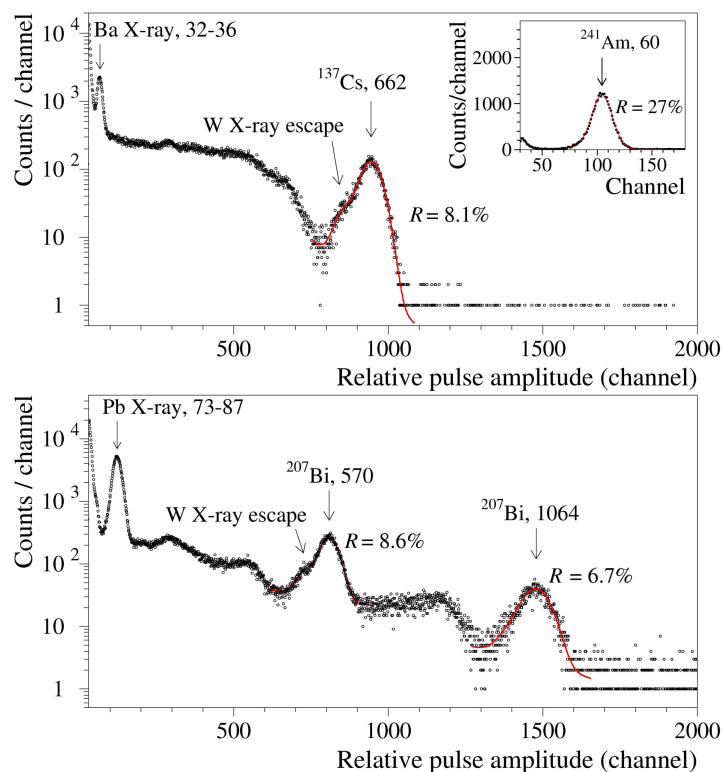


Fig. 8. The energy spectra of γ -ray quanta of ^{137}Cs and ^{207}Bi measured by scintillation detector with the ZnWO_4 crystal sample No. 84. Energy spectrum of γ -ray quanta of ^{241}Am is shown in Inset. Energy of X-ray and γ -ray quanta is in keV.

The data on the relative scintillation pulse amplitude (estimated from the scintillation measurements for 570-keV γ -peak of ^{207}Bi) versus relative luminescence intensity of the ZnWO_4 crystal samples at room temperature are presented at Fig. 9 (filled circles). These two characteristics do not correlate as one naively would expect. Possible explanations can be a contribution of phosphorescence that does not affect the scintillation pulse amplitude, and a dose dependence of XRL intensity that is negligible in scintillation measurements.

To estimate a possible degradation of ZnWO_4 scintillation efficiency after the X-ray irradiation, the samples that have not been used for the XRL measurements were investigated as scintillators in the same conditions (see Fig. 9, open circles). Despite the XRL measurements were performed in December 2020, one year before the scintillation test (in December 2021), the samples irradiated with a dose $\sim (1.4\text{--}1.6) \text{ W} \times \text{cm}^2$ showed a slightly lower scintillation light output at level of 1.4% – 5.7% than the non-irradiated ones.

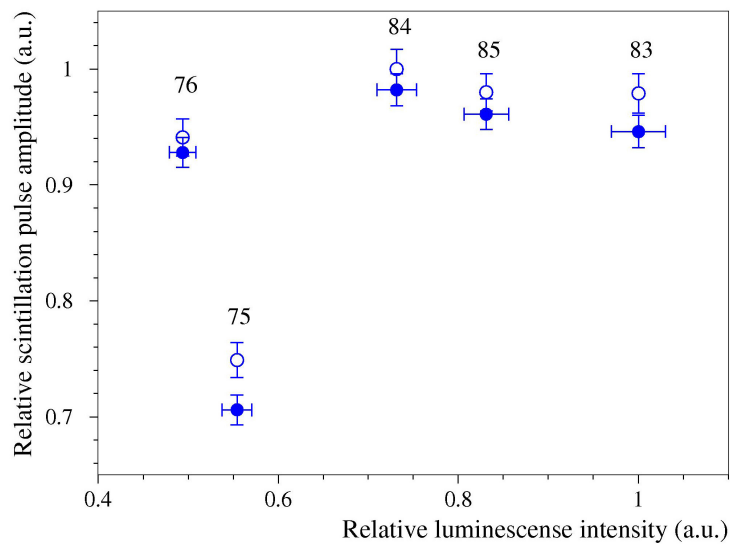


Fig. 9. Relative scintillation pulse amplitude versus relative XRL intensity of the ZnWO_4 crystal samples at room temperature (filled circles). Results of scintillation measurements with non-irradiated samples are shown by open circles.

The scintillation properties of a ZnWO_4 scintillator $\text{Ø}30 \times 31 \text{ mm}^3$ cut from the boule No. 94 were tested with the same equipment. The crystals surface was diffused by sanding paper with an average grain size $46 \mu\text{m}$. For scintillation light collection the scintillator was wrapped by few layers of Teflon tape and by one layer of aluminized film. Energy spectra measured by the scintillation detector with ^{60}Co , ^{137}Cs , ^{232}Th and ^{241}Am γ -sources are presented in Fig. 10. The obtained energy resolutions are rather high; they are near the best reported for ZnWO_4 crystal scintillators [20, 22, 23, 43, 44].

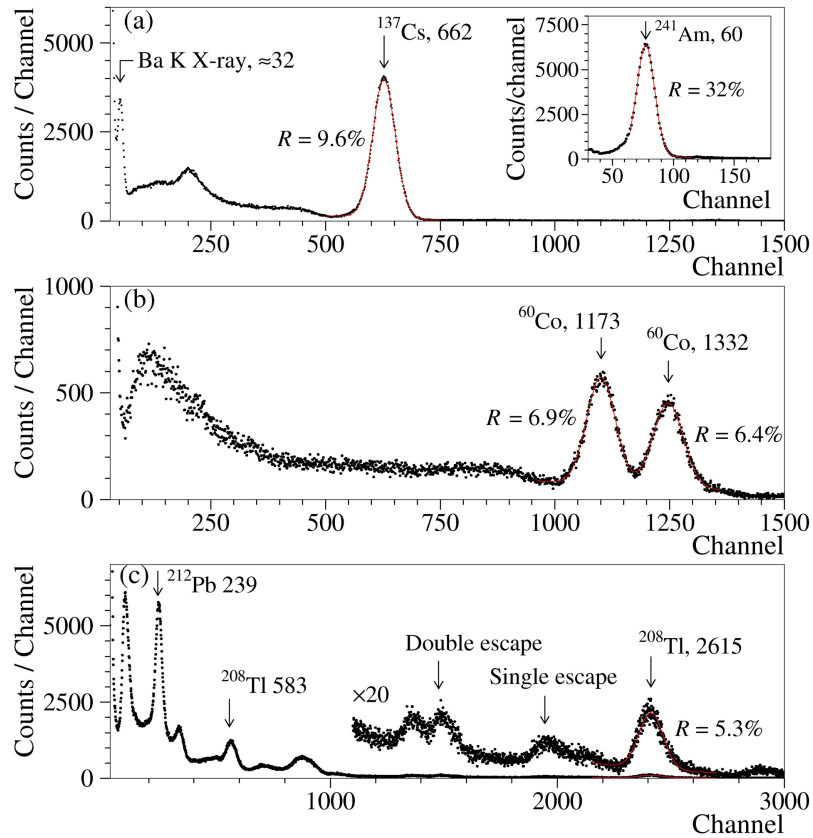


Fig. 10. Energy spectra of γ -ray quanta of ^{137}Cs (a), ^{60}Co (b) and ^{232}Th (c) measured by scintillation detector with the ZnWO_4 crystal No. 94 with sizes $\varnothing 30 \times 31$ mm. Energy spectrum of ^{241}Am is shown in Inset.

5. Conclusions

High optical and scintillation properties ZnWO_4 crystal scintillators were developed by using the low-thermal gradient Czochralski technique after an extended R&D that included variation of the compound stoichiometry, using of initial WO_3 of different producers and additionally purified, utilization of single and double crystallization with and without annealing of the grown boules.

Luminescence under X-ray excitation of the developed ZnWO_4 crystals (emission spectra, temperature and dose dependencies of the luminescence intensity, phosphorescence, and thermally stimulated luminescence) was studied in the temperature region from 85 K to room temperature (thermally stimulated luminescence was measured till 350 K). Scintillation properties of the ZnWO_4 crystals were tested with ^{60}Co , ^{137}Cs , ^{207}Bi , ^{232}Th and ^{241}Am γ -ray sources, optical transmission spectra of the samples were measured in the wavelength interval 300–700 nm. The best optical and scintillation characteristics were obtained with ZnWO_4 crystal samples grown by single crystallization from the ZnWO_4 compound of the stoichiometric composition prepared from deeply purified WO_3 , annealed in air atmosphere. Surprisingly the double crystallization leads to deterioration of the optical, luminescent and scintillation properties of the material, despite lower level of phosphorescence and thermally stimulated luminescence that is evidence of a lower defects' concentration. It can be explained by the increase of competing centres of nonradiative recombination concentration (further study of the material luminescence mechanisms is a subject of another report [45]). No clear correlation was observed between the scintillation light output and luminescence intensity of the samples that can be explained by phosphorescence and dose

dependence of XRL intensity that are both negligible in scintillation measurements. The absence of correlation between the luminescence intensity and the scintillation pulse amplitude indicates that the achieved scintillators quality (especially of the samples produced by double crystallization) is not perfect and there is still room to improve the ZnWO_4 production technology.

Low-background measurements of two highest optical quality crystal samples produced from the crystal boule No. 94 are running at the INFN Gran Sasso underground laboratory to estimate radioactive contamination of the material. A further R&D is in progress aiming at development of larger volume crystals for low counting experiments.

Acknowledgements

Yu.A. Borovlev and V.N. Shlegel were supported by the Ministry of Science and Higher Education of the Russian Federation N121031700314-5. F.A.Danevich and D.V. Kasperovych were supported in part by the National Research Foundation of Ukraine Grant No. 2020.02/0011.

References

-
- [1] F.A. Kroger, *Some Aspects of the Luminescence of Solids* (Elsevier Publishing Company, Inc., New York, 1948).
 - [2] L.G. van Uitert, R.R. Soden, Single Crystal Tungstates for Resonance and Emission Studies, *J. Appl. Phys.* 31 (1960) 328.
 - [3] T. Oi, K. Takagi, T. Fukazawa, Scintillation study of ZnWO_4 single crystals, *Appl. Phys. Lett.* 36 (1980) 278.
 - [4] B.C. Grabmaier, Crystal scintillators, *IEEE Trans. Nucl. Sci.* NS-31 (1984) 372.
 - [5] H. Grassmann, H.-G. Moser, E. Lorenz, Scintillation properties of ZnWO_4 , *J. Lumin.* 33 (1985) 109.
 - [6] I. Holl, E. Lorenz, G. Mageras, A measurement of the light yield of common inorganic scintillators, *IEEE Trans. Nucl. Sci.* 35 (1988) 105.
 - [7] Y.C. Zhu, et al., Measurements of the scintillation properties of ZnWO_4 crystals, *Nucl. Instr. and Meth. A* 244 (1986) 579.
 - [8] M. Ishi, I. Kobayashi, Single crystals for radiation detectors, *Progr. Cryst. Growth Charact.* 23 (1991) 245.
 - [9] A.E. Ovechkin, V.D. Ryzhikov, G. Tomylaitis, A. Zukauskas, Luminescence of ZnWO_4 and CdWO_4 crystals. *Phys.Stat. Sol. a* 103 (1987) 285.
 - [10] V. Nagirnyi et al., Iron-related luminescence centers in $\text{ZnWO}_4\text{:Fe}$, *Radiat. Eff. Defects Solids* 157 (2002) 1123.
 - [11] L. Grigorjeva et al., Time – resolved spectroscopy in ZnWO_4 and $\text{ZnWO}_4\text{:Fe}$, *Radiation Effects and Defects in Solids* 158 (2003) 135.
 - [12] H. He, J. Huang, L. Cao, J. Wu, Synthesis and luminescence property of Fe-doped ZnWO_4 powders with aqueous solution reaction, *J. Optoelectron. Adv. Mater.* 3 (2009) 236.
 - [13] H. Y. He et al., Luminescence of Fe-substituted ZnWO_4 powders synthesized by aqueous solution reaction, *Int. J. Mater. Res.* 101 (2010) 852.
 - [14] N.R. Krutyak et al., The features of energy transfer to the emission centers in ZnWO_4 and $\text{ZnWO}_4\text{:Mo}$, *J. Lumin.* 144 (2013) 105.
 - [15] D. Spassky et al., Energy transfer in solid solutions $\text{Zn}_x\text{Mg}_{1-x}\text{WO}_4$, *Opt. Mater.* 36 (2014) 1660.

-
- [16] L. Kostyk, A. Luchechko, S. Novosad, The influence of chromium impurity on the luminescence properties of ZnWO₄ crystals, *Electronics and information technologies* 5 (2015) 33.
- [17] S. Novosad et al., Low Temperature Luminescence of ZnWO₄ Crystals with Li Impurity, *Proceedings of the 2019 XIth International Scientific and Practical Conference on Electronics and Information Technologies (ELIT) 2019*, DOI: 10.1109/ELIT.2019.8892292
- [18] F.A. Danevich et al., CdWO₄, ZnSe and ZnWO₄ scintillators in studies of 2β-processes, *Instr. Exp. R.* 32 (1989) 1059.
- [19] F.A. Danevich et al., ZnWO₄ crystals as detectors for 2β decay and dark matter experiments, *Nucl. Instrum. Meth. A* 544 (2005) 553.
- [20] L.L. Nagornaya et al., Growth of ZnWO₄ Crystal Scintillators for High Sensitivity 2β Experiments, *IEEE Trans. Nucl. Sci.* 55 (2008) 1469.
- [21] F.A. Danevich et al., Scintillation properties of pure and Ca-doped ZnWO₄ crystals. *Phys. Stat. Sol. a* 205 (2008) 335.
- [22] L.L. Nagornaya et al., Large Volume ZnWO₄ Crystal Scintillators With Excellent Energy Resolution and Low Background, *IEEE Trans. Nucl. Sci.* 56 (2009) 994.
- [23] H. Kraus et al., ZnWO₄ scintillators for cryogenic dark matter experiments. *Nucl. Instrum. Meth. A* 600 (2009) 594.
- [24] I. Bavykina et al., Development of cryogenic phonon detectors based on CaMoO₄ and ZnWO₄ scintillating crystals for direct dark matter search experiments, *Opt. Mater.* 31 (2009) 1382.
- [25] P. Belli et al., Search for 2β processes in ⁶⁴Zn with the help of ZnWO₄ crystal scintillator, *Phys. Lett. B* 658 (2008) 193.
- [26] P. Belli et al., Search for double beta decay of zinc and tungsten with low-background ZnWO₄ crystal scintillators, *Nucl. Phys. A* 826 (2009) 256.
- [27] P. Belli et al., Final results of an experiment to search for 2β processes in zinc and tungsten with the help of radiopure ZnWO₄ crystal scintillators, *J. Phys. G* 38 (2011) 115107.
- [28] P. Belli et al., Radioactive contamination of ZnWO₄ crystal scintillators, *Nucl. Instr. Meth. A* 626&627 (2011) 31.
- [29] A.S. Barabash et al., Improvement of radiopurity level of enriched ¹¹⁶CdWO₄ and ZnWO₄ crystal scintillators by recrystallization, *Nucl. Instrum. Meth. A* 833 (2016) 77.
- [30] F.A. Danevich, V.I. Tretyak, Radioactive contamination of scintillators, *Int. J. Mod. Phys. A* 33 (2018) 1843007.
- [31] F. Cappella et al., On the potentiality of the ZnWO₄ anisotropic detectors to measure the directionality of Dark Matter, *Eur. Phys. J. C* 73 (2013) 2276.
- [32] P. Belli et al., Measurements of ZnWO₄ anisotropic response to nuclear recoils for the ADAMO project, *Eur. Phys. J. A* 56 (2020) 83.
- [33] P. Belli et al., New development of radiopure ZnWO₄ crystal scintillators, *Nucl. Instr. Meth. A* 935 (2019) 89.
- [34] A.A. Pavlyuk et al., Low Thermal Gradient technique and method for large oxide crystals growth from melt and flux, in *Proceedings of The APSAM-92, Asia Pacific Society for Advanced Materials, Shanghai, P.R.C., 26–29 April 1992, Institute of Materials Research, Tohoku University, Sendai, Japan, 1993*, p. 164.
- [35] I.M. Ivanov et al., Extrapure WO₃ for the preparation of CdWO₄ single crystals, *Inorg. Mater.* 44 (2008) 1330.

-
- [36] E.N. Galashov, V.A. Gusev, V.N. Shlegel, Y.V. Vasiliev, Growing of ZnWO₄ single crystals from melt by the low thermal gradient Czochralski technique, *Functional Materials* 16 (2009) 63.
- [37] V.N. Shlegel et al., Recent progress in oxide scintillation crystals development by low-thermal gradient Czochralski technique for particle physics experiments, *JINST* 12 (2017) C08011.
- [38] L.A. Lisitsyna, Influence of oxygen on luminescent properties of ZnWO₄ crystals surface, *IOP Conf. Ser.: Mater. Sci. Eng.* 110 (2016) 012083.
- [39] K. Takagi et al., Growth of high purity ZnWO₄ single crystals, *J. Cryst. Growth* 52 (1981) 580.
- [40] Z. Kowalski et al., Radioluminescence, low temperature thermoluminescence and scintillation properties of Ca and Eu doped ZnWO₄ single crystals, *Radiat. Meas.* 118 (2-18) 1.
- [41] H. Kraus et al., Feasibility study of a ZnWO₄ scintillator for exploiting materials signature in cryogenic WIMP dark matter searches, *Phys. Lett. B* 610 (2005) 37.
- [42] L.L. Nagornaya et al., Radiation stability of tungstate-based scintillators in radiometric control systems, *Proceedings of 1994 IEEE Nuclear Science Symposium - NSS'94*.
doi:10.1109/nssmic.1994.474386
- [43] F.A. Danevich et al., Optimization of light collection from crystal scintillators for cryogenic experiments, *Nucl. Instrum. Meth. A* 744 (2014) 41.
- [44] W. Klamra et al., Properties of CdWO₄ and ZnWO₄ scintillators at liquid nitrogen temperature, *JINST* 7 (2012) P03011.
- [45] V.Ya. Degoda et al., Luminescence of ZnWO₄ crystals under X-ray excitation, submitted to *J. Lumin.*