

Spin-orbital order and excitons in magnetoresistive HoBi

J. Gaudet,^{1,2,3,*} H.-Y. Yang,⁴ E. M. Smith,⁵ T. Halloran,¹ J. P. Clancy,⁵ J. A. Rodriguez-Rivera,^{2,3} Guangyong Xu,² Y. Zhao,^{2,3} W. C. Chen,² G. Sala,⁶ A. A. Aczel,⁷ B. D. Gaulin,^{5,8,9} F. Tafti,⁴ and C. Broholm^{1,2,7}

¹*Institute for Quantum Matter and Department of Physics and Astronomy,
Johns Hopkins University, Baltimore, MD 21218, USA*

²*Center for Neutron Research, National Institute of Standards and Technology, MS 6100 Gaithersburg, Maryland 20899, USA*

³*Department of Materials Science and Eng., University of Maryland, College Park, MD 20742-2115*

⁴*Department of Physics, Boston College, Chestnut Hill, Massachusetts 02467, USA*

⁵*Department of Physics and Astronomy, McMaster University, Hamilton, ON L8S 4M1, Canada*

⁶*Spallation Neutron Source, Second Target Station, Oak Ridge National Laboratory, Oak Ridge, TN, 37831, USA*

⁷*Neutron Scattering Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA*

⁸*Canadian Institute for Advanced Research, 661 University Avenue, Toronto, Ontario M5G 1M1, Canada.*

⁹*Brockhouse Institute for Materials Research, Hamilton, ON L8S 4M1 Canada*

(Dated: January 13, 2023)

The magnetism of the rock-salt *fcc* rare-earth monopnictide HoBi, a candidate topological material with extreme magnetoresistance, is investigated. From the Ho^{3+} non-Kramers $J=8$ spin-orbital multiplet, the cubic crystal electric field yields six nearly degenerate low-energy levels. These constitute an anisotropic magnetic moment with a Jahn-Teller-like coupling to the lattice. In the cubic phase for $T > T_N = 5.72(1)$ K, the paramagnetic neutron scattering is centered at $\mathbf{k} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$ and was fit to dominant antiferromagnetic interactions between Ho spins separated by $\{100\}$ and ferromagnetic interactions between spins displaced by $\{\frac{1}{2}\frac{1}{2}0\}$. For $T < T_N$, a type-II AFM long-range order with $\mathbf{k} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$ develops along with a tetragonal lattice distortion. While neutron diffraction from a multi-domain sample cannot unambiguously determine the spin orientation within a domain, the bulk magnetization, structural distortion, and our measurements of the magnetic excitations all show the easy axis coincides with the tetragonal axis. The weakly dispersive excitons for $T < T_N$ can be accounted for by a spin Hamiltonian that includes the crystal electric field and exchange interactions within the Random Phase Approximation.

I. INTRODUCTION

In spite of their structural simplicity, the *fcc* rare-earth monopnictides (see Fig. 1), RX (R=Ce to Yb and X=N, As, P, Sb, and Bi^{1,2}), display a wide variety of anisotropic magnetism and electronic transport properties. The lattice parameter varies by 30% across the pnictide series and this provides opportunities to tune the relative strength of crystal field and exchange interactions. In the 1960s to 1980s, the rare-earth monopnictides were studied to understand magnetic phases driven by oscillatory and highly anisotropic Ruderman-Kittel-Kasuya-Yosida (RKKY) exchange interactions³⁻⁸. Work on CeSb for example gave rise to an extensive literature on the anisotropic nearest and next nearest neighbor Ising model (ANNNI)⁹. This work also resulted in progress towards a quantitative understanding of their anisotropic exchange interactions¹⁰.

A recent resurgence of interest in these rare-earth monopnictides is driven by their extreme magnetoresistance (XMR) and resistivity plateaus, and the possible connection to the 3D topological state of the non-magnetic lanthanum monopnictides LaX^{11,12}. LaAs, LaSb, and LaBi have unsaturated XMR arising from near perfect electron-hole compensation and there is a topological transition from a trivial electronic band structure in LaAs to a topologically non-trivial band structure in LaBi¹³⁻¹⁷. Several studies have confirmed the presence of protected surface states in LaBi¹⁸⁻²¹. Since then, extensive works have been devoted to characterizing the XMR and topological states of various RX including for example CeX, HoX, and PrX. XMR has been found in each reported

magnetic RX with characteristics that depend on the rare-earth ion²²⁻³⁰. The stabilization of topological non-trivial electronic bands generating protected surface states was proposed for several of the magnetic monopnictides^{29,31-33}.

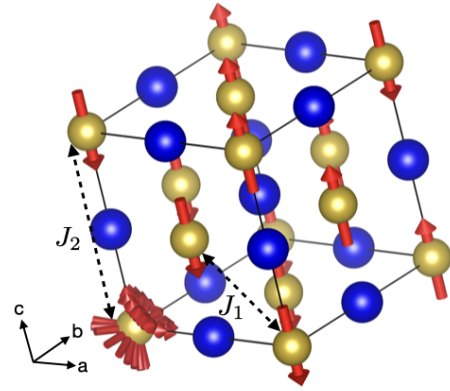


FIG. 1. The rock-salt structure of the rare-earth monopnictide HoBi. Yellow and blue spheres respectively correspond to Ho and Bi. Spins interacting through the J_1 and J_2 exchange interaction are shown by the dashed black arrows. The $\mathbf{k} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$ magnetic order of the Ho^{3+} spins is represented by the red arrows. The local spin orientations of the Ho^{3+} spins that are consistent with neutron diffraction are indicated for the Ho ion at $(0,0,0)$. The magnetization, structural distortion, and inelastic neutron scattering however, provide clear evidence for easy $[001]$ axis anisotropy.

Here we study the magnetism of HoBi using modern neutron scattering techniques to gain insights into its unique magneto-transport properties^{29,34}. Consistent with previous works^{35–37}, we confirm the antiferromagnetic (AFM) $\mathbf{k} = (\frac{1}{2} \frac{1}{2} \frac{1}{2})$ structure and the associated tetragonal lattice distortion. Due to multi-domain averaging, our single-crystal neutron diffraction cannot unambiguously determine the local spin anisotropy of the $\mathbf{k} = (\frac{1}{2} \frac{1}{2} \frac{1}{2})$ AFM structure. However, we could resolve this ambiguity by measuring and modeling the magnetic excitations of HoBi, which take the form of weakly propagating spin-orbital excitons whose energies and intensities are sensitive to the local orientation of the Ho³⁺ moments. Using this method, we found the $\mathbf{k} = (\frac{1}{2} \frac{1}{2} \frac{1}{2})$ AFM structure has an Ising local spin anisotropy, which is consistent with the Ising easy-axis bulk magnetization and the tetragonal distortion. Through analysis of the paramagnetic diffuse scattering of HoBi and the crystal field excitons in the low T ordered state, we obtain a spin Hamiltonian with comparable crystal field (CEF) and exchange energy scales.

II. EXPERIMENTAL METHODS

HoBi single crystals with mass of 10-50 mg were grown following a previously published procedure³⁴. Single crystal low-temperature X-ray diffraction was performed using a Huber four-circle diffractometer with a Rigaku Rotaflex 18 kW rotating copper anode X-ray generator and a Bicon point detector. We used a Ge (111) monochromator with $d_{111} = 3.266 \text{ \AA}$. The sample was aligned for diffraction in the (HHL) plane and mounted in a closed cycle cryogenic system with a base temperature of 2.17 K.

We performed thermal neutron diffraction using the HB-1A triple-axis instrument at Oak Ridge National Laboratory. We used PG filtered 14.5 meV neutrons, and collected rocking scans at all accessible magnetic and nuclear Bragg positions in the (HHL) plane. Polarized neutron diffraction measurements were conducted with the triple-axis instrument BT-7 at the Center for Neutron Research (NCNR), NIST. Nuclear spin-polarized ³He gas was used to polarize the incident neutron beam and to analyze the polarization of scattered neutrons^{38,39}. Horizontal guide fields were present throughout the beam path to allow measurements of the spin-flip (SF) and non-spin-flip (NSF) scattering cross-sections for incident neutron spins polarized parallel to momentum transfer \mathbf{Q} . The flipping ratio measured at nuclear Bragg peaks was greater than 30.

Cold neutron triple-axis experiments were performed using the SPINS and the MACS spectrometers at the NCNR. On both instruments we employed a fixed final neutron energy $E_f = 3.7 \text{ meV}$ or 5 meV and measured the elastic and inelastic scattering for a single crystal of HoBi aligned for scattering within the (HHL) and the (HK0) plane in two different experiments. For the $E_f = 3.7 \text{ meV}$ configuration, we used polycrystalline cooled Be and BeO filters before and after the sample, respectively. For the 5 meV configuration we only used a Be filter after the sample while the incident beam from the cold neutron source was unfiltered. For both experiments, we

co-mounted 11 HoBi single crystals on an aluminum mount. We acquired background data using an identical mount without HoBi crystals. We used an "orange" 4He flow cryostat to reach a base temperature of 1.6 K for these experiments.

For the highest energy resolution and energy transfer, we performed time-of-flight neutron scattering experiments using the CNCS spectrometer at Oak Ridge National Laboratory. There we co-aligned two HoBi single crystals on an aluminum mount and collected inelastic neutron scattering data with fixed incident energy $E_i = 25 \text{ meV}$ at $T = 13 \text{ K}$ with a total proton charge of 47 C. We used the high flux mode of operation of CNCS with a Fermi Chopper, Chopper 2, Chopper 3, and a Double Disk frequency of 60, 60, 60, 300, and 300 Hz respectively. The energy resolution (FWHM) at the elastic line for this configuration is 2.0(1) meV. Finally, we note that the error bars associated with the neutron scattering experiments represent one standard deviation.

Both the magnetization and heat capacity measurements presented here were performed in a Quantum Design physical properties measurement system (PPMS). We used a PPMS dilution refrigerator option for the low-temperature heat capacity.

III. RESULTS AND ANALYSIS

A. 1st order phase transition

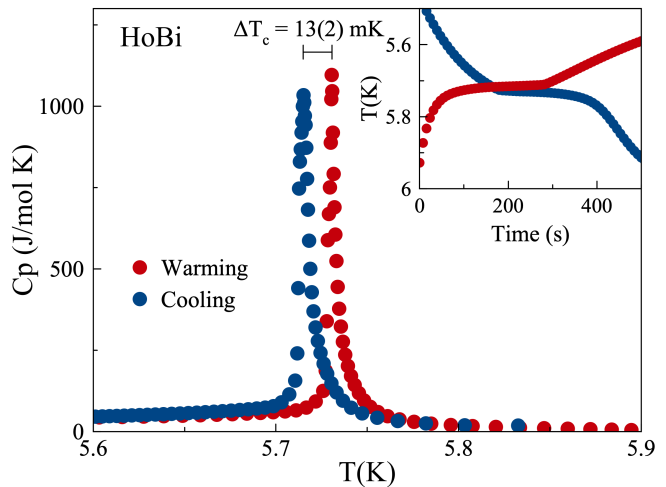


FIG. 2. Low temperature heat capacity of HoBi collected using the long-pulse method. The red and blue curves respectively correspond to the warming and cooling protocol and shows a thermal hysteresis of 13(2) mK. The observation of a plateau at T_N in the heating profile for both warming and cooling protocol (top inset panel) suggests a 1st order phase transition in HoBi.

The thermodynamic properties of HoBi were previously reported and a long-range $\mathbf{k} = (\frac{1}{2} \frac{1}{2} \frac{1}{2})$ antiferromagnetic (AFM) order is known to occur concomitantly with a structural distortion around $T_N = 5.7 \text{ K}$ ^{14,35,36}. The order of the transition, however, remains unknown. To determine the

order of the phase transition, we measured the temperature dependent specific heat capacity using the long-pulse heat method⁴⁰. The resulting C_p data for HoBi is reported in Fig. 2 for both warming and cooling protocols. A sharp peak with a thermal hysteresis of 13(2) mK is observed in C_p . Correspondingly the inset shows a distinct plateau in the temperature versus time curves during heating and cooling. These observations indicate a 1st order phase transition at T_N in HoBi.

B. Paramagnetic phase

To determine the magnetic interactions leading to this phase transition, we mapped the neutron elastic scattering for momentum transfer \mathbf{Q} covering the (HHL) plane and for temperatures between 150 K and 1.6 K. Representative data sets are shown in Fig. 3.

In the cubic paramagnetic phase for $T = 12 \text{ K} > T_N = 5.72(1) \text{ K}$, the scattering is broad in \mathbf{Q} and is centered at $\mathbf{k} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$ positions (Fig. 3(a)). This indicates short-range AFM correlations preceding the long-range order. The "butterfly" pattern of paramagnetic diffuse scattering is consistent with the equal time structure factor $S(\mathbf{Q})$ of an *fcc* Heisenberg paramagnet with FM interactions between the first nearest-neighbor (n.n.) Ho^{3+} ions (J_1), and AFM interactions between the 2nd n.n. (J_2). Dashed lines in Fig. 1 indicate the lattice geometry associated with these interactions. The scattered intensity was modeled using $I(\mathbf{Q}) = \frac{2}{3}N|f(\mathbf{Q})|^2 \sum_{ij} \langle \mathbf{S}_i \cdot \mathbf{S}_j \rangle \cos(\mathbf{Q} \cdot \mathbf{r}_{ij})$ where N is the number of spins, \mathbf{r}_{ij} is the displacement vector from Ho^{3+} site j to i , and $f(\mathbf{Q})$ is the Ho^{3+} atomic form factor⁴¹. Including only self-correlations and correlations between spins separated by $\{100\}$ and $\{\frac{1}{2}\frac{1}{2}0\}$, a ratio of $\langle \mathbf{S}_i \cdot \mathbf{S}_j \rangle_{\{100\}} / \langle \mathbf{S}_i \cdot \mathbf{S}_j \rangle_{\{\frac{1}{2}\frac{1}{2}0\}} = -2.2(2)$ was obtained at $T = 12 \text{ K}$. The calculated paramagnetic diffuse scattering corresponding to the best fit shown in Fig. 3(d) accounts for all major features in the data (Fig. 3(a)) and the introduction of third n.n. correlations does not improve the fit significantly. A high temperature expansion allows us to associate the ratio of correlations to the ratio of the corresponding exchange interactions^{42,43} so that we may infer that $J_2/J_1 \approx -2.2(2)$. Even if some of the J_1 bond interactions are frustrated, this resulting fitted ratio of exchange parameters stabilize a $\mathbf{k} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$ order, which is driven by the dominant AFM J_2 interactions⁴⁴⁻⁴⁶.

Upon cooling, the elastic magnetic scattering gets stronger ($T = 5.5 \text{ K} \approx T_N$ in Fig. 3(b)) and eventually forms magnetic Bragg peaks ($T = 1.6 \text{ K} \ll T_N$ in Fig. 3(c)) indicating long range magnetic order. To quantify the temperature dependence of the diffuse and Bragg scattering, as shown in Fig. 3(e), we fitted the integrated intensity obtained from one-dimensional (HHH) scans acquired through the magnetic Bragg peak at $\mathbf{Q} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$. Each scan was fit to the sum of a Gaussian function and a Lorentzian function to describe the long and short range components of the spin correlations, and a linear background (needed to describe the temperature independent nuclear and temperature-dependent magnetic inco-

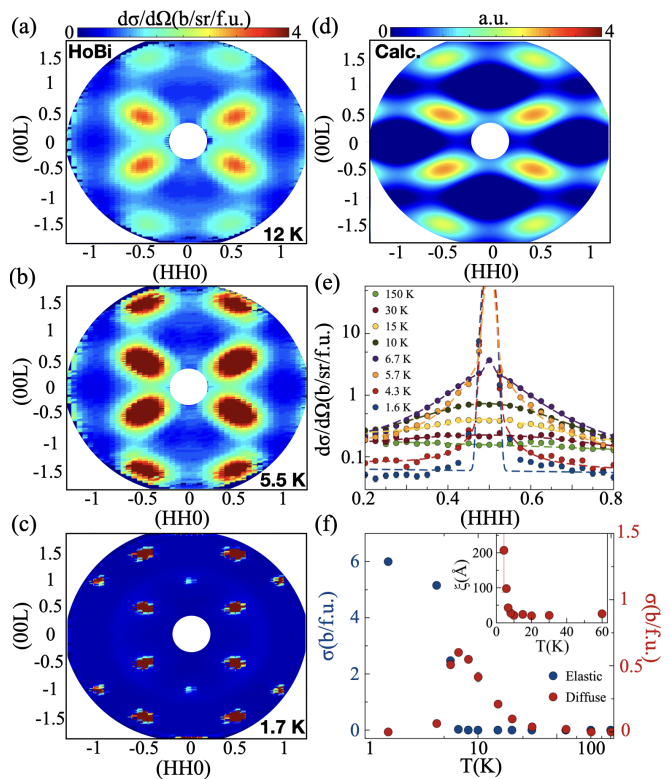


FIG. 3. The elastic diffuse neutron scattering from HoBi measured in the (HHL) reciprocal lattice plane at (a) 12 K, (b) 5.5 K, and (c) 1.7 K with an incident neutrons energy of 3.7 meV. The scattering for panels (a,b,c) have been symmetrized to increase statistics. (d) Calculated paramagnetic diffuse scattering with $J_1/J_2 = -2.17$ on an *fcc* lattice where J_1 is the first n.n. ferromagnetic interaction and J_2 is the 2nd n.n. antiferromagnetic interaction. Panel (e) is the elastic neutron scattering near the $\mathbf{Q} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$ Bragg peak acquired through scans along the the (HHH) direction. The data in panel (e) were fitted using a Lorentzian function for the diffuse scattering and a Gaussian function for the resolution limited Bragg component. The inferred integrated intensity for each component of the scattering are plotted in panel (f) as a function of temperature. The temperature dependence of the magnetic correlation length is plotted in the inset panel of (f).

herent elastic scattering). The fits included as dashed curves in Fig. 3(e) provide a good account of the data.

The temperature dependence of the integrated intensity of both the Bragg and the diffuse components of the scattering are reported in Fig. 3(f). The integrated intensity of the diffuse scattering (red markers) is peaked at T_N where the appearance of Bragg scattering (blue markers) reveals the onset of long range order and translation symmetry breaking. The temperature variation of the correlation length ξ , as inferred from the Lorentzian after correcting for resolution effects, is reported in the inset of Fig. 3(f). As expected, ξ increases dramatically at T_N .

C. Structural distortion

A previous X-ray diffraction study revealed that a tetragonal distortion accompanies magnetic ordering in HoBi³⁵. We confirmed the occurrence of this distortion in HoBi with a four-circle X-ray diffractometer experiment. The θ - 2θ scans of various nuclear Bragg peaks were collected above and below T_N with a base temperature of 5 K. Consistent with previous work³⁵, we observed a splitting of the ($H00$), ($0K0$), and ($00L$) nuclear Bragg peaks whereas the (HHH) Bragg peaks do not split. This indicates a tetragonal distortion and specifically precludes a rhombohedral distortion.

The temperature dependence of a longitudinal θ - 2θ scan through the $\mathbf{Q} = (006)$ peak is plotted in Fig. 4(a). This is an unfiltered copper source with K_{α_1} and K_{α_2} radiation. Both components yield a split (006) peak below T_N . The distortion was quantified by fitting the θ - 2θ scans to Lorentzian functions while constraining the ratio of the $K_{\alpha_1} / K_{\alpha_2}$ integrated intensity to be temperature independent and set by its fitted value obtained at high temperatures. Examples of these fits are included in Fig. 4(a). The temperature dependent lattice parameters inferred from this analysis are shown in Fig. 4(b). The order parameter-like temperature dependence is similar for both warming and cooling with no hysteresis detected down to the 100 mK temperature scale. For comparison the hysteresis detected through heat capacity measurements was 13 mK (Fig. 2). A single (006) Bragg peak with a lattice parameter of 6.2095(1) Å above T_N , splits into two peaks with lattice parameters 6.2143(1) Å and 6.2075(1) Å below T_N . Assuming an approximately volume conserving phase transition implies that the lattice parameter that changes most is the c -axis. This indicates the structural unit cell elongates along the c -axis in the AFM state with $c/a = 1.0011(1)$ at 5 K. We note that an orthorhombic distortion with the a and b axis differing by less than 0.002 Å is not excluded by these data.

A possible space group for HoBi below T_N is the maximal tetragonal subgroup of the paramagnetic space group $Fm\bar{3}m$, which is $I4/mmm$. The structural parameters in the tetragonal phase are $a_T = b_T = 6.2075(1)/\sqrt{2}$ Å and $c_T = 6.2143(1)$ Å where the \mathbf{a}_T and \mathbf{b}_T axes are rotated by 45° relative to the \mathbf{a} and \mathbf{b} axes of the paramagnetic simple cubic cell. In this space group Ho³⁺ ions occupy a single $2a$ Wyckoff site and the magnetic ordering vector is $\mathbf{k} = (\frac{3}{2}0\frac{3}{2})$. While we must use the tetragonal space group below T_N , we continue to use the cubic unit cell to index wave vector transfer in the neutron scattering experiments, which do not resolve the multi-domain tetragonal distortion.

D. Spin structure

As described in the previous sections, the magnetic order has a characteristic wavevector $\mathbf{k} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$. In addition to the corresponding low T magnetic Bragg peaks, the intensities of all nuclear Bragg peaks are observed to increase below T_N . The increase of intensity is approximately proportional to the intensity in the paramagnetic phase, which indicates it arises from secondary extinction release⁴⁷. To check this hypothesis,

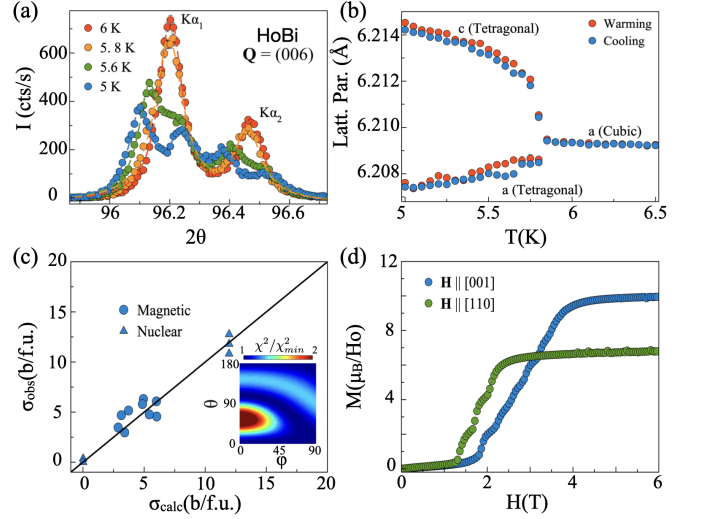


FIG. 4. A series of θ - 2θ X-ray diffraction scans through the $\mathbf{Q} = (006)$ Bragg peak. The inferred temperature dependence of the lattice parameters is shown in panel (b). The neutron magnetic and nuclear refinement of HoBi are presented in (c) where the observed cross-sections for various Bragg peaks are plotted as a function of the calculated cross-sections. The inset in (c) reports the variation of the χ^2 goodness of fit for the magnetic refinement of HoBi assuming a multi-domain $\mathbf{k} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$ spin structure with an easy axis defined by spherical coordinates θ and ϕ ($\phi = 0$ corresponds to the [110] direction). Panel (d) shows the low-temperature magnetization versus field for fields applied parallel to the [001] and [110] directions. The data show that [001] is the easy axis.

we performed polarized neutron diffraction on the (002) and (220) Bragg peaks below T_N and found them to be exclusively nuclear in origin.

We note that weak $\mathbf{k} = (001)$ Bragg peaks also onset at T_N . Examples of these peaks include the (001) and (111) Bragg peaks (see Fig. 3(c)), which are forbidden within the $Fm\bar{3}m$ space group. These Bragg peaks are attributed to multiple magnetic scattering as their presence depends on both the employed incident neutron wavelength and the scattering plane, and they are absent in powder neutron diffraction measurements³⁶. The multiple scattering processes involve magnetic $\mathbf{k} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$ Bragg reflections so they occur only for $T < T_N$.

Referring to fcc close packing, the AFM $\mathbf{k} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$ spin structure can be described as an AFM stacking of FM triangular lattices. As the magnetic order and structural distortion in HoBi occur in a single 1st order phase transition, the direction of the spins in each FM sheet is not constrained by the usual Landau argument for second order phase transitions. To determine the local spin orientation of the Ho³⁺ ions, we collected 18 rocking scans at different magnetic Bragg positions for a sample presumed to be in an unbiased multi-domain state. The data were compared to a cubic domain average of the calculated magnetic Bragg diffraction for a general spin orientation within one domain given by spherical angles θ, ϕ and $\mathbf{k} = (\frac{1}{2}\frac{1}{2}\frac{1}{2})$. Here $\theta = 0$ corresponds to the tetragonal c -direction and $\theta = \pi/2$ and $\phi = 0$ corresponds to the [110] direction. Minimizing with respect to the moment size at each

point, the χ^2 measure of fit quality is shown versus θ and ϕ in the inset panel of Fig. 4(c). The manifold of states represented by the red arrows in Fig. 1 are indistinguishable by neutron diffraction. This degeneracy arises because the magnetic diffraction intensity for a multi-domain sample only depends on the smallest angle between the spin and a $\langle 111 \rangle$ axis. From our refinement, we find this angle is $47(10)^\circ$. This is experimentally indistinguishable from the angle between $[001]$ and $[111]$, which is 55° . This means the magnetic diffraction data are consistent with spins pointing along the $[001]$ directions, but also with many other directions including close to the $[110]$ direction.

Fortunately the spin anisotropy of the Ho^{3+} ions can be deduced from other pieces of information. First, the low-temperature magnetization of HoBi shown in Fig. 4(d) reveals the saturation magnetization is larger for fields along the $[001]$ direction than along $[110]$. Second, the structural distortion also occurs along the $[001]$ direction. Both of these measurements are consistent with spins oriented along the tetragonal c_T -axis in the AFM ordered state. Additionally, in Sec. III F we show that a $[001]$ easy axis anisotropy is needed to accurately model the inelastic neutron scattering spectrum below T_N . We thus conclude the spins in the AFM type II order of HoBi are oriented along the c_T direction, which is the direction of the structural elongation. The comparison between measured and calculated magnetic Bragg intensities is shown in Fig. 4(c). The corresponding spin structure is shown in Fig. 1. An ordered moment of $10.3(6) \mu_B$ was determined, which is experimentally indistinguishable from the $gJ\mu_B = \frac{5}{4} \cdot 8 \mu_B = 10 \mu_B$ saturation magnetization of Ho^{3+} .

E. Crystal electrical field interaction

For Ho^{3+} ions, the $J = 8$ spin-orbit ground state manifold is $(2J+1) = 17$ fold degenerate under full rotation symmetry. This degeneracy is, however, lifted by the symmetry breaking crystal electric fields (CEF). Using the Stevens operator formalism, the CEF Hamiltonian appropriate for Ho^{3+} in the high-temperature cubic phase of HoBi can be expressed as follows:

$$\hat{H}_{cef}^{cubic} = B_4(\hat{O}_4^0 + 5\hat{O}_4^4) + B_6(\hat{O}_6^0 - 21\hat{O}_6^4). \quad (1)$$

Here \hat{O}_n^m are Stevens operators⁴⁸ that can be written in terms of the spin-orbital angular momentum operators \hat{J}_+ , \hat{J}_- and \hat{J}_z where $\hat{\mathbf{z}} \parallel \mathbf{c}$. The CEF parameters B_n are scalars of dimension energy that dictate the strength of the different CEF terms and can be determined by fitting spectroscopic or thermomagnetic data sensitive to the crystal field level scheme. B_n can also be estimated through the point-charge model⁴⁹.

Following Hutchings's formalism⁴⁹ the point charge model yields

$$B_4 = \frac{7|e||q_{Bi}|\beta_J\langle r^4 \rangle}{64\pi\epsilon_0 d_{Bi}^5} \quad (2)$$

and

$$B_6 = \frac{3|e||q_{Bi}|\gamma_J\langle r^6 \rangle}{256\pi\epsilon_0 d_{Bi}^7}. \quad (3)$$

Here e is the electron charge, q_{Bi} is the charge of the Bi ligand and ϵ_0 is the vacuum permittivity. β_J and γ_J are reduced matrix elements calculated in ref⁴⁸ whereas the radial integrals for the $4f$ state $\langle r^n \rangle$ are tabulated in ref⁵⁰. We used $q_{Bi} = -3e$ and the distance between a holmium ion and its first n.n. bismuth ion $d_{Bi} = a/2 = 6.2093(1)/2 \text{ \AA}$. Introducing these values in Eqs. 2 and 3 we obtain $B_4 = -2.2709(2) \times 10^{-4} \text{ meV}$ and $B_6 = -1.0468(1) \times 10^{-7} \text{ meV}$.

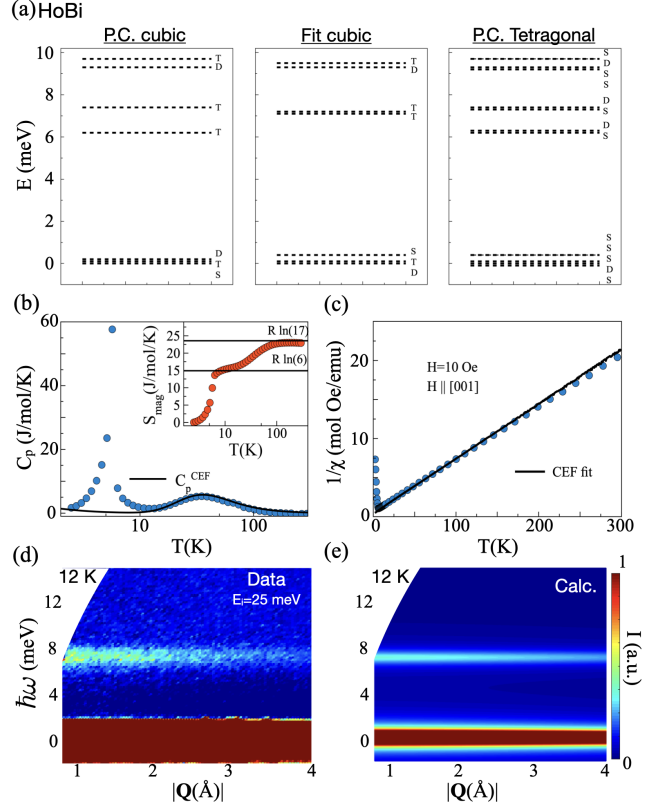


FIG. 5. Determination of the crystal electric field (CEF) level scheme for the $J=8$ Ho^{3+} ion in HoBi. (a) shows the results of a point charge (PC) calculation for the cubic and tetragonal phases. The cubic CEF scheme may be compared to the level scheme for the fitted CEF Hamiltonian of HoBi. Panel (b) and (c) respectively show the temperature dependence of the magnetic heat capacity (C_p) and the inverse magnetic susceptibility of HoBi compared to corresponding properties based on the fitted CEF Hamiltonian. The magnetic entropy obtained from integrating the C_p of HoBi is shown in the inset of (b). The measured (d) and calculated (e) inelastic neutron scattering spectra of HoBi are shown for $T = 12 \text{ K}$. The neutron inelastic scattering data were acquired using a 25 meV incident neutron beam.

The corresponding CEF level scheme for Ho^{3+} in the cubic phase of HoBi is shown in Fig. 5(a). The Ho^{3+} J -multiplet is split into 4 triplets, 2 doublets, and 1 singlet that form three groups. Group I includes one doublet, one triplet, and one singlet between 0 and 0.2 meV. Group II is formed by two

triplets between 6 meV and 7 meV, and group III consists of a doublet and a triplet between 9 meV and 10 meV.

The CEF Hamiltonian estimated from our point-charge calculation can reproduce the temperature dependence of the magnetic heat capacity C_p (Fig. 5(b)) and magnetic susceptibility χ (Fig. 5(c)). Obtained by integrating C_p/T , the temperature dependence of the entropy shown in the inset of Fig. 5(b) is informative. A first entropy plateau near 10 K is associated with the sharp C_p anomaly at the phase transition to long range magnetic order. The corresponding change in entropy of $\Delta S = R \ln 6$ is that associated with the group I CEF states. The second plateau at $S = R \ln 17$ is reached at room temperature and encompasses all of the entropy associated with the three groups of crystal field levels.

For a more stringent test of the point charge model, we turn to inelastic neutron scattering. Fig. 5(d) shows the 12 K inelastic neutron scattering spectrum with energy transfer ranging from 0 to 15 meV. At this temperature, the group II and III of CEF states are so scarcely populated that only CEF excitations originating from group I should be visible. No significant intrinsic broadening of the CEF excitations is observed and we note, also, that the experimental resolution is too coarse to resolve CEF levels within a group. The magnetic neutron scattering cross section associated with CEF transition from group I to II and from group I to III can be computed based on the point charge CEF Hamiltonian ($I_{mn} \propto \sum_i | \langle m | J_i | n \rangle |^2$). This calculation predicts the cross section for transitions from group I to group II is 250 times stronger than for transitions from group I to group III. The intensity of the transition from I to III is thus predicted to be too weak to be detected. This explains why Fig. 5(d) shows just a single peak that we associate with transitions from group I to group II crystal field levels.

While the measured 7.2 meV gap between group I and group II CEF levels is just 0.4 meV off from the point charge prediction of 6.8 meV, we can improve our estimate of the CEF Hamiltonian by simultaneously fitting B_4 and B_6 for the best possible account of the neutron scattering spectra (Fig. 5(d)), the specific heat data (Fig. 5(b)), and the magnetic susceptibility data (Fig. 5(c)). The best fit parameters thus obtained are $B_4 = -2.24(1) \times 10^{-4}$ meV and $B_6 = -2.4(1) \times 10^{-7}$ meV and with them the CEF Hamiltonian provides an excellent account of all single ion properties that we've measured, as shown in Fig. 5.

The CEF scheme obtained from our fit (Fig. 5(a)) is remarkably similar to the point-charge calculation. Also a re-scaling of our CEF Hamiltonian for HoBi using Eq. 2 and Eq. 3 considering only the different ligand spacing successfully predicts the level scheme for HoN ref⁵¹. This is in contrast with the praseodymium case where a pnictide ligand charge of $q = -2e$ is needed to bring the point charge model into agreement with experimental data⁵. This indicates that holmium monopnictides are more ionic than praseodymium monopnictides.

Finally, we estimated the effect of the tetragonal distortion on the CEF interaction in HoBi. We performed a point-charge calculation assuming that the first n.n. Ho-Bi bond is shorter along the **a** and **b** direction (d_a) as compared to the **c** direction (d_c). The calculated CEF Hamiltonian can be written as:

$$\begin{aligned} \mathcal{H}_{cef}^{tet} = & \frac{|e||q_{Bi}|}{4\pi\epsilon_0} [\alpha_J \langle r^2 \rangle \left(\frac{1}{d_c^3} - \frac{1}{d_a^3} \right) \hat{O}_2^0 + \\ & \beta_J \langle r^4 \rangle \left(\frac{1}{4d_c^5} + \frac{3}{16d_a^5} \right) \hat{O}_4^0 + \frac{35}{16d_a^5} \hat{O}_4^4 + \\ & \gamma_J \langle r^6 \rangle \left(\frac{1}{8d_c^7} - \frac{5}{64d_a^7} \right) \hat{O}_6^0 - \frac{63}{64d_a^7} \hat{O}_6^4]. \end{aligned} \quad (4)$$

The corresponding level scheme is shown in Fig. 5(a). For this calculation, we used the lattice parameters determined in our high-resolution X-ray scattering experiment. The degeneracy of all the triplets and doublets associated with cubic symmetry is lifted. This results in four doublets and nine singlets and a significant broadening of each of the three groups of crystal field levels.

F. Low energy spin dynamics

We now turn our attention to the collective physics of HoBi, which we explore using inelastic magnetic neutron scattering. Fig. 6(a) shows the temperature dependence of the inelastic scattering for $\mathbf{Q} = (\frac{1}{2}, \frac{1}{2}, \frac{1}{2})$. Just above T_N , the scattering is quasi-elastic with a physical (resolution corrected) FWHM of 0.30(5) meV. No inelastic intensity is observed up to 2 meV. This is consistent with the CEF energy scheme shown in Fig. 5(c). Below T_N , the quasi-elastic scattering splits into an elastic and an inelastic component.

To probe any dispersion of the low energy spin excitations, we acquired low energy spectra at momentum transfer \mathbf{Q} corresponding to high symmetry points in the Brillouin zone. Fig. 6(b) shows the spectrum consists of a peak that is broader than the experimental resolution (FWHM indicated by horizontal bar) and that shifts by less than the peak width between the different values of \mathbf{Q} . A gaussian fit finds the peak centered at 1.7(2) meV with a FWHM of 0.48(4) meV that exceeds the instrumental resolution (FWHM of 0.22 meV). The limited resolution and statistical accuracy of the data does not rule out the possibility of multiple dispersive components within the approximately Gaussian envelope of the peak.

We also examined the higher energy excitations for $T < T_N$ by acquiring momentum resolved inelastic scattering data up to 11.5 meV. A representative slice through the data is displayed as a color image versus \mathbf{Q} along the (HH0) direction and energy transfer in Fig. 6(c). No dispersion is resolved. The data are similar to the high-temperature plot of intensity versus $|Q|$ and $\hbar\omega$ in Fig. 5(d) though with additional inelastic features at 9.0(3) meV and 1.7(2) meV.

Fig. 6(e) shows the momentum dependence of the integrated intensity of the 1.7 meV mode throughout the (HHL) zone. The \mathbf{Q} dependence of the intensity is subtle albeit peaked at the magnetic $(\frac{1}{2}, \frac{1}{2}, \frac{1}{2})$ zone center and smoothly decreases with $|Q|$ in accordance with the Ho^{3+} magnetic form factor⁴¹. We note that the 1.7 meV gap is about an order of magnitude greater than the predicted CEF gap arising from the tetragonal distortion. This indicates the phase transition is driven by the magnetic interactions, which we model below.

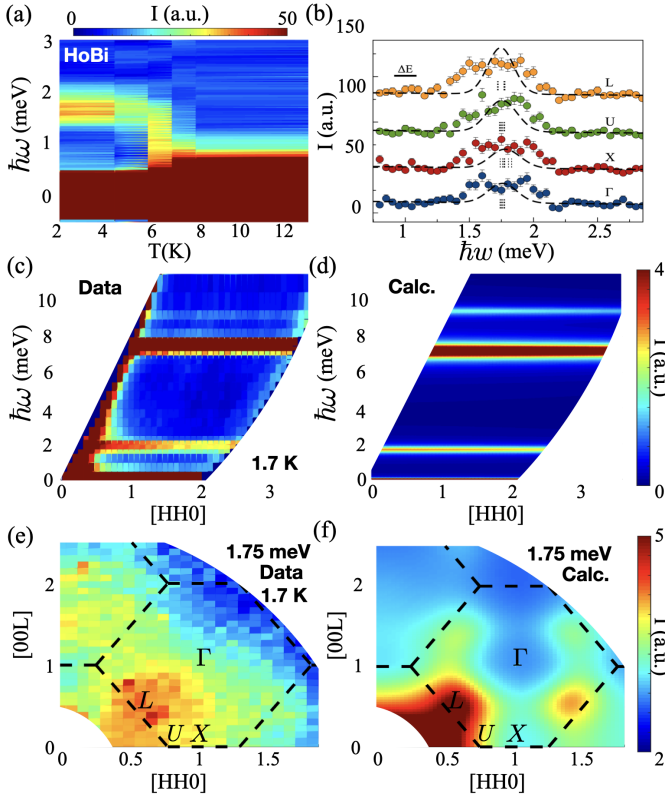


FIG. 6. The temperature dependence of the low energy inelastic neutron spectrum of HoBi at $\mathbf{Q} = (\frac{1}{2} \frac{1}{2} \frac{1}{2})$ is shown in panel (a). The spectrum of neutron scattering at some high symmetry positions within the first Brillouin zone of HoBi are shown in (b). The horizontal black bar indicates the FWHM energy resolution of the spectrometer while the black dashed lines show the predicted spectrum based on the spin Hamiltonian presented in this work. The energies associated with each exciton are indicated by vertical black dashed lines. The observed and calculated inelastic neutron scattering spectrum up to 11.5 meV are respectively plotted in (c) and (d) for momentum transfer \mathbf{Q} along the [HH0] direction. The observed and calculated momentum dependence of the 1.75 meV exciton scattering intensity is shown in (e) and (f). The energy integration for panel (e) is ± 0.25 meV.

IV. MODELING SPIN DYNAMICS OF SPIN-ORBITAL EXCITONS

The low-temperature excitations in HoBi are similar to other rare-earth metallic compounds where exchange interactions are strong enough to mix crystal field levels^{4,52,53}. Because components that are longitudinal with respect to the ordered moment are involved, these are not conventional transverse spin wave excitations. They may be described as crystal field excitations that can propagate through the lattice due to inter-site interactions. We shall adopt the practice of calling these “crystal field exciton” or simply “exciton”^{54–56}.

A common theoretical approach to describing excitons in rare-earth magnets is to use a pseudo-boson theory where the exciton creation operator is a linear combination of single-ion operators^{53,57,58}. In this theory, the $\mathbf{Q} = \mathbf{0}$ single-ion opera-

tors are obtained by diagonalizing the mean-field spin Hamiltonian and the dispersion at finite \mathbf{Q} is produced by the exchange terms. We use this pseudo-boson theory to describe the magnetic excitation spectrum of HoBi below T_N . The Hamiltonian \mathcal{H}_s includes the single-ion tetragonal crystal field terms and isotropic exchange interactions. \mathcal{H}_s is decomposed into a mean-field term ($\mathcal{H}_{0,k}$) and an interacting part (\mathcal{H}_{int}) so $\mathcal{H}_s = \sum_k \mathcal{H}_{0,k} + \mathcal{H}_{int}$ where:

$$\mathcal{H}_{0,k} = \mathcal{H}_{cef,k}^{tet} + (-1)^k H_z J_{jz}^k \quad (5)$$

and

$$\mathcal{H}_{int} = \sum_{j,j',k,k'} \mathcal{J}_{j,j'}^{k,k'} \mathbf{J}_j^k \cdot \mathbf{J}_{j'}^{k'} - \sum_{j,k} (-1)^k H_z J_{jz}^k. \quad (6)$$

Here j indexes the unit cell while $k = 1, 2$ specifies the anti-parallel sub-lattices of the AFM order (Fig. 1). We define $H_z = 2 \sum_r Z_r \mathcal{J}_r \langle J_z \rangle$ where \mathcal{J}_r and Z_r are respectively the exchange constant and coordination number associated with the r^{th} neighbor. $\langle J_z \rangle$ is the thermal average of J_z on each site, which we found to be $\langle J_z \rangle = 8$ in our diffraction and CEF analysis. By definition, \mathcal{H}_{int} carries no mean value and so can be written in terms of creation ($\hat{a}_{n,k}^\dagger = |n, k\rangle\langle 0, k|$) and annihilation ($\hat{a}_{n,k} = |0, k\rangle\langle n, k|$) operators that connect the ground state $|0, k\rangle$ and the excited eigenstates $|n, k\rangle$ of $\hat{H}_{0,k}$. In this case, $\hat{H}_{0,k} = \sum_n E_n \hat{a}_{n,k}^\dagger \hat{a}_{n,k}$ where $E_{n,k}$ is the eigenvalue of the $|n, k\rangle$ eigenstate of $\hat{H}_{0,k}$. After writing \hat{H}_s in terms of these operators and Fourier transforming it, we obtain:

$$\hat{H}_s = \frac{1}{2} \sum_{\mathbf{Q}} \left\{ \hat{a}^\dagger(\mathbf{Q}) A(\mathbf{Q}) \hat{a}(\mathbf{Q}) + \hat{a}^\dagger(-\mathbf{Q}) A(-\mathbf{Q}) \hat{a}(-\mathbf{Q}) \right. \\ \left. + \hat{a}^\dagger(\mathbf{Q}) B(\mathbf{Q}) \hat{a}^\dagger(-\mathbf{Q}) + \hat{a}(-\mathbf{Q}) B(\mathbf{Q}) \hat{a}(-\mathbf{Q}) \right\} \quad (7)$$

with $\hat{A} = \hat{\Delta} + 2\hat{h}_{zz} + \hat{h}_{+-} + \hat{h}_{-+}$ and $\hat{B} = 2\hat{h}_{zz} + \hat{h}_{++} + \hat{h}_{--}$ where $\hat{\Delta} = E_{n,k} \delta_{k,k'} \delta_{n,n'}$ and $\hat{h}_{\alpha\beta}(k, k', n, n', \mathbf{Q}) = J(\mathbf{Q}) \langle k, n | \hat{J}_\alpha | 0, k \rangle \langle k', 0 | \hat{J}_\beta | n', k' \rangle$.

The procedure to compute the spin dynamics first consist of diagonalizing $\hat{H}_{0,k}$ to obtain the eigenvalues $E_{n,k}$ and eigenvectors $|n, k\rangle$ for $\mathbf{Q} = \mathbf{0}$. At finite \mathbf{Q} , the matrix $\hat{H}_s = \begin{pmatrix} \hat{A} & \hat{B} \\ -\hat{B} & -\hat{A} \end{pmatrix}$ is then computed and diagonalized to obtain the perturbed energies ($E_{\tilde{n}}(\mathbf{Q})$) and eigenstates $|\tilde{n}(\mathbf{Q})\rangle$ for each exciton. We consider all the excited CEF states belonging to the $(2J+1)$ spin-orbit manifold of HoBi so there are 32 creation and annihilation operators for each of the 2 Ho³⁺ spins within the magnetic unit cell. This give a Hilbert space of 64 states for \hat{H}_s . The associated inelastic magnetic neutron scattering cross-section for a single magnetic domain is then^{53,57}:

$$\frac{d^2\sigma}{dE d\Omega} = N(\gamma r_0)^2 \frac{k_f}{k_i} \left| \frac{g}{2} f(\mathbf{Q}) \right|^2 \\ \times \sum_{\tilde{n}, \mathbf{q}, \tau_{\mathbf{m}}} |\langle \tilde{n}(\mathbf{q}) | \hat{J}_{\mathbf{Q}} | GS \rangle|^2 \delta(E - E_{\tilde{n}}(\mathbf{q})) \Delta(\mathbf{Q} - \mathbf{q} - \tau_{\mathbf{m}}) \quad (8)$$

Here N is the number of primitive magnetic unit cells, $\gamma = -1.91$ is the gyromagnetic ratio of the neutron, $r_0 = 2.818 \times$

10^{-15} m is the classical electron radius, τ_m is the magnetic zone center, \mathbf{q} is the reduced momentum transfer within the first magnetic Brillouin zone, while k_f and k_i respectively are the scattered and incoming neutron wave vector. The measured spectrum is subject to the finite resolution of the instrument which we account for by replacing the delta functions by a united normalized Gaussian functions with the \mathbf{Q} -integrated energy resolution width. The final calculated spectrum was averaged over all possible magnetic domains.

V. MICROSCOPIC SPIN HAMILTONIAN FOR HOLMIUM BISMUTH

We determined the microscopic parameters of \hat{H}_s for HoBi by fitting the $\mathbf{Q} = \mathbf{0}$ spectrum consisting of three excitons at $E_1 = 1.7(2)$ meV, $E_2 = 7.4(2)$ meV and $E_3 = 9.0(3)$ meV with relative intensities $I_2/I_1 = 5.5(3)$ and $I_2/I_3 = 37(7)$. Employing the ratio $\|J_2/J_1\| = 2.17$ obtained by analyzing the magnetic diffuse scattering (section III B) leaves just one free parameter. The tetragonal CEF Hamiltonian has six free parameters that were initially estimated from the point-charge model. To reproduce the exact energies of the excitons at E_2 and E_3 , we allowed the CEF parameters to relax away from their point-charge values which results in many combinations of parameters consistent with the data. We estimated the exchange constants by varying the CEF parameters away from their point-charge calculation values and keeping all solutions that have a χ^2 within 20% ($1/N_{obs}$) of the global minimum. The exchange parameters refined to $J_1 = -1.4(2)$ μeV and $J_2 = 3.0(5)$ μeV . A mean-field critical temperature of 20(7) K is obtained from these parameters. For comparison, the actual ordering temperature is only $T_N = 5.72(1)$ K. We hypothesize that fluctuations arising from competition between the ferromagnetic J_1 and the antiferromagnetic J_2 interactions lead to the reduced critical temperature.

The right column of Fig. 6 compares the optimized model for a multi-domain sample to the experimental data. Fig. 6(d) shows the full intensity versus $\hbar\omega$ and $\mathbf{Q} \parallel (HH0)$ for comparison with Fig. 6(c). The position and relative intensity of the three modes are well reproduced. Looking more closely at the 1.75 meV mode, Fig. 6(b) compares the intensity versus energy transfer at select high symmetry points in the Brillouin zone. The vertical dashed lines show that multiple excitons contribute at each \mathbf{Q} . This is generally consistent with the featured spectrum observed though there is more broadening/dispersion observed than reproduced by the model. Inclusion of anisotropic or longer range interactions might be needed to remedy this discrepancy though data with higher energy resolution is needed to justify the greater model complexity. Fig. 6(f) shows the calculated \mathbf{Q} -dependent integrated intensity of the 1.75 meV mode. The dominant features of the experimental result in Fig. 6(e) are reproduced, including mainly the increase of scattered intensity at the magnetic zone centers. We note the presence of phonon scattering near $\mathbf{Q} = (002)$ that may account for the discrepancy between the calculation and the experimental data at that momentum point.

VI. DISCUSSION AND CONCLUSION

In this manuscript, we have characterized an antiferromagnetic order and the associated crystal field excitons that develop below $T_N = 5.72(1)$ K in the rare-earth monopnictide HoBi. This magnetic state is driven by strong 2nd n.n. antiferromagnetic and weaker 1st n.n. ferromagnetic interactions, which we quantified via modeling of the diffuse paramagnetic and low temperature inelastic neutron scattering. The excitation spectrum is sensitive to the local orientation of the Ho^{3+} ordered spins, which allowed us to establish the Ising nature of the antiferromagnetic order in HoBi that cannot be deduced from neutron diffraction of a multi-domain sample. We used X-ray diffraction to provide evidence for a tetragonal structural distortion that accompanies magnetic ordering. Our CEF analysis and modelling of inelastic scattering data indicates the elongated c -axis coincides with the easy magnetic axis within a domain.

The magnetic excitations that we have documented here surely have significant impacts on the magneto-transport properties of HoBi³⁴. For example, we found strong quasi-elastic neutron scattering in the paramagnetic state. The associated short range correlated spin fluctuations, which may be accompanied by short range tetragonal lattice distortions too given the non-Kramers nature of the Ho^{3+} , are expected to enhance the electrical resistivity above T_N . Below T_N , these gapless fluctuations are replaced by a coherent exciton at 1.7(2) meV and correspondingly the electrical resistivity is reduced by an order of magnitude upon cooling below T_N ³⁴. The field-dependence of spin-orbital excitons may be responsible for various features observed in the magnetoresistance of HoBi and more broadly in the rare-earth monopnictides²³⁻²⁹.

VII. ACKNOWLEDGEMENTS

This work was supported as part of the Institute for Quantum Matter, an Energy Frontier Research Center funded by the U.S. Department of Energy, Office of Science, Basic Energy Sciences Under Award No.DE-SC0019331. CB was further supported by the Gordon and Betty Moore foundation EPIQS program under GBMF9456. The work at Boston College was supported by the U.S. Department of Energy, Office of Basic Energy Sciences, Division of Physical Behavior of Materials under Award DE-SC0023124. This work was supported in part by the Natural Sciences and Engineering Research Council of Canada (NSERC). We acknowledge the support of the National Institute of Standards and Technology, U.S. Department of Commerce. Access to MACS was provided by the Center for High Resolution Neutron Scattering, a partnership between the National Institute of Standards and Technology and the National Science Foundation under Agreement No. DMR-1508249. The identification of any commercial product or trade name does not imply endorsement or recommendation by the National Institute of Standards and Technology.

A portion of this research used resources at the High Flux Iso-

tope Reactor, a DOE Office of Science User Facility operated by the Oak Ridge National Laboratory.

- * Correspondence email address: Jonathan.Gaudet@nist.gov
- ¹ C.-G. Duan, R. F. Sabirianov, W. N. Mei, P. A. Dowben, S. S. Jaswal, and E.Y. Tsymbal, “Electronic, magnetic and transport properties of rare-earth monopnictides,” *J. Condens. Matter Phys.* **19**, 315220 (2007).
 - ² L. Petit, R. Tyer, Z. Szotek, W.M. Temmerman, and A. Svane, “Rare earth monopnictides and monochalcogenides from first principles: towards an electronic phase diagram of strongly correlated materials,” *New J. Phys.* **12**, 113041 (2010).
 - ³ H. R. Child, M. K. Wilkinson, J. W. Cable, W. C. Koehler, and E. O. Wollan, “Neutron diffraction investigation of the magnetic properties of compounds of rare-earth metals with group V anions,” *Phys. Rev.* **131**, 922–931 (1963).
 - ⁴ K. C. Turberfield, L. Passell, R. J. Birgeneau, and E. Bucher, “Neutron crystal-field spectroscopy in rare-earth metallic compounds,” *J. Appl. Phys.* **42**, 1746–1754 (1971).
 - ⁵ R. J. Birgeneau, E. Bucher, J. P. Maita, L. Passell, and K. C. Turberfield, “Crystal fields and the effective-point-charge model in the rare-earth pnictides,” *Phys. Rev. B* **8**, 5345–5347 (1973).
 - ⁶ P. Schobinger-Papamantellos, A. Niggli, P. Fischer, E. Kaldis, and V. Hildebrandt, “Magnetic ordering of rare earth monochalcogenides. I. neutron diffraction investigation of CeS, NdS, NdSe, NdTe and TbSe,” *J. Solid State Phys.* **7**, 2023 (1974).
 - ⁷ P. Fischer, P. Schobinger-Papamantellos, E. Kaldis, and A. Ernst, “Magnetic ordering of rare earth monochalcogenides. II. Neutron diffraction investigation of terbium sulphide, telluride and holmium telluride,” *J. Phys. C: Solid State Phys* **10**, 3601 (1977).
 - ⁸ H. Heer, A. Furrer, W. Halg, and O. Vogt, “Neutron spectroscopy in the cerium monopnictides,” *J. Phys. C: Solid State Phys* **12**, 5207–5220 (1979).
 - ⁹ W. Selke, “The ANNNI model — Theoretical analysis and experimental application,” *Phys. Rep.* **170**, 213 – 264 (1988).
 - ¹⁰ Q.G. Sheng and B.R. Cooper, “Combined effect of hybridization and exchange coulomb interaction on magnetic ordering in correlated-*f*-electron cerium systems,” *Phys. Rev. B* **50**, 965–977 (1994).
 - ¹¹ F.F. Tafti, Q.D. Gibson, S.K. Kushwaha, N. Haldolaarachchige, and R.J. Cava, “Resistivity plateau and extreme magnetoresistance in lasb,” *Nat. Phys.* **12**, 272–277 (2016).
 - ¹² F.F. Tafti, Q.D. Gibson, S. Kushwaha, J.W. Krizan, N. Haldolaarachchige, and R.J. Cava, “Temperature-field phase diagram of extreme magnetoresistance,” *PNAS* **113**, E3475–E3481 (2016).
 - ¹³ P.-J. Guo, H.-C. Yang, B.-J. Zhang, K. Liu, and Z.-Y. Lu, “Charge compensation in extremely large magnetoresistance materials LaSb and LaBi revealed by first-principles calculations,” *Phys. Rev. B* **93**, 235142 (2016).
 - ¹⁴ H.-Y. Yang, T. Nummy, H. Li, S. Jaszewski, M. Abramchuk, D.S. Dessau, and F.F. Tafti, “Extreme magnetoresistance in the topologically trivial lanthanum monopnictide LaAs,” *Phys. Rev. B* **96**, 235128 (2017).
 - ¹⁵ R. Lou, B.-B. Fu, Q.N. Xu, P.-J. Guo, L.-Y. Kong, L.-K. Zeng, J.-Z. Ma, P. Richard, C. Fang, Y.-B. Huang, S.S. Sun, Q. Wang, L. Wang, Y.-G. Shi, H.C. Lei, K. Liu, H.M. Weng, T. Qian, H. Ding, and S.-C. Wang, “Evidence of topological insulator state in the semimetal LaBi,” *Phys. Rev. B* **95**, 115140 (2017).
 - ¹⁶ H. Oinuma, S. Souma, D. Takane, T. Nakamura, K. Nakayama, T. Mitsuhashi, K. Horiba, H. Kumigashira, M. Yoshida, A. Ochiai, T. Takahashi, and T. Sato, “Three-dimensional band structure of LaSb and CeSb: Absence of band inversion,” *Phys. Rev. B* **96**, 041120 (2017).
 - ¹⁷ T. J. Nummy, J. A. Waugh, S. P. Parham, Q. Liu, H.-Y. Yang, H. Li, X. Zhou, N. C. Plumb, F. F. Tafti, and Dessau D. S., “Anomalous quantum oscillations and evidence for a non-trivial Berry phase in SmSb,” *npj Quantum Mater.* **3**, 24 (2018).
 - ¹⁸ X.H. Niu, D.F. Xu, Y.H. Bai, Q. Song, X.P. Shen, B.P. Xie, Z. Sun, Y.B. Huang, D.C. Peets, and D.L. Feng, “Presence of exotic electronic surface states in LaBi and LaSb,” *Phys. Rev. B* **94**, 165163 (2016).
 - ¹⁹ R. Singha, B. Satpati, and P. Mandal, “Fermi surface topology and signature of surface dirac nodes in LaBi,” *Sci. Rep.* **7**, 1–9 (2017).
 - ²⁰ J. Nayak, S.-C. Wu, N. Kumar, C. Shekhar, S. Singh, J. Fink, E.E.D. Rienks, G.H. Fecher, S.S.P. Parkin, B. Yan, and C. Felser, “Multiple Dirac cones at the surface of the topological metal LaBi,” *Nat. Commun.* **8**, 13942 (2017).
 - ²¹ B. Feng, J. Cao, M. Yang, Y. Feng, S. Wu, B. Fu, M. Arita, K. Miyamoto, S. He, K. Shimada, Y. Shi, T. Okuda, and Y. Yao, “Experimental observation of node-line-like surface states in LaBi,” *Phys. Rev. B* **97**, 155153 (2018).
 - ²² Orest Pavlosiuk, Przemysław Swatek, Dariusz Kaczorowski, and Piotr Wiśniewski, “Magnetoresistance in LuBi and YBi semimetals due to nearly perfect carrier compensation,” *Phys. Rev. B* **97**, 235132 (2018).
 - ²³ D.D. Liang, Y.J. Wang, C.Y. Xi, W.L. Zhen, J. Yang, L. Pi, W.K. Zhu, and C.J. Zhang, “Extreme magnetoresistance and Shubnikov-de Haas oscillations in ferromagnetic DySb,” *APL Mater.* **6**, 086105 (2018).
 - ²⁴ F. Wu, C.Y. Guo, M. Smidman, J.L. Zhang, and H.Q. Yuan, “Large magnetoresistance and fermi surface topology of PrSb,” *Phys. Rev. B* **96**, 125122 (2017).
 - ²⁵ L. Ye, T. Suzuki, C.R. Wicker, and J.G. Checkelsky, “Extreme magnetoresistance in magnetic rare-earth monopnictides,” *Phys. Rev. B* **97**, 081108 (2018).
 - ²⁶ Y.-Y. Wang, H. Zhang, X.-Q. Lu, L.-L. Sun, S. Xu, Z.-Y. Lu, K. Liu, S. Zhou, and T.-L. Xia, “Extremely large magnetoresistance and electronic structure of TmSb,” *Phys. Rev. B* **97**, 085137 (2018).
 - ²⁷ Y.-Y. Wang, L.-L. Sun, S. Xu, Y. Su, and T.-L. Xia, “Unusual magnetotransport in holmium monoantimonide,” *Phys. Rev. B* **98**, 045137 (2018).
 - ²⁸ Y.-Y. Lyu, F. Han, Z.-L. Xiao, J. Xu, Y.-L. Wang, H.-B. Wang, J.-K. Bao, D.y. Chung, M. Li, I. Martin, U. Welp, M.G. Kanatzidis, and W.-K. Kwok, “Magnetization-governed magnetoresistance anisotropy in the topological semimetal CeBi,” *Phys. Rev. B* **100**, 180407 (2019).
 - ²⁹ Z.M. Wu, Y.R. Ruan, F. Tang, L. Zhang, Y. Fang, J.M. Zhang, Z.D. Han, R.J. Tang, B. Qian, and X.F. Jiang, “Multiple metamagnetism, extreme magnetoresistance and nontrivial topological electronic structures in the magnetic semimetal candidate holmium monobismuthide,” *New J. Phys.* **21**, 093063 (2019).
 - ³⁰ M. M. Hosen, G. Dhakal, B. Wang, N. Poudel, B. Singh, K. Dimitri, F. Kabir, C. Sims, S. Regmi, W. Neff, A. B. Sarkar,

- A. Agarwal, D. Murray, F. Weickert, K. Gofryk, O. Pavlosiuk, P. Wiśniewski, D. Kaczorowski, A. Bansil, and Neupane. M., "Observation of gapped state in rare-earth monopnictide HoSb," *Sci. Rep.* **10**, 1–8 (2020).
- ³¹ M. Neupane, M.M. Hosen, I. Belopolski, N. Wakeham, K. Dimitri, Na. Dhakal, J.-X. Zhu, M.Z. Hasan, E.D. Bauer, and F. Ronning, "Observation of Dirac-like semi-metallic phase in NdSb," *J. Condens. Matter Phys.* **28**, 23LT02 (2016).
- ³² C. Guo, C. Cao, M. Smidman, F. Wu, Y. Zhang, F. Steglich, F.-C. Zhang, and H. Yuan, "Possible weyl fermions in the magnetic kondo system CeSb," *npj Quantum Mater.* **2**, 1–6 (2017).
- ³³ F. Wu, C. Guo, M. Smidman, J. Zhang, Y. Chen, J. Singleton, and H. Yuan, "Anomalous quantum oscillations and evidence for a non-trivial Berry phase in SmSb," *npj Quantum Mater.* **4**, 1–6 (2019).
- ³⁴ H.-Y. Yang, J. Gaudet, A.A. Aczel, D.E. Graf, P. Blaha, B.D. Gaulin, and F.F. Tafti, "Interplay of magnetism and transport in HoBi," *Phys. Rev. B* **98**, 045136 (2018).
- ³⁵ F. Hulliger, H.R. Ott, and T. Siegrist, "Low temperature behaviour of HoBi," *J. less-common met.* **96**, 263–268 (1984).
- ³⁶ P. Fischer, W. Hälg, and F. Hulliger, "Magnetic ordering in HoBi, HoS, ErS and ErSe," *Physica B+C* **130**, 551 – 554 (1985).
- ³⁷ A. Fente, H. Suderow, S. Vieira, N.M. Nemes, M. García-Hernández, S.L. Bud'ko, and P.C. Canfield, "Low temperature magnetic transitions of single crystal HoBi," *Solid State Commun.* **171**, 59–63 (2013).
- ³⁸ W.C. Chen, R. Erwin, J.W. McIver III, S. Watson, C.B. Fu, T.R. Gentile, J.A. Borchers, J.W. Lynn, and G.L. Jones, "Applications of ^3He neutron spin filters at the NCNR," *Physica B Condens.* **404**, 2663–2666 (2009).
- ³⁹ W.C. Chen, T.R. Gentile, R. Erwin, S. Watson, Q. Ye, K.L. Krycka, and B.B. Maranville, " ^3He spin filter based polarized neutron capability at the NIST Center for Neutron Research," *J. Phys. Conf. Ser.* **528**, 012014 (2014).
- ⁴⁰ A. Scheie, "LongHCPulse: Long-Pulse heat capacity on a quantum design PPMS," *J. Low Temp. Phys.* **193**, 60–73 (2018).
- ⁴¹ M. Blume, A.J. Freeman, and R.E. Watson, "Neutron magnetic form factors and x-ray atomic scattering factors for rare-earth ions," *Chem. Phys.* **37**, 1245–1253 (1962).
- ⁴² R.M. White and B. Bayne, *Quantum theory of magnetism*, Vol. 1 (Springer, 1983).
- ⁴³ D. Hohlwein, J.-U. Hoffmann, and R. Schneider, "Magnetic interaction parameters from paramagnetic diffuse neutron scattering in MnO," *Phys. Rev. B* **68**, 140408 (2003).
- ⁴⁴ L.C. Bartel, "Stability of f.c.c. type-2 antiferromagnetic ordering and comments on the calculation of exchange constants: Application to MnO, α -MnS, NiO, GdP and GdAs," *Solid State Commun.* **11**, 55–59 (1972).
- ⁴⁵ N.-N. Sun and H.-Y. Wang, "The J1-J2 model on the face-centered-cubic lattices," *J. Magn. Magn. Mater.* **454**, 176–184 (2018).
- ⁴⁶ P. Balla, Y. Iqbal, and K. Penc, "Degenerate manifolds, helimagnets, and multi- q chiral phases in the classical heisenberg antiferromagnet on the face-centered-cubic lattice," *Phys. Rev. Res.* **2**, 043278 (2020).
- ⁴⁷ G.E. Bacon and R.D. Lowde, "Secondary extinction and neutron crystallography," *Acta Crystallogr.* **1**, 303–314 (1948).
- ⁴⁸ K.W.H. Stevens, "Matrix elements and operator equivalents connected with the magnetic properties of rare earth ions," *Proc. Phys. Soc. Section A* **65**, 209 (1952).
- ⁴⁹ M.T. Hutchings, "Point-charge calculations of energy levels of magnetic ions in crystalline electric fields," in *Solid state physics*, Vol. 16 (Elsevier, 1964) pp. 227–273.
- ⁵⁰ A.J. Freeman and R.E. Watson, "Theoretical investigation of some magnetic and spectroscopic properties of rare-earth ions," *Phys. Rev.* **127**, 2058 (1962).
- ⁵¹ A Furrer and W Halg, "Crystal-field splittings of NdN and HoN," *J. Phys. C Solid State Phys.* **9**, 3499 (1976).
- ⁵² B.D. Rainford and J.D. Houmann, "Magnetic exciton dispersion in praseodymium," *Phys. Rev. Lett.* **26**, 1254 (1971).
- ⁵³ W.J.L. Buyers, T.M. Holden, E.C. Svensson, R.A. Cowley, and M.T. Hutchings, "Excitations in KCoF_3 . II. Theoretical," *J. Phys. C Solid State Phys* **4**, 2139 (1971).
- ⁵⁴ P.M. Sarte, M. Songvilay, E. Pachoud, R.A. Ewings, C.D. Frost, D. Prabhakaran, K.H. Hong, A.J. Browne, Z. Yamani, J.P. Attfield, E.E. Rodriguez, S.D. Wilson, and C. Stock, "Spin-orbit excitons in CoO," *Phys. Rev. B* **100**, 075143 (2019).
- ⁵⁵ P.M. Sarte, C. Stock, B.R. Ortiz, K.H. Hong, and S.D. Wilson, "Van vleck excitons in Ca_2RuO_4 ," *Phys. Rev. B* **102**, 245119 (2020).
- ⁵⁶ B. Yuan, M.B. Stone, G.-J. Shu, F.C. Chou, X. Rao, J.P. Clancy, and Y.-J. Kim, "Spin-orbit exciton in a honeycomb lattice magnet CoTiO_3 : Revealing a link between magnetism in d - and f -electron systems," *Phys. Rev. B* **102**, 134404 (2020).
- ⁵⁷ T.M. Holden, E.C. Svensson, W.J.L. Buyers, and O. Vogt, "Magnetic excitations in terbium antimonide," *Phys. Rev. B* **10**, 3864 (1974).
- ⁵⁸ P. Bak, "Magnetic excitations in rare earth Al_2 compounds," *AIP Conference Proceedings* **24**, 152–158 (1975).