

Pressure-dependent electronic superlattice in the Kagome-superconductor CsV_3Sb_5

F. Stier,^{1,*} A.-A. Haghighirad,^{2,*} G. Garbarino,³ S. Mishra,^{1,4} N. Stölkerich,^{1,5} D. Chen,^{5,6}
C. Shekhar,⁵ T. Lacmann,² C. Felser,^{5,4} T. Ritschel,¹ J. Geck,^{1,4,†} and M. Le Tacon^{2,‡}

¹*Institut für Festkörper- und Materialphysik, Technische Universität Dresden, 01062 Dresden, Germany*

²*Institute for Quantum Materials and Technologies,*

Karlsruhe Institute of Technology, Kaiserstr. 12, D-76131 Karlsruhe, Germany

³*ESRF, The European Synchrotron, 71, avenue des Martyrs, CS 40220 F-38043 Grenoble Cedex 9*

⁴*Würzburg-Dresden Cluster of Excellence ct.qmat,*

Technische Universität Dresden, 01062 Dresden, Germany

⁵*Max Planck Institute for Chemical Physics of Solids, Dresden, Germany*

⁶*College of Physics, Qingdao University, Qingdao 266071, China*

(Dated: April 24, 2024)

We present a high-resolution single crystal x-ray diffraction study of Kagome superconductor CsV_3Sb_5 , exploring its response to variations in pressure and temperature. We discover that at low temperatures, the structural modulations of the electronic superlattice, commonly associated with charge density wave order, undergo a transformation around $p \sim 0.7$ GPa from the familiar 2×2 pattern to a long-range ordered modulation at wavevector $q = (0, 3/8, 1/2)$. Our observations align with inferred changes in the CDW pattern from prior transport and nuclear magnetic resonance studies, providing new insights into these transitions. Interestingly, the pressure-induced variations in the electronic superlattice correlate with two peaks in the superconducting transition temperature as pressure changes, hinting that fluctuations within the electronic superlattice could be key to stabilizing superconductivity. However, our findings contrast with the minimal pressure dependency anticipated by ab initio calculations of the electronic structure. They also challenge prevailing scenarios based on a Peierls-like nesting mechanism involving van Hove singularities.

Understanding the correlation between unconventional superconductivity (SC) and spatial electronic modulations, encompassing magnetic, nematic, or charge density wave (CDW) orders, represents one of the key challenges in contemporary condensed matter research [1–3]. Consequently, extensive endeavors are underway to unravel the underlying physics in quantum materials like cuprates [4], nickelates [5, 6], iron or nickel pnictides [7–9], transition metal dichalcogenides [10] or heavy fermion compounds [11], where the relation between SC and CDW phenomena can be examined in different settings.

In this framework, a new and extremely intriguing class of materials has recently been discovered: the layered Kagome-compounds $AV_3\text{Sb}_5$ ($A=\text{K}, \text{Cs}, \text{Rb}$) [12]. Characterized by an electronic structure featuring flat bands, van Hove singularities (vHs), Dirac cones, and non-trivial band topology, these materials offer a unique platform for exploring novel electronic states of matter with intertwined orders [3]. Particularly noteworthy is the detection of an electronic superlattice below 94 K, [12] which is commonly associated with a CDW, and that is succeeded by superconductivity below $T_c \simeq 2.7$ K in CsV_3Sb_5 – a revelation that has sparked considerable excitement. This excitement has been further substantiated by recent accounts of the absence of Kohn-anomalies in the phonon dispersion associated with the formation of the CDW [13, 14], chirality [15], time-reversal symmetry

breaking or electronic nematicity [16] of the electronic superlattice. Consequently, while we refer to the electronic modulation in CsV_3Sb_5 as a charge density wave (CDW) in the following, we recognize that it is often rightly considered unconventional and that the underlying electronic order may be substantially more complex. As a matter of fact, numerous important aspects of this CDW and of its relationship with SC in CsV_3Sb_5 remain elusive and subject to intense debate [16–20]. The origin of the CDW and the nature of the interplay between electronic and lattice degrees of freedom in these materials therefore requires further elucidation [13, 14, 21, 22].

To address such issues, pressure tuning has proven to be a valuable tool in quantum materials research [23–25], providing a reversible method to adjust the balance between competing energy scales and enabling the investigation of complex phase diagrams in these materials without introducing chemical disorder. This approach is without doubt most relevant in the case of kagome superconductors, since both SC and CDW transition temperatures have been reported to strongly depend on hydrostatic pressure, displaying intriguing behavior already for relatively modest pressures [17, 26, 27]. This is demonstrated across a diverse array of measurements encompassing electrical- and magnetotransport, magnetic susceptibility, nuclear magnetic and quadrupole resonances (NMR and NQR), x-ray diffraction (XRD), and muon spin resonance [17, 26–29] which have revealed that both the superconducting transition temperature (T_c) and the upper critical field H_{c2} as a function of pressure p exhibit a distinctive double-dome feature below $p < 2.0$ GPa, characterized by a first maximum of ~ 7 K at $p_1 \simeq 0.7$

* These authors contributed equally to this work

† jochen.geck@tu-dresden.de

‡ matthieu.letacon@kit.edu

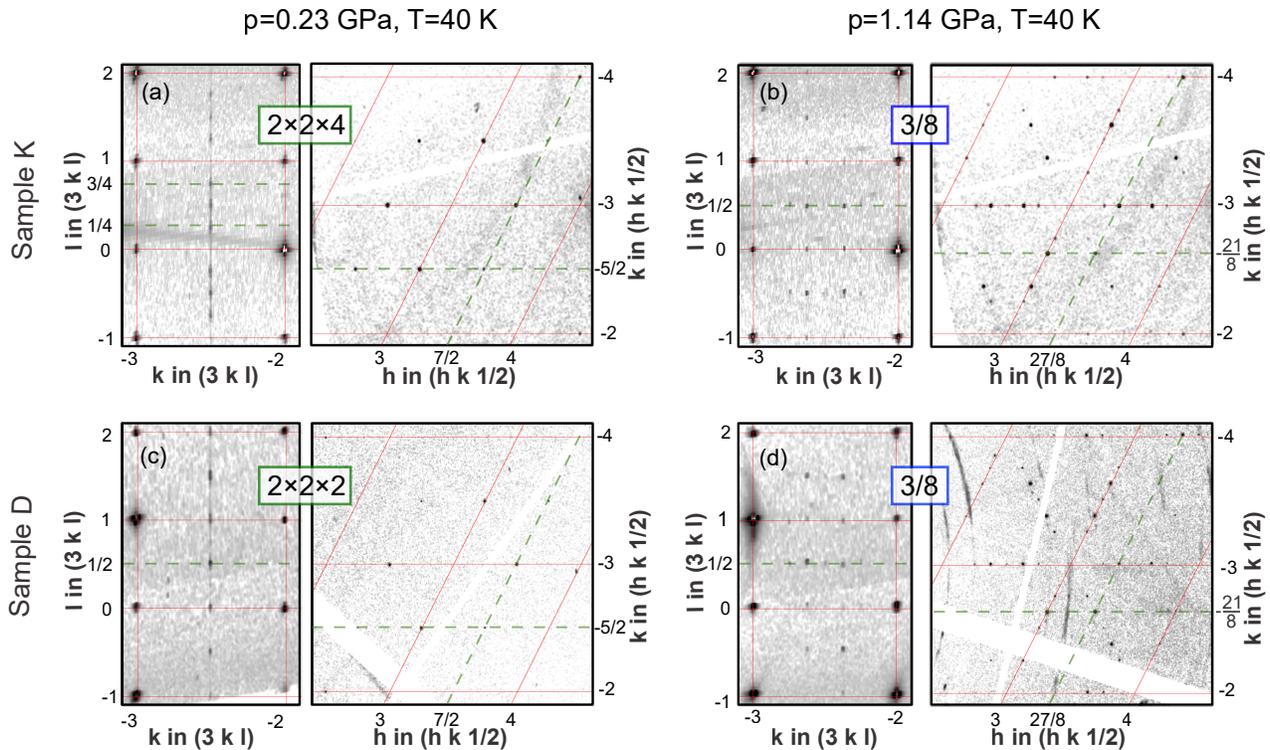


FIG. 1. Temperature and pressure dependence of the superlattice modulation observed for sample *K* (top) and *D* (bottom). hl - and the hk -cuts through XRD intensity distributions reciprocal space are shown. At 40 K and $p = 0.23$ GPa, the two samples both display a 2×2 modulation along ab but a different superstructure along c . Increasing the pressure at 40 K drives both samples into the same $3/8$ -phase.

GPa, succeeded by a second maximum at $p_2 \simeq 2$ GPa with $T_c \simeq 8$ K [17, 27, 30, 31]. The CDW transition temperature appears monotonically suppressed with pressure, but from a marked reduction of the magnetoresistance [26] and the appearance of new NMR lines above p_1 , changes in the electronic modulation pattern have been indirectly inferred.

Nonetheless, a thorough examination of the pressure dependence of CDW superstructures across various temperatures –essential for clarifying the microscopic physics at play– has yet to be undertaken. Here we close this gap, by reporting a detailed high resolution single crystal x-ray diffraction (XRD) study of CsV_3Sb_5 as function of pressure and temperature. We report the gradual suppression of the familiar 2×2 CDW modulation with pressure, alongside the appearance of a new type of modulation with a completely different pattern and periodicity above p_1 . The two orders coexist for a while before the disappearance of the former. At 25 K, no CDW survives above ~ 1.7 GPa. The behavior of these CDWs is compatible with their ultimate vanishing at a quantum critical point located near p_2 [27].

However, the striking transformation of the CDW pattern within this pressure range contrasts with the modest impact on the electronic structure found in density functional theory (DFT). In particular, the van Hove singularities below the Fermi energy show minimal change at

these pressures. This discrepancy challenges weak coupling scenarios that attribute the formation of electronic superlattices in Kagome metals AV_3Sb_5 ($A=\text{K}, \text{Cs}, \text{Rb}$) to a Peierls-like nesting of van Hove singularities [32, 33].

We investigated single crystals from two distinct batches, referred to as batch *D* and batch *K* in the following, synthesized and characterized, as described in the supplementary information [34]. High-resolution XRD measurements as a function of T and p were performed at the ID15B beamline of the ESRF in Grenoble, France, using a monochromatic x-ray beam with an energy of 30.17 keV, focused down to $2 \times 4 \mu\text{m}^2$ at the sample position. The diffraction patterns were measured with an EIGER2 X 9M CdTe flat panel detector. Diamond anvil cells (DACs) with helium as a pressure transmitting medium were used to apply pressures of up to 27 GPa under close to hydrostatic conditions. In each DAC, one sample of batch *D* and one of batch *K* were loaded into the sample space, so that both samples were in exactly the same experimental condition during our pressure and temperature dependent XRD measurements. Further details are given in the supplementary information [34].

At room temperature and ambient pressure, both samples exhibit a hexagonal $P6/mmm$ structure, in full agreement with previously published results [35]. In the following, reflections will be always indexed referring to this structure, even though there are structural

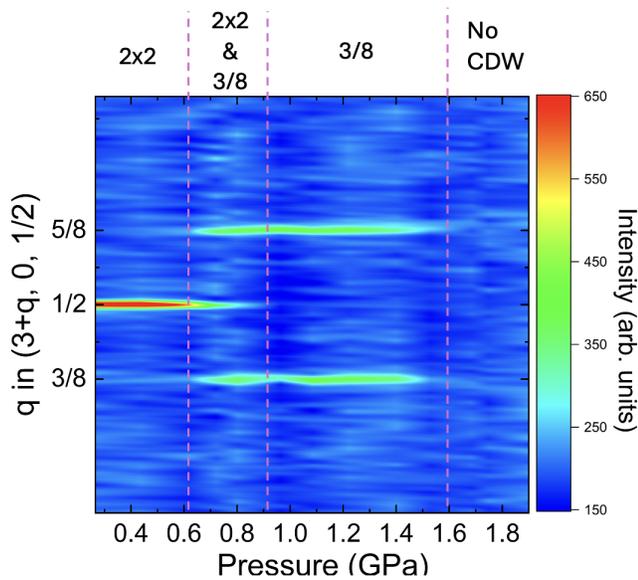


FIG. 2. Pressure dependence of the CDW order in CsV_3Sb_5 . The contour plot shows the XRD-intensity along the $A-L$ reciprocal direction (obtained from the averaging of the intensity along the six equivalent reciprocal directions $A-L$ from the $(3,0,1/2)$ A point) measured at 25 K. The intensity at the L point below 0.7 GPa signals the $2 \times 2 \times 2$ order, which transforms into the $3/8$ modulation with increasing pressure revealed by the intensity at $q = 3/8$ and $q = 5/8$ above 0.7 GPa.

transitions as a function of p and T [34]. In agreement with previous reports [12], both samples develop a 2×2 orthorhombic superstructure within the ab -planes when cooled below 94 K at ambient or small pressure. This CDW transition is signalled by additional satellite reflections, as demonstrated in panels (a) and (c) of Fig. 1. Interestingly, as can also be observed in these panels, the structural modulation of the two set of samples differs along the c -direction. At 40 K and $p = 0.23$ GPa, despite special care taken to ensure they are precisely in the same experimental condition and sharing the same pT -history, sample K exhibits a $2 \times 2 \times 4$ modulation, whereas sample D displays a $2 \times 2 \times 2$ order. This observation supports earlier conclusions that the orders along c are metastable [36], while the 2×2 modulation within the ab -layers is a defining feature of the electronic ordering instability of CsV_3Sb_5 at ambient pressure [37].

The major experimental finding of our study is represented by the data in the right panels (b) and (d) of Fig. 1: Irrespective of the periodicity of the modulation along the c -axis, an increase of the pressure p to 0.7 GPa at constant $T=40$ K induces in both samples a transition into a new phase characterized by the *same* commensurate modulation vector $q = (0, \frac{3}{8}, \frac{1}{2})$. We will refer to this as the ‘ $3/8$ ’ phase in the following. This observation aligns very well with recent findings from ^{51}V NMR [17] and $^{121/123}\text{Sb}$ NQR [27], which reported in this very pressure range the appearance of new spectral features that are distinct from those of the 2×2 modulation and have been

interpreted as evidence of a new type of CDW order. Although these local probes cannot directly determine the ordering wave vector, proposals for an incommensurate structure [27] or a unidirectional order with a period of $4 \times a$ [17] have been suggested. While our XRD data confirms a pressure-driven change in the electronic order, we unambiguously reveal here that the p -induced ordering is commensurate and different from the suggested $4 \times a$.

With a further increase in p at constant T , the intensities of the superlattice peaks of the $3/8$ -phase gradually diminish and vanish above 1.7 GPa, again in good agreement with the nuclear resonance data [17, 27]. According to our structural refinement, the $3/8$ phase is accompanied with a small monoclinic distortion [34].

To further elucidate the evolution of the CDW order with respect p , we show in Fig. 2 the pressure dependence of the XRD-intensity along the high symmetry $A-L$ line (starting from the reciprocal A point at $(3,0,0.5)$) as a function of p at constant $T = 25$ K. With p increasing towards 0.7 GPa, the satellite reflections of the 2×2 in-plane order are gradually suppressed. As can be observed in Fig. 2, the intensity of this peak weakens significantly around 0.7 GPa, but remains detectable up to 0.9 GPa. At the same time, the new $3/8$ modulation emerges around 0.7 GPa, i.e., the 2×2 and the $3/8$ phases coexist between 0.7 and 0.9 GPa. Beyond 0.9 GPa, the 2×2 disappears completely, and by further increasing p also the scattering due to the $3/8$ modulation is progressively reduced until it falls below our detection limit at 1.7 GPa. The data shown in Fig. 2 (a) further reveals that, within the error of our experiment the positions of the satellite peaks corresponding to the 2×2 and the $3/8$ order do not change with varying p and that, despite the strong suppression of the intensity, the satellite reflections always remain as sharp as the Bragg reflections and are essentially resolution limited [34]. This is true both for in- and out-of-plane directions.

The results of our XRD studies below 100 K and up to 2.5 GPa are summarized in the pT -phase diagram presented in Fig. 3, where the stability regions of the 2×2 and the $3/8$ orders are indicated by the green and blue areas, respectively. Comparing the pressure dependence of the electronic order to the pressure dependence of the superconducting T_c [38, 39] reveals an interesting correlation: The pressure $p_1 \simeq 0.7$ GPa, where $T_c(p)$ shows its first maximum, aligns perfectly to the critical pressure where the 2×2 order is suppressed and the $3/8$ order appears. Furthermore, the pressure $p_2 \simeq 2$ GPa of the second maximum of $T_c(p)$ coincides well with that at which the $3/8$ phase disappears. The suppression of the $3/8$ phase also further supports the possible existence of quantum critical point below this dome.

The observation that every time an electronic order is suppressed with increasing p , the superconducting transition temperature $T_c(p)$ exhibits a maximum is remarkable. One obvious explanation to be considered is, of course, the competition between CDW and SC. Direct experimental evidence for this competition, for example

in the form of a suppression of the CDW in the superconducting state is still lacking. Nevertheless, the observation of a peak in $T_c(p)$ near the critical point of a distinct electronically ordered phase (here the 2×2 or the $3/8$ phase) suggests that the corresponding fluctuations may contribute to supporting superconductivity. This conjecture certainly warrants careful examination in future investigations.

It is important to note that the consistently resolution-limited satellite reflections (cf. Fig. 2) do not necessarily imply the absence of fluctuations. The resolution-limited width of these reflections simply indicates that the coherent contribution to a given satellite reflection originates from a volume of about 10^4 unit cells. However, it remains indeterminate whether this volume constitutes a single contiguous entity or a series of smaller, distinct volumes maintaining a fixed phase relation (see Ref. [40]). In essence, despite the sharpness of the satellite peaks, regions experiencing fluctuations may still exist. These fluctuations would manifest as an exceedingly weak diffuse scattering signal, beyond the detection capabilities of the current experimental setup.

The comparison of the present p -dependent XRD results to those of a recent doping dependent study [41] is also very interesting: In the doping dependent study, it was observed that replacing Sb with Sn destabilizes the 2×2 superlattice as well, leading to the emergence of a new superlattice at low temperatures with a modulation wave vector similar to that of the $3/8$ phase observed here. However, there are notable distinctions between the doping and p -induced orders: The doping-induced phase exhibits short and highly anisotropic correlation lengths

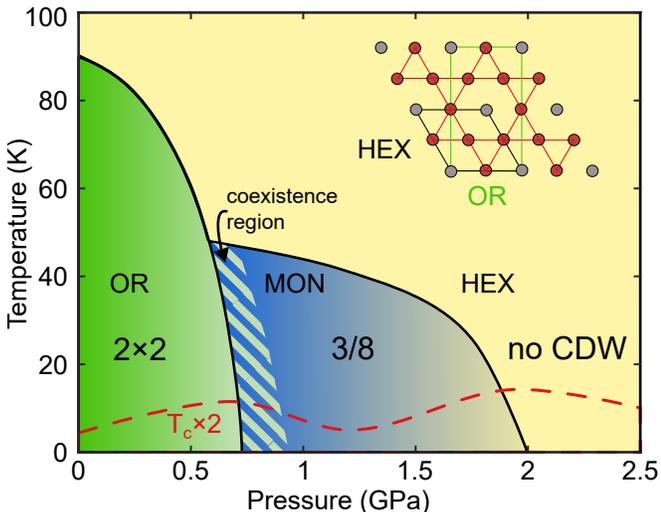


FIG. 3. Electronic phase diagram of CsV_3Sb_5 in the low-pressure and low-temperature region. The orthorhombic $2 \times 2 \times 2$ and $2 \times 2 \times 4$ phases, summarized as 2×2 , exist in the green region below ≈ 0.7 GPa. The new monoclinic phase with the $3/8$ -order is indicated in blue. Both phases coexist in a narrow pressure range as indicated by the striped area. The red dashed line sketches the evolution of the superconducting T_c as a function of pressure (after Ref. 17).

within the ab -layers and signs of electronic nematicity. In contrast, the superlattice modulations observed in pristine CsV_3Sb_5 , including the p -induced $3/8$ -phase, always display full long-range order in all three dimensions with an isotropic in-plane correlation length. The latter is evident from the high-resolution data presented in Fig. 1, and confirmed by further analysis which revealed that all satellites reflections are as narrow (resolution limited) as the neighboring Bragg reflections with correlation lengths amounting to 100 \AA both in and out of the hk plane. The 2×2 and the pressure-induced $3/8$ -order therefore both lack the characteristics discussed earlier in terms of electronic nematicity.

In principle, Sn-substitution and p do not represent equivalent modifications of CsV_3Sb_5 . On a qualitative level, however, they both affect the c/a ratio, which has been found to play a critical role for controlling the electronic properties [19, 22]. Due to the anisotropic layered structure of CsV_3Sb_5 , hydrostatic pressure has indeed a pronounced effect on the c/a ratio, which can be determined precisely by our measurements. We find that a pressure as modest as 1 GPa is sufficient to reduce c/a by about 3% [34].

In good agreement with DFT calculations [22], our structural refinement reveals that the distance between apical Sb and the kagome layers is barely affected by $p = 1$ GPa, in stark contrast to the inter unit-cell distance between apical Sb-sites, which decreases by about 5%. These structural changes primarily affect the Sb $5p_z$ -states, as clearly demonstrated in the DFT band structures shown in supplementary Fig. 7, which are based on our structural data. As can be observed in this figure, the bottom of the Γ -centered electron pocket and the top of the hole-like band at the A-point move significantly closer to the Fermi level with increasing p . However, the vHs at the M-point, which are below the Fermi-level, remain essentially unaffected. This behaviour is in very good agreement with previous theoretical studies [22, 42, 43], where similar trends have been reported.

The drastic pressure dependence of the electronic superlattice reported here therefore implies that the nesting of vHs cannot be the primary stabilization mechanism in CsV_3Sb_5 . If this was the case, the 2×2 order would be expected to remain entirely stable below 1 GPa, at odds with our experimental observation. This conclusion is further supported by a detailed analysis of the Lindhard function from DFT [44], which shows that there is no unique nesting vector and, in particular, that the vHs do not cause well-defined peaks in the Lindhard function. Within DFT, the electronic system alone does therefore not favor a specific ordering wave vector [44]. The emergence of the $3/8$ order, which has not been predicted by any first principles calculations to our knowledge, highlights that the mechanism underlying charge order instabilities in these kagome materials remains to be understood.

A strongly momentum-dependent electron-phonon coupling has for instance been considered as a driv-

ing force behind the stabilization of a specific long-range order [44–46]. The p -driven transition from the 2×2 to the $3/8$ phase would then imply a strongly p -dependent electron-phonon coupling at pressures below 1 GPa, which is hardly consistent with weak coupling models. This hints at strong coupling effects beyond DFT.

In conclusion, the present study yields two major findings namely the correlation between the critical pressures of the electronic modulations and superconductivity in CsV_3Sb_5 and a transition from the 2×2 to a long-range charge ordered $3/8$ phase at pressures below 1 GPa. Furthermore, our findings reveal pressure-induced structural modulations that appear to coincide with the trend in the superconductivity manifested in other experiments. These observations strongly substantiate the notion that critical fluctuations and complex electron-lattice interactions, extending well beyond conventional scenarios and

models, play a prominent role in shaping the complex phase diagram of AV_3Sb_5 .

ACKNOWLEDGEMENTS

We acknowledge fruitful discussions with R. Fernandes, R. Heid, M. Merz and S. M. Souliou. This research received support from the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation), under projects 422213477 (TRR 288 project B03) and 247310070 (CRC 1143 project C06 and B05). T.R., F.S., C.F. and J.G. express gratitude to the Würzburg-Dresden Cluster of Excellence on Complexity and Topology in Quantum Matter (ct.qmat EXC-2147, Project No. 390858490) for financial backing. Additionally, we extend our appreciation to the European Synchrotron Radiation Facility (ESRF) for providing access to their synchrotron radiation facilities.

-
- [1] R. M. Fernandes, P. P. Orth, and J. Schmalian, Intertwined vestigial order in quantum materials: Nematicity and beyond, *Annual Review of Condensed Matter Physics* **10**, 133 (2019).
- [2] D. F. Agterberg, J. C. S. Davis, S. D. Edkins, E. Fradkin, D. J. Van Harlingen, S. A. Kivelson, P. A. Lee, L. Radzihovsky, J. M. Tranquada, and Y. Wang, The physics of pair-density waves: Cuprate superconductors and beyond, *Annual Review of Condensed Matter Physics* **11**, 231 (2020).
- [3] T. Neupert, M. M. Denner, J.-X. Yin, R. Thomale, and M. Z. Hasan, Charge order and superconductivity in kagome materials, *Nature Physics* **18**, 137 (2022).
- [4] B. Keimer, S. A. Kivelson, M. R. Norman, S. Uchida, and J. Zaanen, From quantum matter to high-temperature superconductivity in copper oxides, *Nature* **518**, 179 (2015).
- [5] C. C. Tam, J. Choi, X. Ding, S. Agrestini, A. Nag, M. Wu, B. Huang, H. Luo, P. Gao, M. García-Fernández, L. Qiao, and K.-J. Zhou, Charge density waves in infinite-layer NdNiO_2 nickelates, *Nature Materials* **21**, 1116 (2022).
- [6] G. Krieger, L. Martinelli, S. Zeng, L. E. Chow, K. Kummer, R. Arpaia, M. Moretti Sala, N. B. Brookes, A. Ariando, N. Viart, M. Salluzzo, G. Ghiringhelli, and D. Preziosi, Charge and spin order dichotomy in NdNiO_2 driven by the capping layer, *Physical Review Letters* **129**, 027002 (2022).
- [7] M. Yi, A. Frano, D. H. Lu, Y. He, M. Wang, B. A. Frandsen, A. F. Kemper, R. Yu, Q. Si, L. Wang, M. He, F. Hardy, P. Schweiss, P. Adelman, T. Wolf, M. Hashimoto, S. K. Mo, Z. Hussain, M. Le Tacon, A. E. Bohmer, D. H. Lee, Z. X. Shen, C. Meingast, and R. J. Birgeneau, Spectral evidence for emergent order in $\text{Ba}_{1-x}\text{Na}_x\text{Fe}_2\text{As}_2$, *Physical Review Letters* **121**, 10.1103/PhysRevLett.121.127001 (2018).
- [8] S. M. Souliou, T. Lacmann, R. Heid, C. Meingast, M. Frachet, L. Paolasini, A. A. Haghighirad, M. Merz, A. Bosak, and M. Le Tacon, Soft-phonon and charge-density-wave formation in nematic BaNi_2As_2 , *Physical Review Letters* **129**, 247602 (2022).
- [9] T. Lacmann, A.-A. Haghighirad, S.-M. Souliou, M. Merz, G. Garbarino, K. Glazyrin, R. Heid, and M. Le Tacon, High-pressure phase diagram of bani_2as_2 : Unconventional charge density waves and structural phase transitions, *Physical Review B* **108**, 224115 (2023).
- [10] M. Leroux, I. Errea, M. Le Tacon, S. M. Souliou, G. Garbarino, L. Cario, A. Bosak, F. Mauri, M. Calandra, and P. Rodiere, Strong anharmonicity induces quantum melting of charge density wave in 2h-nbse_2 under pressure, *Physical Review B* **92**, 140303 (2015).
- [11] A. Aishwarya, J. May-Mann, A. Raghavan, L. Nie, M. Romanelli, S. Ran, S. R. Saha, J. Paglione, N. P. Butch, E. Fradkin, and V. Madhavan, Magnetic-field-sensitive charge density waves in the superconductor ute_2 , *Nature* **618**, 928 (2023).
- [12] B. R. Ortiz, S. M. L. Teicher, Y. Hu, J. L. Zuo, P. M. Sarte, E. C. Schueller, A. M. M. Abeykoon, M. J. Krogstad, S. Rosenkranz, R. Osborn, R. Seshadri, L. Balents, J. He, and S. D. Wilson, CsV_3Sb_5 : A F_2 topological kagome metal with a superconducting ground state, *Physical Review Letters* **125**, 247002 (2020).
- [13] H. Li, T. T. Zhang, T. Yilmaz, Y. Y. Pai, C. E. Marvinney, A. Said, Q. W. Yin, C. S. Gong, Z. J. Tu, E. Vescovo, C. S. Nelson, R. G. Moore, S. Murakami, H. C. Lei, H. N. Lee, B. J. Lawrie, and H. Miao, Observation of unconventional charge density wave without acoustic phonon anomaly in kagome superconductors AV_3Sb_5 ($A=\text{Rb}, \text{Cs}$), *Physical Review X* **11**, 031050 (2021).
- [14] D. Subires, A. Korshunov, A. H. Said, L. Sánchez, B. R. Ortiz, S. D. Wilson, A. Bosak, and S. Blanco-Canosa, Order-disorder charge density wave instability in the kagome metal $(\text{Cs},\text{Rb})\text{V}_3\text{Sb}_5$, *Nature Communications* **14**, 1015 (2023).
- [15] C. Guo, C. Putzke, S. Konyzheva, X. Huang, M. Gutierrez-Amigo, I. Errea, D. Chen, M. G. Vergniory,

- C. Felser, M. H. Fischer, T. Neupert, and P. J. W. Moll, Switchable chiral transport in charge-ordered kagome metal CsV_3Sb_5 , *Nature* **611**, 461 (2022).
- [16] L. Nie, K. Sun, W. Ma, D. Song, L. Zheng, Z. Liang, P. Wu, F. Yu, J. Li, M. Shan, D. Zhao, S. Li, B. Kang, Z. Wu, Y. Zhou, K. Liu, Z. Xiang, J. Ying, Z. Wang, T. Wu, and X. Chen, Charge-density-wave-driven electronic nematicity in a kagome superconductor, *Nature* **604**, 59 (2022).
- [17] L. Zheng, Z. Wu, Y. Yang, L. Nie, M. Shan, K. Sun, D. Song, F. Yu, J. Li, D. Zhao, S. Li, B. Kang, Y. Zhou, K. Liu, Z. Xiang, J. Ying, Z. Wang, T. Wu, and X. Chen, Emergent charge order in pressurized kagome superconductor CsV_3Sb_5 , *Nature* **611**, 682 (2022).
- [18] T. Asaba, A. Onishi, Y. Kageyama, T. Kiyosue, K. Ohtsuka, S. Suetsugu, Y. Kohsaka, T. Gaggli, Y. Kasahara, H. Murayama, K. Hashimoto, R. Tazai, H. Kontani, B. R. Ortiz, S. D. Wilson, Q. Li, H. H. Wen, T. Shibauchi, and Y. Matsuda, Evidence for an odd-parity nematic phase above the charge density wave transition in kagome metal CsV_3Sb_5 (2023), [arXiv:2309.16985 \[cond-mat.str-el\]](https://arxiv.org/abs/2309.16985).
- [19] M. Frachet, L. Wang, W. Xia, Y. Guo, M. He, N. Maraytta, R. Heid, A.-A. Haghighirad, M. Merz, C. Meingast, and F. Hardy, Colossal c-axis response and lack of rotational symmetry breaking within the kagome plane of the CsV_3Sb_5 superconductor (2023), [arXiv:2310.06102 \[cond-mat.supr-con\]](https://arxiv.org/abs/2310.06102).
- [20] Z. Liu, Y. Shi, Q. Jiang, E. W. Rosenberg, J. M. DeStefano, J. Liu, C. Hu, Y. Zhao, Z. Wang, Y. Yao, D. Graf, P. Dai, J. Yang, X. Xu, and J.-H. Chu, Absence of nematic instability in the kagome metal CsV_3Sb_5 (2023), [arXiv:2309.14574 \[cond-mat.supr-con\]](https://arxiv.org/abs/2309.14574).
- [21] Y. Zhong, S. Li, H. Liu, Y. Dong, K. Aido, Y. Arai, H. Li, W. Zhang, Y. Shi, Z. Wang, S. Shin, H. N. Lee, H. Miao, T. Kondo, and K. Okazaki, Testing electron-phonon coupling for the superconductivity in kagome metal CsV_3Sb_5 , *Nature Communications* **14**, 1945 (2023).
- [22] E. T. Ritz, H. S. Røising, M. H. Christensen, T. Birol, B. M. Andersen, and R. M. Fernandes, Superconductivity from orbital-selective electron-phonon coupling in AV_3Sb_5 , *Phys. Rev. B* **108**, L100510 (2023).
- [23] S. M. Souliou, A. Bosak, G. Garbarino, and M. L. Tacon, Inelastic x-ray scattering studies of phonon dispersions in superconductors at high pressures, *Superconductor Science and Technology* **33**, 124004 (2020).
- [24] L. G. Pimenta Martins, R. Comin, M. J. S. Matos, M. S. C. Mazzoni, B. R. A. Neves, and M. Yankowitz, High-pressure studies of atomically thin van der waals materials, *Applied Physics Reviews* **10**, 011313 (2023).
- [25] H.-K. Mao, X.-J. Chen, Y. Ding, B. Li, and L. Wang, Solids, liquids, and gases under high pressure, *Rev. Mod. Phys.* **90**, 015007 (2018).
- [26] F. H. Yu, D. H. Ma, W. Z. Zhuo, S. Q. Liu, X. K. Wen, B. Lei, J. J. Ying, and X. H. Chen, Unusual competition of superconductivity and charge-density-wave state in a compressed topological kagome metal, *Nature Communications* **12**, 3645 (2021).
- [27] X. Y. Feng, Z. Zhao, J. Luo, J. Yang, A. F. Fang, H. T. Yang, H. J. Gao, R. Zhou, and G.-q. Zheng, Commensurate-to-incommensurate transition of charge-density-wave order and a possible quantum critical point in pressurized kagome metal CsV_3Sb_5 , *npj Quantum Materials* **8**, 23 (2023).
- [28] C. Mielke, D. Das, J.-X. Yin, H. Liu, R. Gupta, Y.-X. Jiang, M. Medarde, X. Wu, H. C. Lei, J. Chang, P. Dai, Q. Si, H. Miao, R. Thomale, T. Neupert, Y. Shi, R. Khasanov, M. Z. Hasan, H. Luetkens, and Z. Guguchia, Time-reversal symmetry-breaking charge order in a kagome superconductor, *Nature* **602**, 245 (2022).
- [29] Z. Guguchia, R. Khasanov, and H. Luetkens, Unconventional charge order and superconductivity in kagome-lattice systems as seen by muon-spin rotation, *npj Quantum Materials* **8**, 41 (2023).
- [30] K. Y. Chen, N. N. Wang, Q. W. Yin, Y. H. Gu, K. Jiang, Z. J. Tu, C. S. Gong, Y. Uwatoko, J. P. Sun, H. C. Lei, J. P. Hu, and J. G. Cheng, Double superconducting dome and triple enhancement of T_c in the kagome superconductor CsV_3Sb_5 under high pressure, *Physical Review Letters* **126**, 247001 (2021).
- [31] F. Du, S. Luo, B. R. Ortiz, Y. Chen, W. Duan, D. Zhang, X. Lu, S. D. Wilson, Y. Song, and H. Yuan, Pressure-induced double superconducting domes and charge instability in the kagome metal KV_3Sb_5 , *Physical Review B* **103**, L220504 (2021).
- [32] H. Tan, Y. Liu, Z. Wang, and B. Yan, Charge density waves and electronic properties of superconducting kagome metals, *Physical Review Letters* **127**, 046401 (2021).
- [33] M. Kang, S. Fang, J.-K. Kim, B. R. Ortiz, S. H. Ryu, J. Kim, J. Yoo, G. Sangiovanni, D. Di Sante, B.-G. Park, C. Jozwiak, A. Bostwick, E. Rotenberg, E. Kaxiras, S. D. Wilson, J.-H. Park, and R. Comin, Twofold van hove singularity and origin of charge order in topological kagome superconductor CsV_3Sb_5 , *Nature Physics* **18**, 301 (2022).
- [34] See Supplemental Material at XXX for information on the samples and experimental methods as well as on the detailed structural analysis, which includes also references [47–54].
- [35] B. R. Ortiz, L. C. Gomes, J. R. Morey, M. Winiarski, M. Bordelon, J. S. Mangum, I. W. H. Oswald, J. A. Rodriguez-Rivera, J. R. Neilson, S. D. Wilson, E. Ertekin, T. M. McQueen, and E. S. Toberer, New kagome prototype materials: discovery of KV_3Sb_5 , RbV_3Sb_5 , and CsV_3Sb_5 , *Phys. Rev. Mater.* **3**, 094407 (2019).
- [36] Q. Xiao, Y. Lin, Q. Li, X. Zheng, S. Francoual, C. Plueckthun, W. Xia, Q. Qiu, S. Zhang, Y. Guo, J. Feng, and Y. Peng, Coexistence of multiple stacking charge density waves in kagome superconductor CsV_3Sb_5 , *Physical Review Research* **5**, L012032 (2023).
- [37] B. R. Ortiz, S. M. L. Teicher, L. Kautzsch, P. M. Sarte, N. Ratcliff, J. Harter, J. P. C. Ruff, R. Seshadri, and S. D. Wilson, Fermi surface mapping and the nature of charge-density-wave order in the kagome superconductor CsV_3Sb_5 , *Phys. Rev. X* **11**, 041030 (2021).
- [38] K. Y. Chen, N. N. Wang, Q. W. Yin, Y. H. Gu, K. Jiang, Z. J. Tu, C. S. Gong, Y. Uwatoko, J. P. Sun, H. C. Lei, J. P. Hu, and J.-G. Cheng, Double superconducting dome and triple enhancement of T_c in the kagome superconductor CsV_3Sb_5 under high pressure, *Phys. Rev. Lett.* **126**, 247001 (2021).
- [39] F. Du, S. Luo, B. R. Ortiz, Y. Chen, W. Duan, D. Zhang, X. Lu, S. D. Wilson, Y. Song, and H. Yuan, Pressure-induced double superconducting domes and charge instability in the kagome metal KV_3Sb_5 , *Phys. Rev. B* **103**, L220504 (2021).

- [40] M. A. Hossain, I. Zegkinoglou, Y. D. Chuang, J. Geck, B. Bohnenbuck, A. G. C. Gonzalez, H. H. Wu, C. Schüßler-Langeheine, D. G. Hawthorn, J. D. Denlinger, R. Mathieu, Y. Tokura, S. Satow, H. Takagi, Y. Yoshida, Z. Hussain, B. Keimer, G. A. Sawatzky, and A. Damascelli, Electronic superlattice revealed by resonant scattering from random impurities in $\text{Sr}_3\text{Ru}_2\text{O}_7$, *Scientific Reports* **3**, 2299 (2013).
- [41] L. Kautzsch, Y. M. Oey, H. Li, Z. Ren, B. R. Ortiz, G. Pokharel, R. Seshadri, J. Ruff, T. Kongruengkit, J. W. Harter, Z. Wang, I. Zeljkovic, and S. D. Wilson, Incommensurate charge-stripe correlations in the kagome superconductor $\text{CsV}_3\text{Sb}_{5-x}\text{Sn}_x$, *npj Quantum Materials* **8**, 37 (2023).
- [42] M. Wenzel, A. A. Tsirlin, F. Capitani, Y. T. Chan, B. R. Ortiz, S. D. Wilson, M. Dressel, and E. Uykur, Pressure evolution of electron dynamics in the superconducting kagome metal CsV_3Sb_5 , *npj Quantum Materials* **8**, 45 (2023).
- [43] A. A. Tsirlin, P. Fertey, B. R. Ortiz, B. Klis, V. Merkl, M. Dressel, S. D. Wilson, and E. Uykur, Role of sb in the superconducting kagome metal CsV_3Sb_5 revealed by its anisotropic compression, *SciPost Phys.* **12**, 049 (2022).
- [44] F. Kaboudvand, S. M. L. Teicher, S. D. Wilson, R. Seshadri, and M. D. Johannes, Fermi surface nesting and the lindhard response function in the kagome superconductor CsV_3Sb_5 , *Applied Physics Letters* **120**, 111901 (2022).
- [45] Y. Xie, Y. Li, P. Bourges, A. Ivanov, Z. Ye, J.-X. Yin, M. Z. Hasan, A. Luo, Y. Yao, Z. Wang, G. Xu, and P. Dai, Electron-phonon coupling in the charge density wave state of CsV_3Sb_5 , *Phys. Rev. B* **105**, L140501 (2022).
- [46] Z. Ye, A. Luo, J.-X. Yin, M. Z. Hasan, and G. Xu, Structural instability and charge modulations in the kagome superconductor av_3sb_5 , *Phys. Rev. B* **105**, 245121 (2022).
- [47] CrysAlis^{PRO} single crystal x-ray diffraction data collection and processing software.
- [48] G. M. Sheldrick, *SHELXT* – Integrated space-group and crystal-structure determination, *Acta Crystallographica Section A* **71**, 3 (2015).
- [49] V. Petříček, M. Dušek, and L. Palatinus, Crystallographic Computing System JANA2006: General features, *Zeitschrift für Kristallographie - Crystalline Materials* **229**, 345 (2014).
- [50] Q. Stahl, D. Chen, T. Ritschel, C. Shekhar, E. Sadrollahi, M. C. Rahn, O. Ivashko, M. v. Zimmermann, C. Felser, and J. Geck, Temperature-driven reorganization of electronic order in CsV_3Sb_5 , *Phys. Rev. B* **105**, 195136 (2022).
- [51] Z. Zhang, Z. Chen, Y. Zhou, Y. Yuan, S. Wang, J. Wang, H. Yang, C. An, L. Zhang, X. Zhu, Y. Zhou, X. Chen, J. Zhou, and Z. Yang, Pressure-induced reemergence of superconductivity in the topological kagome metal CsV_3Sb_5 , *Phys. Rev. B* **103**, 224513 (2021).
- [52] F. Yu, X. Zhu, X. Wen, Z. Gui, Z. Li, Y. Han, T. Wu, Z. Wang, Z. Xiang, Z. Qiao, J. Ying, and X. Chen, Pressure-induced dimensional crossover in a kagome superconductor, *Phys. Rev. Lett.* **128**, 077001 (2022).
- [53] A. A. Tsirlin, B. R. Ortiz, M. Dressel, S. D. Wilson, S. Winnerl, and E. Uykur, Effect of nonhydrostatic pressure on the superconducting kagome metal CsV_3Sb_5 , *Phys. Rev. B* **107**, 174107 (2023).
- [54] K. Koepnik and H. Eschrig, Full-potential nonorthogonal local-orbital minimum-basis band-structure scheme, *Phys. Rev. B* **59**, 1743 (1999).