

Valence instability of cerium under pressure in the Kondo-like perovskite $\text{La}_{0.1}\text{Ce}_{0.4}\text{Sr}_{0.5}\text{MnO}_3$

T. Eto

Kumamoto Technology Center, Sony Semiconductor Kyushu Company Limited,
Haramizu 4000-1, Kikuyou, Kikuchi, Kumamoto 869-1102, Japan

A. Sundaresan*

Chemistry and Physics of Materials Unit, Jawaharlal Nehru Centre for
Advanced Scientific Research, Jakkur P. O. Bangalore 560 064 India

F. Honda

Advanced Science Research Center, Japan Atomic Energy Research Institute, Tokai, Naka, Ibaraki 319-1195, Japan

G. Oomi

Department of Physics, Kyushu University, Ropponmatsu 4-2-1, Fukuoka 810-8560, Japan

(Dated: July 16, 2018)

Effect of hydrostatic pressure and magnetic field on electrical resistance of the Kondo-like perovskite manganese oxide, $\text{La}_{0.1}\text{Ce}_{0.4}\text{Sr}_{0.5}\text{MnO}_3$ with a ferrimagnetic ground state, have been investigated up to 2.1 GPa and 9 T. In this compound, the Mn-moments undergo double exchange mediated ferromagnetic ordering at $T_C \sim 280$ K and there is a resistance maximum, T_{\max} at about 130 K which is correlated with an antiferromagnetic ordering of *cerium* with respect to the Mn-sublattice moments. Under pressure, the T_{\max} shifts to lower temperature at a rate of $dT_{\max}/dP = -162$ K/GPa and disappears at a critical pressure $P_c \sim 0.9$ GPa. Further, the coefficient, m of $-\log T$ term due to Kondo scattering decreases linearly with increase of pressure showing an inflection point in the vicinity of P_c . These results suggest that *cerium* undergoes a transition from Ce^{3+} state to $\text{Ce}^{4+}/\text{Ce}^{3+}$ mixed valence state under pressure. In contrast to pressure effect, the applied magnetic field shifts T_{\max} to higher temperature presumably due to enhanced ferromagnetic Mn moments.

PACS numbers: 72.64.Fj, 72.15.Eb, 75.30.Mb

Perovskite manganites $R_{1-x}A_x\text{MnO}_3$ (R = trivalent rare earth; A = divalent alkaline earth) have been investigated extensively due to a lot of fascinating electronic properties such as insulator-metal transition (I-M), colossal magnetoresistance (CMR) and charge, orbital and spin ordering. Magnetic field, pressure, photons and electric field are the external parameters by which the size, existence and interplay of these effects can be varied.^{1,2} It is well known that the ground state properties of half-doped manganites, $R_{0.5}A_{0.5}\text{MnO}_3$ depend upon the width (W) of one electron conduction band; W is controlled by the average size (r_A) of the different A -cations through Mn-O-Mn bond angle. For example, $\text{La}_{0.5}\text{Sr}_{0.5}\text{MnO}_3$ with larger W ($r_A = 1.263$ Å) is a metallic ferromagnet in the ground state.³ This behavior has been explained by a theoretical scenario based on the double exchange (DE) interaction between Mn^{3+} and Mn^{4+} ions, where the spins of e_g electrons or holes are aligned in the direction of the t_{2g} local spins by Hund coupling and electrical conduction arises due to the hopping of the charge carriers from one ion to the next without changing their spin orientation.^{4,5,6}

In compounds containing rare earth elements, *cerium* is well known to exhibit a wide variety of electronic properties such as valence change, heavy fermion, superconductivity and magnetic ordering. In $\text{Pr}_{0.1}\text{Ce}_{0.4}\text{Sr}_{0.5}\text{MnO}_3$ compound having larger W , Kondo

like behavior and anomalous magnetic ordering of Ce were reported.⁷ In this system, there is a structural phase transition at 250 K from the high temperature orthorhombic phase (space group: $Imma$) to the low temperature tetragonal phase ($I4/mcm$) which is accompanied by a ferromagnetic ordering of manganese moments due to DE interactions, and Ce moments order antiferromagnetically with respect to Mn moments below $T \sim 120$ K. The electrical resistivity increases anomalously with decrease of temperature, particularly below the Curie temperature T_C , exhibiting a resistivity maximum at 120 K (T_{\max}), which corresponds to the ordering of Ce moments, and a minimum at 15 K (T_{\min}). The anomalous temperature dependence of resistivity $R(T)$ is in contrast to the expected metallic behavior below T_C due to DE interactions. Similar results were reported for $\text{La}_{0.1}\text{Ce}_{0.4}\text{Sr}_{0.5}\text{MnO}_3$ with the ferromagnetic ordering of Mn-moments at $T_C \sim 280$ K and Ce ordering below ~ 130 K.⁸ In these systems with larger W , since there is no charge ordering of manganese ions and the Mn-sublattice remains ferromagnetic down to 1.8 K, the resistivity anomaly has been attributed to Kondo-like scattering of $\text{Mn}:e_g$ conduction electrons by the localized $\text{Ce}:4f$ moments. The decrease of resistivity below T_{\max} or *cerium* ordering temperature is due to reduced spin dependent scattering.

In order to get more insight into the nature of in-

interactions between the localized Ce:4*f* and ferromagnetic Mn moments, we have investigated a simultaneous and individual effects of hydrostatic pressure and magnetic field on the behavior of electrical resistance in $\text{La}_{0.1}\text{Ce}_{0.4}\text{Sr}_{0.5}\text{MnO}_3$ within a temperature range of 4.2 K – 300 K. We use this approach because our earlier ambient-pressure work clearly established that the resistivity features are correlated with magnetization and neutron diffraction data.^{7,8} From this study, we substantiate that the anomalous temperature dependence of electrical resistance is due to Kondo-like scattering of Mn:*e_g* electrons by localized Ce:4*f* moments. Further, we infer that there is a valence change of *cerium* under pressure from Ce^{3+} state to $\text{Ce}^{4+}/\text{Ce}^{3+}$ mixed valence state.

Polycrystalline sample of $\text{La}_{0.1}\text{Ce}_{0.4}\text{Sr}_{0.5}\text{MnO}_3$ was prepared by calcining stoichiometric mixtures of La_2O_3 , CeO_2 , SrCO_3 , Mn_2O_3 at 1100°C and sintering at 1500°C. Phase purity, nuclear and magnetic structures were determined by powder x-ray and neutron diffraction methods.⁸ The electrical resistance was measured by a standard four-probe method with a direct current of 1 mA down to 4.2 K. The electrical contact was made with a silver paint of heat treatment type. Hydrostatic pressure up to 2.1 GPa was generated by using a Cu-Be piston-cylinder device and 1:1 mixture of Fluorinert FC70 and FC77 as a pressure medium. The pressure was changed at RT to minimize internal strain in the specimen and the load was controlled to within $\pm 1\%$ through-

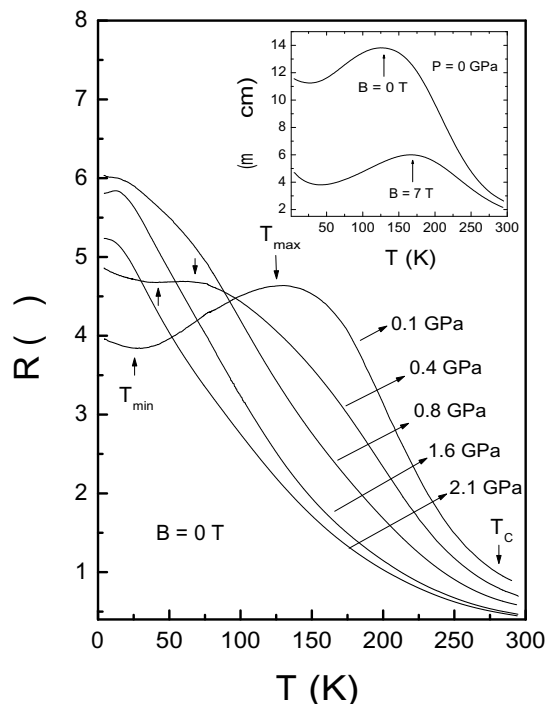


FIG. 1: Temperature dependence of the electrical resistance $R(T)$ of $\text{La}_{0.1}\text{Ce}_{0.4}\text{Sr}_{0.5}\text{MnO}_3$ at high pressures. The downward and upward arrows indicate T_{\max} and T_{\min} , respectively. T_C is nearly 280 K. Inset shows the shift of T_{\max} to a higher temperature under a magnetic field of 7 T and $P = 0$ GPa.

out the measurement. The magnetic field was applied by a superconducting magnet up to 9 T. The details of the present apparatus at multi-extreme conditions have been reported previously.¹⁰

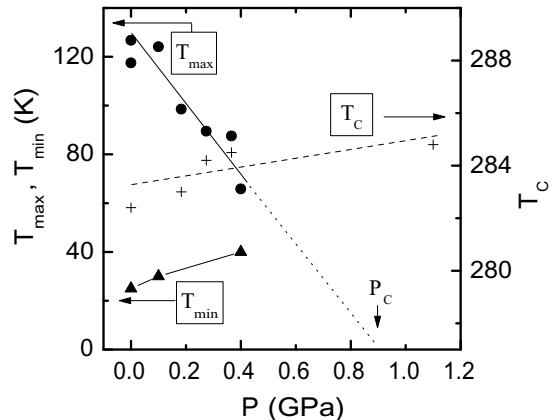


FIG. 2: Pressure dependence of T_{\max} and T_{\min} at $B = 0$ T as shown by solid circle and triangle, respectively. The solid, dashed and dotted lines are guides for the eye. P_C is the value of pressure corresponds to the extrapolation of T_{\max} to zero temperature.

Temperature dependence of electrical resistance at various pressures is shown in Fig. 1. In this figure, there is no indication for the DE ferromagnetic metallic transition near $T_C \sim 280$ K. However, we have already reported⁹ from the temperature derivative of R that, in this system, the T_C increases with pressure at a rate of $dT_C/dP = +1.9$ K/GPa, as shown in Fig.2. The small increase of T_C is consistent with the fact that this system is in a weak coupling region due to a large filling of conduction band, where the system is less sensitive to pressure or change in W .¹⁵ At 0.1 GPa, R increases logarithmically ($-\log T$) with decreasing temperature in the range $\sim 180 - 230$ K as shown by solid line in Fig. 3(a) and exhibits a broad maximum at about 130 K (T_{\max}) and a minimum at about 30 K (T_{\min}) which are shown by arrows in Fig.1. As discussed earlier,⁷ the T_{\max} is due to the onset of antiferromagnetic ordering of Ce^{3+} moments with respect to the ferromagnetic Mn moments. This $R(T)$ behavior is reminiscent of the typical concentrated Kondo compounds.^{12,13} However, the origin of T_{\max} in the present case should be compared and contrasted with the concentrated Kondo systems where the origin of resistivity maximum is due to crystal field effects and Kondo coherence, and the T_{\max} has a large positive pressure coefficient.^{13,14} Further, the decrease of resistivity below Ce ordering is not sharp such as one normally observes at a magnetic ordering of Ce in intermetallics. This is because, the antiferromagnetic coupling in the present system is between Ce and Mn moments and the antiparallel arrangement of Ce is induced by Mn moments.⁸ In fact, a recent theoretical analysis on this system reproduce the magnetic behavior of Mn and Ce in this system.¹⁶

In the present case, with increasing pressure, T_{\max}

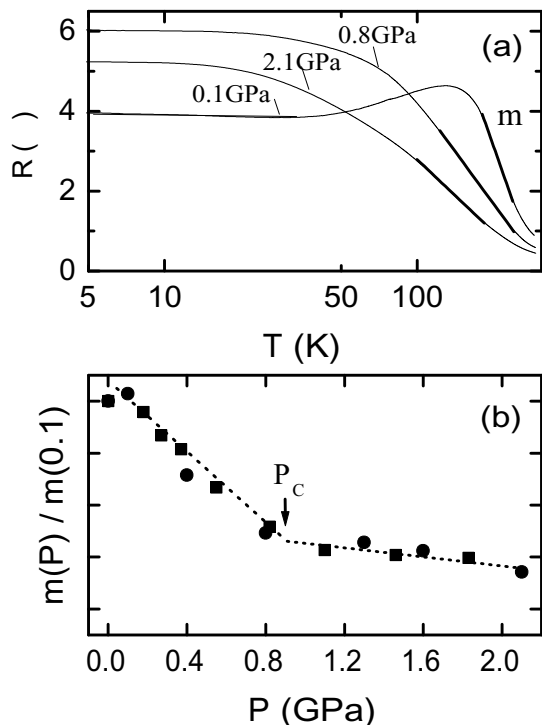


FIG. 3: (a) Temperature dependence of R , in which the abscissa is selected as a logarithmic scale and $-\log T$ dependence is shown by solid lines. (b) Pressure dependence of the normalized coefficient $m(P)/m(0.1)$ of $-\log T$ term. The previous data of $m(P)/m(0.1)$ ⁹ is described as closed circle. P_c is defined as an inflection point of the coefficient. The dotted and solid lines are guides for the eye.

shifts to a lower temperature at a rate of $dT_{max}/dP = -162$ K /GPa, which is in sharp contrast to the typical concentrated Kondo systems, for example, $CeAl_3$ or $CeInCu_2$ where the T_{max} increases with pressure.^{12,13} On the other hand, T_{min} seems to shift to higher temperature as shown in Fig. 2. At pressures higher than 0.8 GPa both T_{max} and T_{min} are not seen down to 4.2 K. It should be noticed from the Fig. 2 that the extrapolated value of pressure, where the T_{max} equals to zero, is 0.9 GPa, which we termed as critical pressure P_c . Since the T_{max} corresponds to the ordering temperature of *cerium*, the P_c might indicate the suppression of magnetic ordering of *cerium*. According to the effect of hydrostatic pressure on DE ferromagnetism,¹⁵ we would expect that the T_{max} associated with Ce ordering should increase with pressure. The observed decrease of T_{max} or the magnetic ordering temperature of *cerium* with increase of pressure rather indicates a valence change of *cerium* from Ce^{3+} towards Ce^{4+} state. In contrast to pressure effect, the application of magnetic field (B) shifts the T_{max} to higher temperature due to enhanced ferromagnetic Mn moments, as shown in the inset of Fig.1, for an applied field of 7 T. The presence of resistivity minimum in the vicinity of 25 K in manganites is well known and has been attributed to the effect of electron-electron interactions.¹⁷

It is intriguing and important to note the change of $R(T)$ at various pressures as a function of temperature (see Fig. 1). Near T_C , the decrease of R with increase of pressure is due to; (i) widening of e_g band as reported for $La_{1-x}Sr_xMnO_3$ ¹⁵ and (ii) valence change of *cerium* ion. On the other hand, at the lowest temperature measured (4.2 K), R increases with pressure up to 0.8 GPa, close to P_c , and then decreases with further increase of pressure. Since the pressure effect on the DE ferromagnet with larger W does not have any contribution to R at low temperatures, the increase of R suggests that the strength of J , the exchange integral, which depends on the hybridization between the conduction electron and f -electron, increases with pressure. The decrease of R above P_c may be due to decrease of T_{max} . In the intermediate region ($90 \leq T \leq 250$) the large decrease of R with increase of pressure is mainly due to suppression of spin dependent scattering that results from the valence change of *cerium*. The fact that the $R(T)$ does not become a metallic like even at 2.1 GPa suggests that the *cerium* has not completely changed to Ce^{4+} state and rather exists in Ce^{4+}/Ce^{3+} mixed valence state. Fig.3a, shows variation of R at various pressures as a function of temperature in logarithmic scale. It can be seen that there is a region of $-\log T$ dependence of R at high temperatures (> 100 K) as shown by solid line at all pressures. This is a signature of Kondo scattering of conduction electrons by the localized moments. The coefficients of $-\log T$ term is termed as m . In Fig.3b, normalized coefficient $m(P)/m(0.1)$ is plotted as a function of pressure, where $m(P)$ is defined as $m = -\partial R / \partial \log T$, and $m(0.1)$ is that at 0.1 GPa. The coefficient, $m(P)/m(0.1)$ decreases linearly with increase of pressure because of the change in valence state of *cerium* as discussed above. This behavior is also different qualitatively from that of the typical Kondo compounds.¹⁴ Near $P_c \sim 0.9$ GPa, a small inflec-

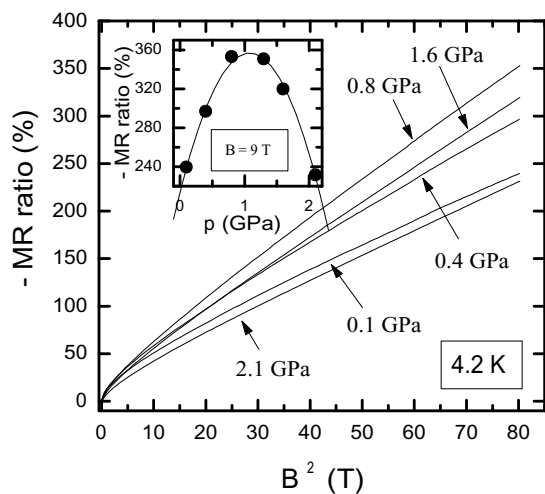


FIG. 4: Pressure dependence of negative MR ratio ($=\Delta R/R(B) \times 100$ %) at 4.2 K. The MR ratio at 9 T is plotted in the inset as a function of pressure. A solid curve is guide for the eye.

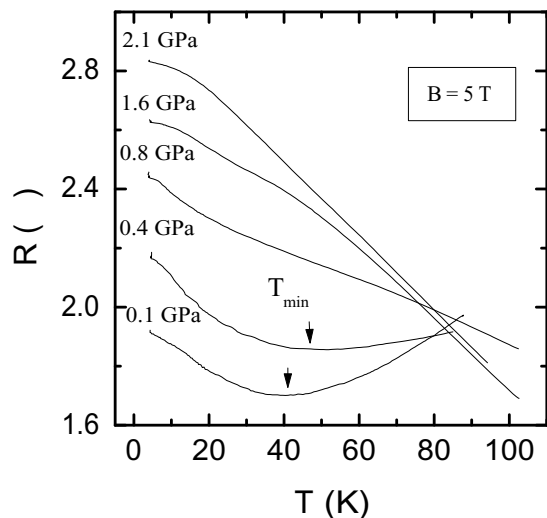


FIG. 5: Pressure dependence of $R(T)$ at magnetic field of 5 T. It can be seen that R at 4.2 K increases monotonically with pressure contrary to zero applied field (see Fig. 1).

tion is seen and above which the effect of pressure on m becomes smaller, indicating a decrease in the strength of the Kondo scattering above P_c . This is consistent with the observation that the T_{max} disappears at P_c , where one would expect a change in the interaction between the Ce:4*f* local and the conduction electron moments.

Magnetoresistance (MR) ratio ($\Delta R/R(B) = (R(0) - R(B))/R(B)$) at various pressures at 4.2 K is plotted as a function of B^2 in Fig. 4. The negative CMR effect in perovskite manganese oxides is well known as reported in previous experiments². In the present experiment, the negative MR monotonically increases with applying B which is mainly due to suppression of Kondo-like scattering and a small contribution from grain boundary scattering, as the DE interactions in large W materials re-

sults in MR effect only near T_C .⁷ Above 5 T, MR linearity increases with respect to B^2 , revealing the existence of spin-dependent scattering. The inset shows MR ratio at 4.2 K and at a field of 9 T as a function of pressure: MR increases with pressure and a peak is clearly seen near $P_c \sim 0.9$ GPa. This is consistent with the observation that the pressure dependence of R at 4.2 K has similar behavior, indicating the electronic changes associated with the valence change of *cerium*.

The pressure dependence of $R(T)$ ($T < 100$ K) under a magnetic field of $B = 5$ T is shown in Fig. 5. By applying 5 T, T_{min} shifts from 30 K to 40 K at 0.1 GPa. This phenomenon was explained by the enhancement of *cerium* ordering induced by the ferromagnetic manganese moments⁷. In contrast to zero applied field, R at 4.2 K and 5 T increases with increasing pressure without showing any maximum in the present pressure range. It is possible that P_c exceeds the maximum pressure limit in our experiment because the ordering temperature of *cerium* increases with applied magnetic field.⁷ T_{min} increases with pressure similar to that observed under zero field as shown Fig. 2. It would be interesting to carry out neutron diffraction experiment under pressure to see the changes in the ordering temperature of *cerium*.

In conclusion, we have found that under zero applied magnetic field, the T_{max} due to magnetic ordering of *cerium* and normalized coefficient of $-\log T$ term, $m(P)/m(0.1)$ originated from Kondo-like scattering of conduction electrons decrease with increasing pressure. Further, the T_{max} disappear at a critical pressure ($P_c \sim 0.9$ GPa) where there is a corresponding change in the slope of the coefficient of the $-\log T$ term, indicating a decrease in the strength of the Kondo-like scattering. The suppression of T_{max} has been attributed to a valence change of *cerium* from Ce^{3+} state to Ce^{4+}/Ce^{3+} mixed valence state under pressure.

* Electronic address: sundaresan@jncasr.ac.in
¹ Colossal Magnetoresistance, Charge Ordering and Related Properties of Manganese Oxides, edited by C. N. R. Rao and B. Raveau (World Scientific, Singapore, 1998).
² A. P. Ramirez, J. Phys. Cond. Matter. **9**, 8171 (1997), and references therein.
³ G. H. Jonker, Physica (Amsterdam) **XVI**, 337 (1950).
⁴ C. Zener, Phys. Rev. **82**, 403 (1951).
⁵ P. W. Anderson and H. Hasegawa, Phys. Rev. **100**, 675 (1955).
⁶ P. -G. de Gennes, Phys. Rev. **118**, 141 (1955).
⁷ A. Sundaresan, V. Caignaert, A. Maignan, B. Raveau, E. Suard, Phys. Rev. **B60**, 533 (1999).
⁸ A. Sundaresan, J. L. Tholence, A. Maignan, B. Raveau, E. Suard, P. Bordet, J. Magn. Magn. Mater. **226-230**, 777 (2001).
⁹ T. Eto, G. Oomi, F. Honda, A. Sundaresan, J. Magn. Magn. Mater. **226-230**, 879 (2001).
¹⁰ F. Honda, S. Kaji, I. Minamitake, M. Ohashi, G. Oomi, T.

Eto, and T. Kagayama, J. Phys. Cond. Matter. **14**, 11501 (2002).
¹¹ F. Hanzawa, K. Yamada, K. Yoshida, J. Magn. Magn. Mater. **47 & 48**, 357 (1985).
¹² T. Kagayama, G. Oomi, H. Takahashi, N. Mōri, Y. Ōnuki, T. Komatsubara, Phys. Rev. **B44**, 7690 (1991).
¹³ T. Kagayama, G. Oomi, J. Phys. Soc. Jpn. **65**, Suppl. B 42 (1996).
¹⁴ G. Oomi, T. Kagayama, Y. Ōnuki, H. Mitamura, T. Goto, Proc. Moscow Inter. Sympo. Magn (MISM'99), 351 (1999).
¹⁵ Y. Moritomo, A. Asamitsu, and Y. Tokura, Phys. Rev. B **51**, 16491 (1995).
¹⁶ G. Martinez, J. R. Iglesias, A. R. Ruppenthal, J. M. Avignon, C. Lacroix, J. Magn. Magn. Mater. **226-230**, 214 (2001).
¹⁷ D. Kumar, J. Sankar, J. Narayan, Rajiv K. Singh, A. K. Majumdar, Phys. Rev. B **65**, 94407 (2002).