

Shifting of the magnetic resonance peak to lower energy in the superconducting state of underdoped $\text{YBa}_2\text{Cu}_3\text{O}_{6.8}$

P. Bourges¹, L.P. Regnault², Y. Sidis¹, J. Bossy³, P. Bulet²,
C. Vettier⁴, J.Y. Henry² and M. Couach²

- (1) Laboratoire Léon Brillouin, CEA-CNRS, CE Saclay, 91191 Gif sur Yvette, France
- (2) CEA Grenoble, Département de Recherche Fondamentale sur la matière Condensée, 38054 Grenoble cedex 9, France
- (3) Institut Laue-Langevin, 156X, 38042 Grenoble Cedex 9, France
- (4) European Synchrotron Research Facility, BP 220, 38043 Grenoble cedex, France

Abstract. - Inelastic neutron scattering has been used to determine the dynamic spin fluctuations in an underdoped high temperature superconductor $\text{YBCO}_{6.8}$ single crystal. The magnetic resonance, that occurs around 40 meV in overdoped samples, is shifted to a lower energy, $E_r = 34$ meV. A constant ratio, $E_r/k_B T_C = 4.9 \pm 0.2$, almost independent of the doping level, is found. According to numerous theoretical approaches, this finding supports the idea that the resonance energy is proportional (approximately twice) to the superconducting gap.

74.20.Mn Nonconventional mechanisms (spin fluctuations, polarons, and bipolarons, resonant valence bond model, anyon mechanism, marginal Fermi liquid, Luttinger liquid, etc.)

25.40.Fq Inelastic neutron scattering

74.72.Bk Y-based cuprates

The electronic correlations in high- T_C superconductors are crucial in understanding normal as well as superconducting (SC) properties. They have been experimentally evidenced by the persistence of spin fluctuations in the metallic state of cuprates. Especially, inelastic neutron scattering (INS) experiments have allowed to investigate the wavevector, energy and the doping dependencies of the imaginary part of the generalized magnetic susceptibility ($Im\chi$) on a unique sample of $\text{YBa}_2\text{Cu}_3\text{O}_{6+x}$ (YBCO) in its metallic state[1, 2, 3]. First, $Im\chi$ is still located at the antiferromagnetic (AF) wavevector, $Q_{AF} = (1/2, 1/2, q) \equiv (\pi, \pi)$. Second, in the SC state, when going from the weakly-doped regime $x \simeq 0.5$ to fully oxidized sample $x \simeq 1$ [3], $Im\chi$ is gradually restricted to a smaller energy range. It is shifted to higher energies with increasing x by a doping dependant energy gap[1, 2, 3, 4], called *spin-gap*. In optimally doped samples and overdoped samples ($x \geq 0.94$), it is now well established that a strong sharp magnetic peak appears around 40 meV, called *resonance* by J. Rossat-Mignod *et al*[1] for its first evidence. Its magnetic origin has been then confirmed by using polarized neutron scattering[5]. Its major characteristic is that it disappears above T_C [1, 3, 4, 6]. This peak also occurs in $Im\chi$ in addition to another contribution which stands in the normal state[1, 3]. However, this part of $Im\chi$ is so reduced with increased doping[3, 4] that it becomes hardly detectable[4, 6, 7] in fully oxidized samples.

The origin of this magnetic resonance has been extensively discussed, especially in itinerant magnetism descriptions[8, 9, 10, 11, 12, 13, 14]. Beyond all the different hypotheses in these approaches, one can basically consider that an enhancement of the electronic spin susceptibility arises at a specific energy due to the opening of the SC gap. This is usually argued to support a $d_{x^2-y^2}$ symmetry for the SC order parameter, Δ_k [8, 9, 10, 11, 12, 13, 15], ruling

out other symmetries[11] like extended s-wave[12]. For others[14], the neutron data indicate that Δ_k has a s-wave symmetry and opposite signs in bounding and antibounding electron bands formed within the $(\text{CuO}_2)_2$ bilayer. More particularly, a resonance peak may occur i) due to a dynamic nesting[8], ii) as a consequence of van Hove singularity in the electronic density of states (DOS)[9], iii) because of a collective mode in the particle-particle channel in the Hubbard model[10]. Other approaches propose that this resonance results from spin-flip charge carriers excitations across the SC gap[11, 12, 13, 14, 15]. In this view, the resonance energy, E_r , closely reflects the amplitude of the SC gap as well as its doping dependence. However, the behaviour of the resonance peak in the underdoped regime remains unclear. So far, only short reports of a previous investigation at $x \simeq 0.83$ [2, 3] have emphasized that crucial point.

In this letter, we establish that, for an underdoped sample exhibiting a $T_C = 82$ K, the magnetic resonance peak is shifted to $E_r = 34$ meV. This energy leads to a resonance energy and T_C ratio which is almost the same as in optimally doped and overdoped samples, $E_r/k_B T_C = 4.9 \pm 0.2$. It confirms the following picture in which the resonance energy seen in INS experiments actually measures the amplitude of the SC gap.

The sample used in which the oxygen content can be changed was the same as in our previous investigations[1, 2, 3]. It has been prepared by heat treatment to achieve a nominal oxygen content $x = 0.8$. Macroscopic susceptibility measurements have been performed to determine T_C : when applying a small magnetic field ($H=0.1$ Oe), an onset superconducting transition temperature occurs at 87 K (midpoint at 82 K). A small amount of the 60 K- T_C phase (≤ 10 %) can be estimated from these measurements.

Unpolarized inelastic neutron scattering experiments have been performed on the triple axis IN8 at the Institut Laue Langevin (ILL-Grenoble). Cu111 reflection was chosen as monochromator and horizontally focussed pyrolytic graphite PG002 as analyzer. We worked without collimators except between the analyser and the detector, where a 60' Soller slit has been put to reduce the background level. A pyrolytic graphite filter was placed in the scattered beam to avoid higher order contaminations in k_F -fixed mode. The sample was mounted inside an orange-type cryostat in the scattering plane usual in such investigations[4] where the (110) and (001) directions are lying within the horizontal plane. We have worked with a final wavevector $k_F = 4.1 \text{ \AA}^{-1}$, yielding a full width at half maximum (FWHM) of the resolution along the (110) direction (see Fig. 2.b.) of $\Delta^{resol} q \simeq 0.1$ r.l.u. for energy transfers of interest, $\hbar\omega \simeq 35$ meV. It yields an energy resolution width of 4.7 meV also for $\hbar\omega \simeq 35$ meV. As we have to measure a broad in q-space but sharp in energy signal, such a spectrometer resolution is particularly well adapted.

The major experimental problem encountered in such INS experiments is the extraction of the magnetic contribution from the scattering arising from the nuclear lattice: There is no unambiguous determination of the energy dependence of $Im\chi$ over a wide range of energy. For instance, the use of polarized neutron[5] has even led to spurious effects like the persistence of the resonance peak in the normal state. All unpolarized[1, 2, 3, 4, 6, 7] neutron measurements have shown its disappearance above T_C . However, few complementary methods as well as the accumulation of neutron data allow to solve the experimental problem[3, 4, 5, 6, 7]. The major criteria to determine the magnetic signal are the dependencies of the measured intensities on the wavevector as well as the temperature[3, 4, 7]. Therefore, we performed q-scans along the (110) direction with as many fixed energy transfers as possible. The q_l value along the (001) direction was chosen to get the maximum of the magnetic structure factor (q_l -dependence is reported in Ref. [7]). For instance, Fig. 1.a displays the neutron intensity obtained at $\hbar\omega = 35$ meV and $q_l = 5.2$. It shows a well-defined maximum at $q = 0.5$, corresponding to the AF wavevector (π, π) , at all temperatures investigated from 4 K up to 200 K. However,

the correlated signal significantly decreases with heating. Q-scans having similar \mathbf{q} - and T-dependencies have been performed at few other energy transfers. At 39 meV (for details see [7]), correlated intensity is reduced on increasing the scattering wavevector \mathbf{Q} , according to the expected magnetic form factor of copper spins. Magnetism is indeed known to decrease on increasing \mathbf{Q} in contrast to the scattering arising from phonons[16]. Such a wavevector and temperature dependencies demonstrate the magnetic origin of this signal.

The next step is to determine the energy profile of the spin susceptibility. Schematically, the energy scan performed at the AF wavevector is the sum of nuclear and magnetic contributions, and then consists of three terms as:

$$I(Q_{AF}, \omega) = A + I_{nuclear}(\omega) + I_{magnetic}(\omega) \quad (1)$$

where A is a constant independent of T and ω . Both, nuclear and magnetic contributions follow temperature population factor according to the detailed balance[16]:

$$\begin{aligned} I_{nuclear}(\omega) &= B(\omega)\{1 + n(\omega, T)\} \\ I_{magnetic}(\omega) &= Im\chi(Q_{AF}, \omega)\{1 + n(\omega, T)\} \end{aligned} \quad (2)$$

Because the spin fluctuations contribution at 200 K is weak (see for instance Fig. 1.a), the energy scan performed at the AF wavevector, $Q_{AF}=(0.5,0.5,5.2)$, mainly reflects, at that temperature, the shape and the amplitude of the nuclear contributions, $B(\omega)$. Then, the q-scans performed at few constant energies crosscheck that determination and allow to take into account weak 200 K magnetic contribution in a self-consistent way. Once this nuclear part, $B(\omega)$, has been determined, the magnetic part, $Im\chi(Q_{AF}, \omega)$, is then simply obtained by difference (Eqn. (1)) and temperature correction (Eqn. (2)).

As shown in Fig 2.a, the spin susceptibility is spread over a wide energy range. This is in contrast with the overdoped regime, in which $Im\chi(Q_{AF}, \omega)$ is restricted to a narrow energy range around 40 meV[3, 4, 6]. However, $Im\chi$ is characterized by a clear maximum at 34 meV which might be a resonance peak. We have fitted the q-scans performed at different energy transfer by a simple Gaussian lineshape. The deduced q-width, Δq , is reported in Fig 2.b versus energy. Magnetic correlations amplitude is maximum (Fig. 2.a) when they are sharper in q-space (Fig. 2.b). Δq displays a minimum around 35 meV, $\Delta q= 0.14$ r.l.u., which is still significantly broader than the resolution width. In YBCO_{6.97}[4], similar energy dependence and values of Δq have been found between 35 meV and 45 meV. In terms of correlation lengths, it yields $\xi_{E_r} = 10$ Å after a proper deconvolution from the spectrometer resolution. Actually, such a characteristic length associated with the resonance is found to be independent from the doping[3]. Fig. 3 compares the temperature dependence of the neutron intensity obtained at 35 meV and at 39 meV. A change in the slope is observed at T_C at the former energy whereas only a smooth behaviour is found at the latter energy. Such a temperature dependence of the 34 meV peak also indicates its resonating nature. Therefore, disappearing above T_C (Fig. 2.a), the 34 meV peak in underdoped YBCO_{6.8} has the same physical origin as the magnetic resonance peak around 40 meV in optimally and overdoped samples, i.e. for $x \geq 0.92$ [1, 3, 4, 5, 6].

Apart from the resonance peak, $Im\chi(Q_{AF}, \omega)$ displays other important features. It is limited at low energy by a spin gap defined by the inflexion point at $E_G = 20$ meV. Between this energy gap and the resonance peak, there is a plateau at 25 meV (Fig. 2.a). This part of $Im\chi$ is evidenced by the temperature dependence of the q-scan (Fig. 1.b). This plateau is characterized by a q-width different from the one of the resonance peak (Fig. 2.b). From the energy dependence of Δ_q , the plateau extends to higher energies, i.e. above E_r . This

correlated magnetic signal clearly remains up to the highest investigated energy, 55 meV. In contrast, no magnetic fluctuations were sizeable at 47 meV in overdoped YBCO_{6.97}[4]. The amplitude of this non-resonant contribution for energies around E_r might be suggested by continuity (dashed lines in Fig 2.a and in Fig. 3). However, only quantitative models allow to correctly distinguish the resonance intensity from this second contribution. After a Gaussian deconvolution of the q-width, this plateau can be associated with an AF correlation length, $\xi_{AF} = 5 \pm 1 \text{ \AA}$, twice smaller than the one related to the resonance[3]. It is worth noting that non-negligible magnetic fluctuations corresponding to the non-resonant part clearly remain in the normal state at all energies investigated (Fig. 2). Actually, the vanishing of the normal state spin fluctuations (which might be due to experimental limitations) only occurs in the overdoped regime[4, 6]. This has led to controversies in the literature.

Our results demonstrate that the resonance peak is shifted to lower energy in the underdoped regime. From the temperature dependence at 39 meV (Fig. 3.b), its occurrence around 40 meV is ruled out. Almost independently of the doping, the resonance energy and T_C are barely proportional to each other[18] as $E_r/k_B T_C = 4.9 \pm 0.2$. This mean ratio also stands for overdoped samples in which both T_C and E_r are slightly renormalized (from $E_r = 41$ meV for optimally doped samples $x \simeq 0.93$ to 39 meV for YBCO₇)[3]. According to numerous calculations[11, 12, 13, 14, 15], the resonance energy corresponds to roughly twice the SC energy gap ($2 \Delta_{max}$ for a $d_{x^2-y^2}$ -wave symmetry), i.e. E_r would approximately be the energy necessary to break a Cooper pair. However, accurate calculations taking into account realistic electronic bands show that this proportionality factor between E_r and Δ_{max} should be renormalized to smaller values[12, 13, 15, 17], and that it might also be slightly doping dependent[17].

Furthermore, the doping dependence of the characteristic magnetic resonance peak energy, E_r , enlightens why the well-known anomalous behaviour of the 340 cm^{-1} B_{1g} phonon measured in Raman scattering[19] occurs only in fully oxygenated samples[20]. Indeed, the phonon softening and broadening (abruptly occurring just below T_C) are currently interpreted in terms of a coupling of phonons with the electronic bath responsible of the superconductivity. Consequently, only phonons whose frequency is located close to $2\Delta_{max}$ (the SC gap has been estimated[19] to be $2\Delta = 316 \text{ cm}^{-1} = 39.2 \text{ meV}$ for YBCO₇) should display marked modifications at T_C . As discussed above, the resonance peak energy also probes the SC gap. Noticing the slight renormalization of its energy when increasing the doping, this implies a shift of the SC gap, and consequently, the vanishing of the phonon anomaly in non fully oxygenated samples due to its extreme sensitivity with the frequency[19].

Finally, our results show that the neutron magnetic resonance peak is shifting to lower energies in YBCO_{6.8} ($T_C = 82 \text{ K}$). However, a large part of $Im\chi$ remains in the normal state in this underdoped sample. The SC transition temperature does not affect this contribution. Then, the simple itinerant pictures described above cannot account for the complex behaviour of the spin susceptibility in cuprates. Other approaches involving the localized-itinerant duality of the magnetism, as in the framework of the t - t' - J model[15], have to be considered.

ACKNOWLEDGEMENTS

We kindly acknowledge the technical support of ILL, and especially D. Puschner. We also thank H.F. Fong, B. Hennion, B. Keimer, L. Manificier, I. Mazin and F. Onufrieva for enlightening discussions and/or critical reading of the manuscript.

References

- [1] J. Rossat-Mignod *et al*, *Physica C*, **185-189**, 86 (1991).
- [2] J. Rossat-Mignod *et al*, *Physica B*, **199&200**, 281 (1994).
- [3] L.P. Regnault *et al*, *Physica C*, **235-240**, 59, (1994); P. Bourges *et al*, *Physica B*, **215**, 30, (1995).
- [4] P. Bourges, L.P. Regnault, Y. Sidis, and C. Vettier, *Phys. Rev. B*, **53**, 876, (1996).
- [5] H.A. Mook *et al*, *Phys. Rev. Lett.*, **70**, 3490 (1993);
- [6] H. F. Fong *et al*, *Phys. Rev. Lett.*, **75**, 316 (1995).
- [7] P. Bourges *et al*, *J. of Low Temp. phys.*, **105**, 377 (1996).
- [8] S.V. Maleyev, *J. Phys. I. France*, **2**, 181 (1992); S. Charfi-Kaddour *et al*, *J. Phys. I. France*, **2**, 1853 (1992); J. P. Lu, *Phys. Rev. Lett.*, **68**, 125 (1992). N. Bulut *et al*, *Phys. Rev. B*, **53**, 5149 (1996).
- [9] M. Lavagna *et al*, *Phys. Rev. B*, **49**, 4235 (1994); G. Blumberg *et al*, *Phys. Rev. B*, **52**, R15741 (1995).
- [10] E. Demler, and S.C. Zhang, *Phys. Rev. Lett.*, **75**, 4126 (1995);
- [11] Y. Ohashi *et al*, *J. Phys. Soc. Jpn.*, **62**, 2783 (1993); P. Monthoux *et al*, *Phys. Rev. Lett.*, **72**, 1874 (1994).
- [12] F. Onufrieva, *Physica C*, **251**, 348, (1995).
- [13] D.Z. Liu, Y. Zha, and K. Levin, *Phys. Rev. Lett.*, **75**, 4130 (1995).
- [14] I.I. Mazin, and V. M. Yakovenko, *Phys. Rev. Lett.*, **75**, 4134 (1995).
- [15] F. Onufrieva *et al*, *Physica C*, **235-240**, 1687 (1994); *Phys. Rev. B*, **52**, 7572 (1995).
- [16] S.W. Lovesey, *Theory of Neutron Scattering from Condensed Matter*, Vol 2, (Clarendon, Oxford, 1984).
- [17] F. Onufrieva, S. Petit, and Y. Sidis, *Physica C*, **266**, 101 (1996); *Phys. Rev. B*, **54**, (1996); *J. of Low Temp. phys.*, **105**, 597 (1996).
- [18] Similar data have been very recently reported by P. Dai *et al*, *Phys. Rev. Lett.*, **77**, 5425 (1996) and H.F. Fong *et al*, *Phys. Rev. Lett.*, **78**, 713 (1997) which supports that conclusion.
- [19] See e.g. B. Friedl, C. Thomsen, and M. Cardona, *Phys. Rev. Lett.*, **65**, 915 (1990).
- [20] E. Altendorf *et al*, *Phys. Rev. B*, **47**, 8140 (1993).

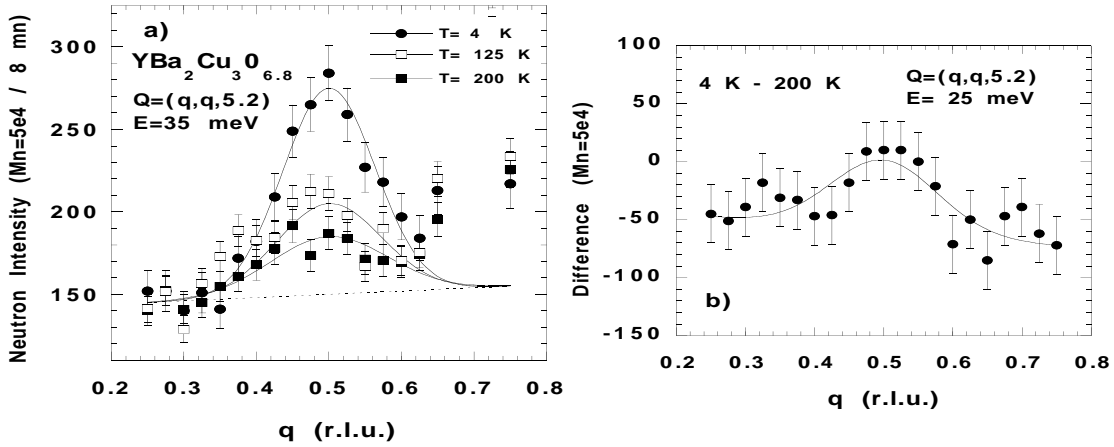


Figure 1: a) Q-scans across the magnetic line at an energy transfer of 35 meV at different temperatures. Data reported at 125 K have been measured independently at 100 K and 150 K, and then summed up to improve statistics. At 200 K, 20 counts have been subtracted at each point to scale the background to the scans measured at lower temperature. The higher intensities located around $q=0.7$ correspond to a well-known accidental Bragg peak scattering[4]. b) Difference of q-scans measured at $\hbar\omega = 25$ meV between 4 K and 200 K. The full lines correspond to a fit to a Gaussian lineshape $I(Q, \omega) = \text{Im}\chi(Q_{AF}, \omega)\{1 + n(\omega, T)\} \exp(-4 \ln 2 \left(\frac{q - q_{AF}}{\Delta_q}\right)^2)$ with $q_{AF} = 0.5$ above a sloping background (dashed line).

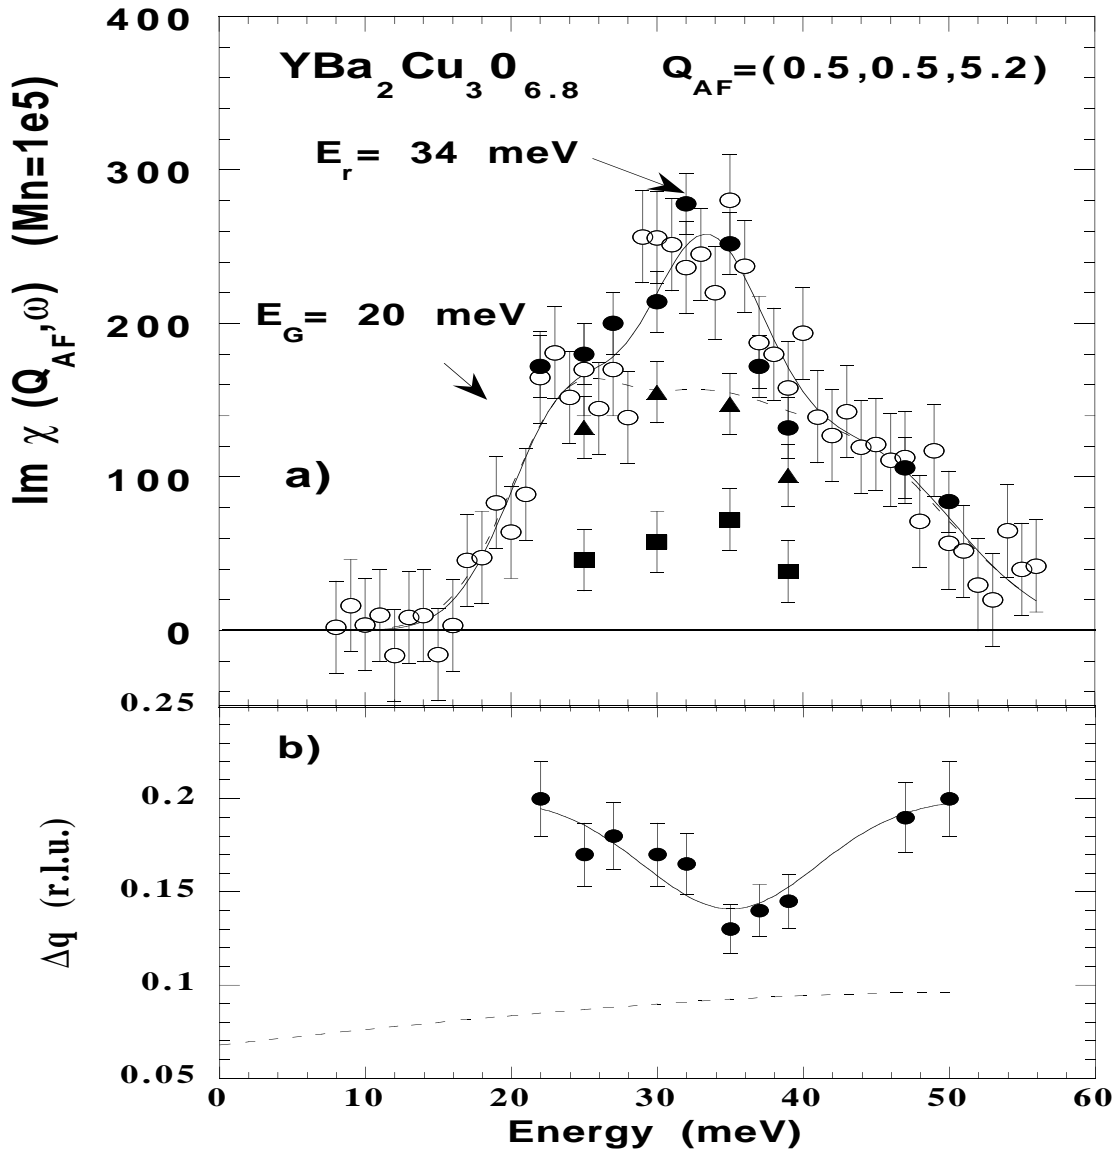


Figure 2: a) $\chi''(Q_{AF}, \hbar\omega)$ at different temperature: circles at 4 K (SC state), triangles at 100 K (normal state) and squares at 200 K. Closed symbols have been obtained from q-scans (as in Fig. 1) at each energy. b) FWHM q-width, Δq , in the (110) direction from a Gaussian fit of q-scans. The resolution q-width is represented by the dashed line. Other lines are guides to the eye.

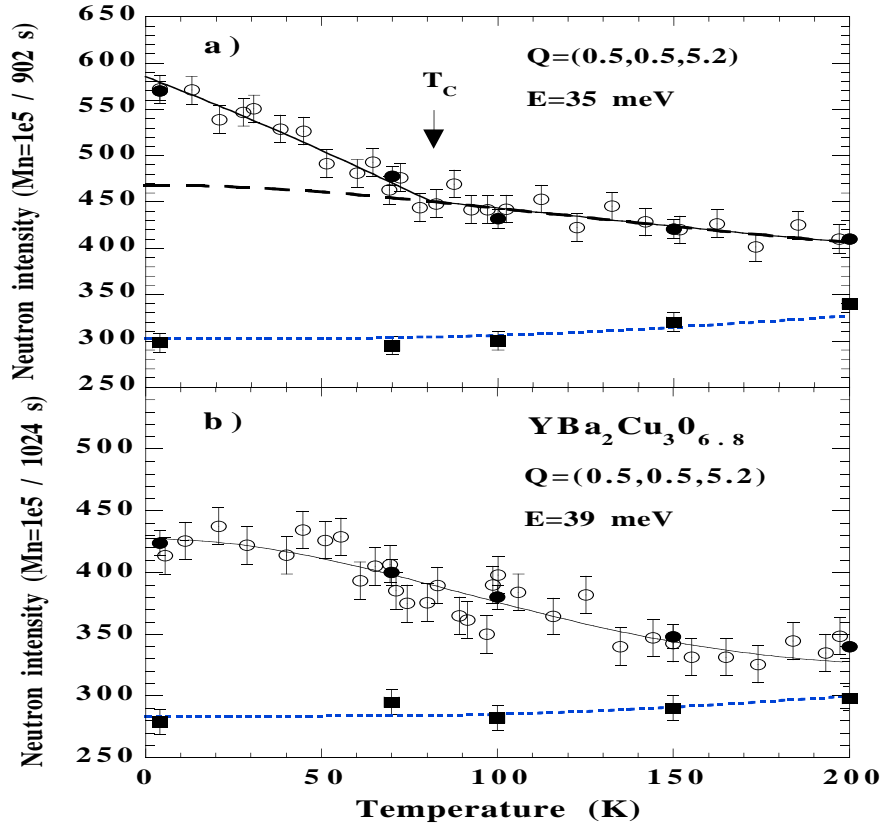


Figure 3: Temperature dependence of the neutron intensity at two energies (circles). Closed circles have been obtained from q-scans (as in Fig. 1) at each energy whereas squares display the background deduced from them. Dotted lines correspond to a fit of the nuclear contributions by $I_{nuclear} = A + B(\omega)\{1 + n(\omega, T)\}$. The full lines are guides to the eye.