

Twin Boundaries in d -wave Superconductors

D.L. Feder, A. Beardsall, A.J. Berlinsky, and C. Kallin

Department of Physics and Astronomy, McMaster University, Hamilton, Ontario L8S 4M1, Canada
(October 9, 2018)

Twin boundaries in orthorhombic d -wave superconductors are investigated numerically using the Bogoliubov-deGennes formalism within the context of an extended Hubbard model. The twin boundaries are represented by tetragonal regions of variable width, with a reduced chemical potential. For sufficiently large twin boundary width and change in chemical potential, an induced s -wave component may break time-reversal symmetry at a low temperature T^* . The temperature T^* , and the magnitude of the complex component, are found to depend strongly on electron density. The results are compared with recent tunneling measurements.

61.72.Mm, 74.20.-z, 74.50.+r, 74.72.Bk

In spite of mounting experimental evidence that the high-temperature superconductors have an order parameter with $d_{x^2-y^2}$ (d -wave) symmetry,¹ a number of experiments on both twinned and untwinned YBa₂Cu₃O_{7- δ} (YBCO) suggest the presence of an additional s -wave order parameter.^{2,3} By symmetry, a small s -wave component always coexists with a predominantly d -wave order parameter in an orthorhombic superconductor such as YBCO, and changes its sign (relative to the d -wave component) across a twin boundary.⁴ The experimental results can be understood either if the s -wave component of the order parameter breaks time-reversal (\mathcal{T}) symmetry near the twin boundary at low temperatures, as it can near surfaces,⁵⁻¹⁰ or if there is far more of one kind of twin domain (i.e. twin boundaries form in groups).^{11,12} Recent SQUID measurements on vortices trapped by twin boundaries in YBCO did not detect the fractional flux that would accompany local \mathcal{T} -violation.¹³ In the present work, however, we present strong evidence that such a symmetry breaking could indeed occur in the vicinity of twin boundaries at low temperatures under certain conditions.

Sigrist *et al.*⁷ have addressed the possibility of \mathcal{T} -violation near boundaries by considering the Ginzburg-Landau (GL) free energy for a homogeneous orthorhombic d -wave superconductor:

$$F_s = F_n + \alpha_d |d|^2 + \alpha_s |s|^2 + \beta_1 |d|^4 + \beta_2 |s|^4 + \beta_3 |s|^2 |d|^2 + \beta_4 (s^* d^2 + s^2 d^{*2}) + \beta_5 (s^* d + s d^*), \quad (1)$$

where s and d are the s -wave and d -wave components of a superconducting order parameter of the form $d + e^{i\theta} s$, with θ the relative phase between s and d . Only the lowest-order orthorhombic term is kept in the GL free energy since $s \ll d$ for small β_5 . Assuming all the coefficients are positive (except α_d), the β_5 term favors $\theta = n\pi$ (n integer), while the β_4 term favors $\theta = \pi/2$. Thus, in a tetragonal superconductor there can be a continuous transition to a bulk \mathcal{T} -violating phase at a temperature T^* given by $\alpha_s(T^*) = [2\beta_4(T^*) - \beta_3(T^*)] d^2(T^*)$.⁸ The coefficients of the GL free energy can be chosen such that $T^* \leq 0$ for a uniform system; the orthorhombic term further discourages a positive T^* . Yet the suppression of

d near an inhomogeneity, or the presence of a tetragonal region within an orthorhombic system, could induce local \mathcal{T} -violation for a finite temperature $0 \leq T \leq T^*$. Furthermore, the associated complex s -wave component could be large relative to $|d|$, and would vary on a new length scale.⁷ In contrast, an s -wave component nucleated solely through spatial variations of d , such as is found in magnetic vortices^{14,15} or near impurities,¹⁶ is usually small relative to $|d|$ (unless $\alpha_s \rightarrow 0$, which only occurs for densities just above a crossover to bulk s -wave superconductivity¹⁷) and varies on a length scale of the d -wave coherence length.

It is not clear, however, whether GL theory (which is strictly valid only near the bulk superconducting transition temperature) can reliably describe the low-temperature regime associated with \mathcal{T} -violation. In the present work, twin boundaries in d -wave superconductors are investigated numerically using Bogoliubov-deGennes theory. We employ an extended Hubbard model which gives rise to d -wave superconductivity in a restricted parameter regime.¹⁸ Despite its simplicity, results obtained previously using this model^{19,20} are consistent with those obtained within the context of a model better representing the high- T_c oxides,^{17,21} and with experimental results.^{22,23} Twin boundaries are modeled as tetragonal regions of varying widths and reduced chemical potential, in order to approximate the experimental observations that twin boundaries are oxygen-deficient (i.e. locally antiferromagnetically insulating) regions, generally 7-40Å wide.²⁴

The Hamiltonian for the extended Hubbard model is:

$$H = - \sum_{\langle ij \rangle \sigma} t_{ij} c_{i\sigma}^\dagger c_{j\sigma} - \mu \sum_{i\sigma} n_{i\sigma} - \sum_{i\sigma} \mu_i^I n_{i\sigma} - V_0 \sum_i n_{i\uparrow} n_{i\downarrow} - \frac{V_1}{2} \sum_{\langle ij \rangle \sigma \sigma'} n_{i\sigma} n_{j\sigma'}, \quad (2)$$

where the sums are over spin and nearest-neighbors on the square lattice, t_{ij} is a direction-dependent hopping parameter used to model orthorhombicity, μ is the chemical potential, μ^I is a site-dependent impurity potential representing the depletion of the carrier density at the

twin boundary, and V_0 and V_1 are on-site and nearest-neighbor interactions, respectively ($V > 0$ denotes attraction). Choosing the unit cell as shown in Fig. 1, we can exploit the translational invariance of the Hamiltonian in the (110) direction. With $\hat{R} \equiv \hat{x} + \hat{y}$ parallel and $\hat{r} \equiv -\hat{x} + \hat{y}$ perpendicular to the twin direction, we obtain the Bogoliubov-deGennes (BdG) equations:

$$\begin{pmatrix} \hat{\xi} & \hat{\Delta} \\ \hat{\Delta}^* & -\hat{\xi} \end{pmatrix} \begin{pmatrix} u_{n,k}(r_\alpha) \\ v_{n,-k}(r_\alpha) \end{pmatrix} = \varepsilon_{n,k} \begin{pmatrix} u_{n,k}(r_\alpha) \\ v_{n,-k}(r_\alpha) \end{pmatrix}, \quad (3)$$

such that

$$\begin{aligned} \hat{\xi} u_{n,k}(r_\alpha) &= - \sum_{\hat{\delta}} t_{\hat{\delta}} u_{n,k}(r_\alpha + \hat{\delta}) \\ &\quad - [\mu + \mu^I(r_\alpha)] u_{n,k}(r_\alpha), \end{aligned} \quad (4)$$

$$\begin{aligned} \hat{\Delta} u_{n,k}(r_\alpha) &= \Delta_0(r_\alpha) u_{n,k}(r_\alpha) \\ &\quad + \sum_{\hat{\delta}} \Delta_{\hat{\delta}}(r_\alpha) u_{n,k}(r_\alpha + \hat{\delta}), \end{aligned} \quad (5)$$

where the gap functions are defined by

$$\Delta_0(r_\alpha) \equiv V_0 \langle c_\uparrow(r_\alpha) c_\downarrow(r_\alpha) \rangle; \quad (6)$$

$$\Delta_{\hat{\delta}}(r_\alpha) \equiv V_1 \langle c_\uparrow(r_\alpha + \hat{\delta}) c_\downarrow(r_\alpha) \rangle. \quad (7)$$

We have introduced the index α labeling the two basis points in the unit cell, the label k which is the Fourier inverse of R , and $\hat{\delta} = \hat{0}, \hat{r}, \hat{r} - \hat{R}, -\hat{R}$ connecting nearest neighbors with different basis indices. The equations (3) are subject to the self-consistency requirements

$$\Delta_0(r_\alpha) = V_0 \sum_{nk} u_{n,k}(r_\alpha) v_{n,-k}^*(r_\alpha) \tanh \left(\frac{\beta \varepsilon_{n,k}}{2} \right), \quad (8)$$

$$\begin{aligned} \Delta_{\hat{\delta}}(r_\alpha) &= \frac{V_1}{2} \sum_{nk\hat{\delta}} \left[u_{n,k}(r_\alpha + \hat{\delta}) v_{n,-k}^*(r_\alpha) \right. \\ &\quad \left. + u_{n,k}(r_\alpha) v_{n,-k}^*(r_\alpha + \hat{\delta}) \right] \tanh \left(\frac{\beta \varepsilon_{n,k}}{2} \right), \end{aligned} \quad (9)$$

where the sum is over positive energy eigenvalues $\varepsilon_{n,k}$ only.

The orthorhombicity of YBCO is modeled by an anisotropy in the hopping parameters, reflecting the increased electronic mobility associated with the chains;²⁵ throughout the present work we use $t_y/t_x = 1.5$, which approximates the observed a - b anisotropy in the magnetic penetration depth,²⁶ and $V_0 = -V_1 = -3t_x$. Twin boundaries of up to $4|\hat{r}|$ width (corresponding to approximately 22\AA) are investigated, with $t_y = t_x$ and $\mu^I \leq 0$ within the twin. The largest system studied is $100|\hat{r}|$ in length with 400 k -states, or 80 000 sites; periodic boundary conditions are assumed throughout.

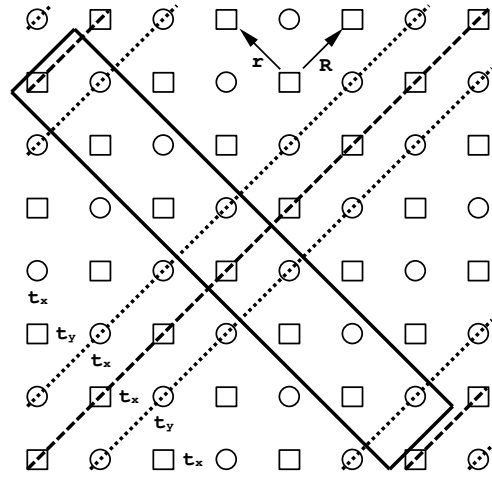


FIG. 1. The unit cell of the finite-size system for the BdG calculations is shown as a solid line superimposed on a square lattice. Long and short dashed lines represent twin boundaries of width 0 and $|\hat{r}|$, respectively. Basis points are labeled by circles and squares.

At a twin boundary of zero width and $\mu^I = 0$, we find within the BdG theory that for all temperatures the dominant d -wave component of the order parameter is virtually unaffected. The extended and on-site s -wave components, whose bulk values are approximately 10% of Δ_d , go from their near-bulk values to zero, over a single lattice spacing r , reversing their sign relative to Δ_d on either side of the boundary. As the impurity strength is increased at low temperatures, however, the d -wave and s -wave components become increasingly perturbed from their bulk values over the coherence length $\xi_{d+s}(T)$, where $\xi_{d+s}(0) \approx |\hat{r}|$ in the present work. When the magnitude of the d -wave component in the twin boundary is suppressed to approximately half its bulk value, an additional complex s -wave component may be nucleated near the twin edge, breaking time-reversal symmetry. We have found no evidence for a phase transition to a bulk \mathcal{T} -violating state in a uniform system.

The real and imaginary parts of the various components of the order parameter are shown in Fig. 2 for a twin boundary with $\mu^I = -10t_x$, $\mu = -t_x$, $T = 0$, and boundary width $W_T = 4|\hat{r}|$. While all the components go to zero rapidly within the twin boundary, both the real and imaginary parts of the s -wave gap functions are enhanced near the twin edge. In the immediate vicinity of the twin boundary, the real s -wave components are perturbed from their bulk values over a short distance comparable to $\xi_{d+s}(0)$, reflecting the local nucleation of additional s -wave components through spatial variations of the dominant d -wave component. The presence of finite complex gap functions in the bulk, however, implies that the imaginary components vary over a different characteristic distance $\xi_{is}(0) \gg \xi_{d+s}(0)$. This longer length scale, as well as the comparable sizes of $\text{Im}(\Delta_0)$ near the twin edge and the bulk Δ_d , is consistent with the GL predictions⁷ discussed above.

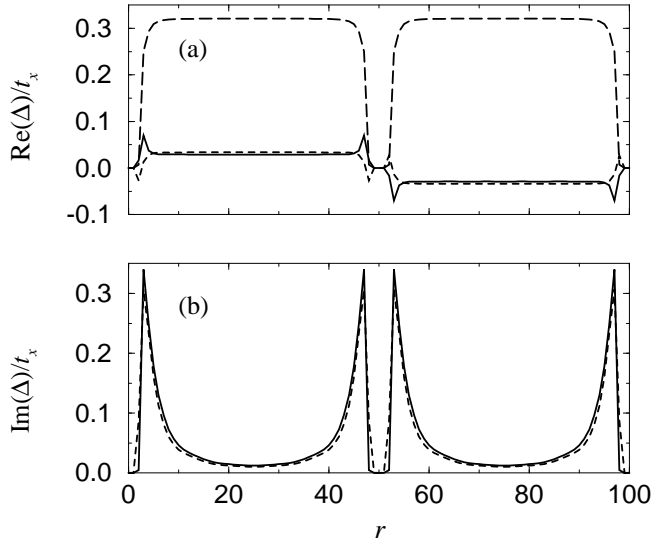


FIG. 2. The (a) real and (b) complex components of the d -wave, on-site, and extended s -wave gap functions (corresponding to long-dashed, short-dashed, and solid lines respectively) are shown as a function of distance r perpendicular to the twin boundary. In (b), $\text{Im}(\Delta_s)$ is multiplied by a factor of -10 to facilitate comparison with $\text{Im}(\Delta_0)$. Results are obtained using $\mu = -t_x$, $\mu^I = -10t_x$, $T = 0$, and twin width $4|\hat{r}|$. Twin boundaries are centered at positions $r = 0$ (which is equivalent to $r = 100$ by periodic boundary conditions) and $r = 50$ in units of $|\hat{r}|$.

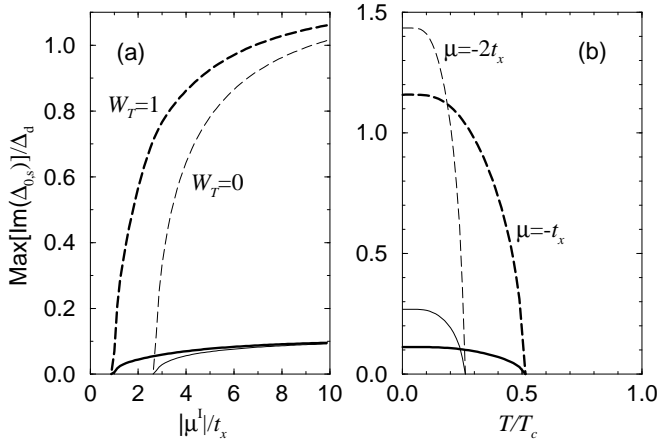


FIG. 3. The maximum value of the complex on-site (dashed lines) and extended s -wave (solid lines) components relative to the bulk value of the d -wave order parameter are shown as a function of (a) $|\mu^I|$ (note $\mu^I \leq 0$) and W_T at zero temperature and $\mu = -t_x$, and (b) T/T_c and μ . In (a) thin and bold lines correspond to twin boundary widths $W_T/|\hat{r}| = 0$ and 1 , respectively. In (b), thin and bold lines denote results for $\mu = -2t_x$ and $\mu = -t_x$, and we have chosen $\mu^I = -100t_x$, and $W_T = 0$.

As shown in Fig. 3, the size of the complex s -wave component nucleated near the twin boundary is extremely sensitive to the temperature, impurity strength, and the width of the twin boundary. At zero temper-

ature, Fig. 3(a), a \mathcal{T} -violating state first appears for $\mu^I \approx -2.7t_x$ at all electron densities for an impurity line (i.e. $W_T = 0$). As the impurity strength continues to increase, the perturbation of the d -wave component, and the maximum values of the imaginary s -wave components, begin to saturate. For $W_T > 0$, however, a lower impurity strength can give rise to \mathcal{T} -violation at zero temperature, since the d -wave component is already suppressed by approximately 20% in a locally tetragonal region (with $t_x = t_y$) even for $\mu^I = 0$. Increasing W_T beyond approximately $3|\hat{r}|$ has no further effect. This result, valid for all electron densities, is also consistent with the GL prediction⁷ that local tetragonal symmetry could favor a time-reversal breaking state at low temperature.

The growth of all the s -wave components with decreasing chemical potential reflects the impending instability of the system against bulk dominant s -wave superconductivity at slightly lower electron densities.^{17,18} As the temperature is increased at finite μ^I , the complex component decreases to zero as $\sqrt{1 - T/T^*}$; the transition temperature T^* is strongly density-dependent, scaling roughly with Δ_d . The same T^* is obtained for wider twin boundaries at a given density, though the magnitudes of the complex s -wave components increases with increasing W_T .

The spatial variation of the s -wave component's phase relative to Δ_d implied by Fig. 2 leads to currents which flow parallel to the twin surface and in opposite directions on either side of the twin boundary. The strong impurity potential therefore mimics a line of temperature-dependent magnetic flux passing through the twin boundary and oriented parallel to the c -axis. As shown by the differential conductance in Fig. 4

$$\frac{\partial I(r)}{\partial V} \propto - \sum_{nk} [|u_{n,k}(r)|^2 f'(V - \varepsilon_{n,k}) + |v_{n,k}(r)|^2 f'(V + \varepsilon_{n,k})], \quad (10)$$

where f' is the voltage-derivative of a Fermi function, this effective field splits the low-energy band of virtual-bound states associated with Andreev reflections at the twin surface.²⁷ Alternatively, the presence of two low-energy quasiparticle peaks in the tunneling conductance at low temperatures reflects the existence of a physical gap in the excitation spectrum, proportional to the magnitude of the total complex s -wave component. The zero-temperature maximum peak-to-peak separation, found in Fig. 4a to be approximately $0.2t_x \sim 2$ meV (where t_x is estimated from $T_c = 0.51t_x \approx 60$ K at this carrier concentration $\langle n \rangle \approx 0.75$), grows with increasing $|V_0|$ and $|\mu^I|$ but diminishes with increasing temperature and distance from the twin boundary. While the tunneling conductance exhibits low-temperature features that are no doubt finite-size effects, it is evident that the low energy band splits at a temperature $0.1T_c \approx 6$ K which is considerably lower than the $T^* \sim 0.5T_c$ estimated from Fig. 3b. A comparable splitting of the zero-energy peak has been

recently observed⁶ in tunneling spectra of YBCO surfaces, and has been interpreted¹⁰ as a clear signature of \mathcal{T} -violation.

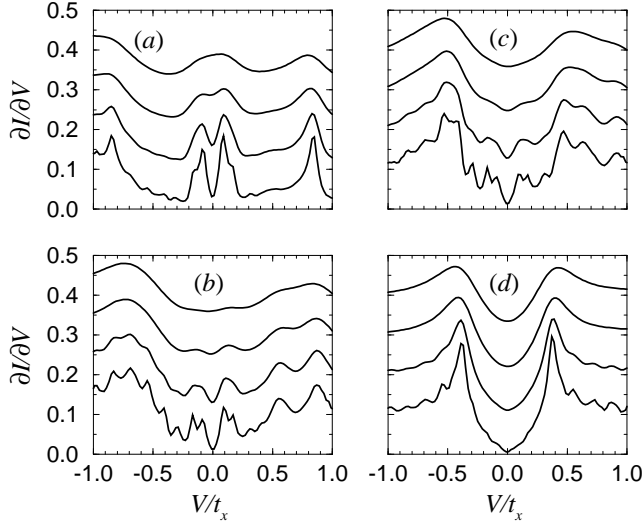


FIG. 4. A low-energy portion of the tunneling conductance near a twin boundary is shown as a function of energy, distance r from the twin edge where (a) through (c) correspond to $|\hat{r}|$ through $3|\hat{r}|$ while (d) illustrates the bulk, and temperatures $T = 0$ (lower), $T = 0.05T_c$ (offset 0.1), $T = 0.1T_c$ (offset 0.2) and $T = 0.15T_c$ (offset 0.3). Parameters are as in Fig. 2.

In summary, we have found evidence for time-reversal symmetry breaking near twin boundaries in a d -wave orthorhombic superconductor at low temperatures $T < T^* < T_c$, where T^*/T_c scales approximately with the size of the bulk d -wave gap. The magnitudes of the complex s -wave components associated with the \mathcal{T} -violation depend strongly on the chemical potential and depletion of the carrier density in the twin boundary. These s -wave gap functions could be responsible for the finite Josephson currents observed in c -axis tunnel junctions to heavily-twinned YBCO.³ As a consequence of the time-reversal breaking, the low energy quasiparticle peak in the tunneling conductance (related to the zero-bias anomaly in STS) is predicted to split in the vicinity of the twin edge.

ACKNOWLEDGMENTS

The authors are grateful to D. Branch, L.-W. Chen, M. Franz, L.H. Greene, K.A. Moler, and M.I. Salkola for their insightful comments. This work has been partially supported by the Natural Sciences and Engineering Research Council of Canada and the Ontario Centre for Materials Research.

- ¹ E. Dagotto, Rev. Mod. Phys. **66**, 763 (1994); D.J. Van Harlingen, Rev. Mod. Phys. **67**, 515 (1995).
- ² P. Chaudhari and S.Y. Lin, Phys. Rev. Lett. **72**, 1048 (1994).
- ³ A.G. Sun, D.A. Gajewski, M.B. Maple and R.C. Dynes, Phys. Rev. Lett. **72**, 2267 (1994); A.S. Katz, A.G. Sun, R.C. Dynes, and K. Char, Appl. Phys. Lett. **66**, 105 (1995); R. Kleiner *et al.*, Phys. Rev. Lett. **76**, 2161 (1996).
- ⁴ M.B. Walker, Phys. Rev. B **53**, 5835 (1996); M.B. Walker and J. Luettmer-Strathmann, Phys. Rev. B **54**, 588 (1996).
- ⁵ J.R. Kirtley, *et al.* Phys. Rev. B **51**, 12057 (1995).
- ⁶ M. Covington, M.M. Aprili, L.H. Greene, F. Xu, and C.A. Mirkin, unpublished.
- ⁷ M. Sigrist, K. Kuboki, P.A. Lee, A.J. Millis, and T.M. Rice, Phys. Rev. B **53**, 2835 (1996).
- ⁸ M. Sigrist, D.B. Bailey, and R.B. Laughlin, Phys. Rev. Lett. **74**, 3249 (1995).
- ⁹ M. Matsumoto and H. Shiba, J. Phys. Soc. Jpn. **65**, 2194 (1996).
- ¹⁰ M. Fögelstrom, D. Rainer, and J.A. Sauls, unpublished.
- ¹¹ A. Rosová, C. Boulesteix, and I. Vávra, Physica C **214**, 247 (1993).
- ¹² C. O'Donovan, M.D. Lumsden, B.D. Gaulin, and J.P. Carbotte, Phys. Rev. B **55**, 9088 (1997).
- ¹³ K.A. Moler, J.R. Kirtley, R. Liang, D. Bonn, and W.N. Hardy, unpublished.
- ¹⁴ M. Franz, C. Kallin, P.I. Soininen, A.J. Berlinsky, and A.L. Fetter, Phys. Rev. B **53**, 5795 (1996).
- ¹⁵ J.-H. Xu, Y. Ren, and C.-S. Ting, Phys. Rev. B **53**, R2991 (1996).
- ¹⁶ M. Franz, C. Kallin, and A.J. Berlinsky Phys. Rev. B **54**, R6897 (1996).
- ¹⁷ D.L. Feder and C. Kallin, Phys. Rev. B **55**, 559 (1997).
- ¹⁸ R. Micnas, J. Ranninger and S. Robaszkiewicz, Rev. Mod. Phys. **62**, 113 (1990).
- ¹⁹ P.I. Soininen, C. Kallin, and A.J. Berlinsky, Phys. Rev. B **50**, 13 883 (1994).
- ²⁰ Y. Wang and A.H. MacDonald, Phys. Rev. B **52**, R3876 (1995).
- ²¹ E. Dagotto, A. Nazarenko and A. Moreo, Phys. Rev. Lett. **74**, 310 (1995).
- ²² B. Keimer *et al.* J. Appl. Phys. **76**, 1 (1994).
- ²³ I. Maggio-Aprile *et al.* Phys. Rev. Lett. **75**, 2754 (1995).
- ²⁴ Y. Zhu and M. Suenaga, in "Interfaces in High- T_c Superconducting Systems," S.L. Shindé and D.A. Rudman, eds. Springer-Verlag, New York (1994).
- ²⁵ W.A. Atkinson and J.P. Carbotte, Phys. Rev. B **52**, 10 601 (1995).
- ²⁶ D.N. Basov *et al.* Phys. Rev. Lett. **74**, 598 (1995).
- ²⁷ C.-R. Hu, Phys. Rev. Lett. **72**, 1526 (1994).