

Supplementary material for: Shear thinning in dilute and semidilute solutions of polystyrene and DNA

Sharadwata Pan,^{1,2,3} Duc At Nguyen,³ B. Dünweg,^{3,4,5} P. Sunthar,^{2,1} T. Sridhar,^{3,1} and J. Ravi Prakash^{3,1, a)}

¹⁾*IITB-Monash Research Academy, Indian Institute of Technology Bombay, Powai, Mumbai - 400076, India*

²⁾*Department of Chemical Engineering, Indian Institute of Technology Bombay, Powai, Mumbai - 400076, India*

³⁾*Department of Chemical Engineering, Monash University, Melbourne, VIC 3800, Australia*

⁴⁾*Max Planck Institute for Polymer Research, Ackermannweg 10, 55128 Mainz, Germany*

⁵⁾*Condensed Matter Physics, TU Darmstadt, Hochschulstraße 12, 64289 Darmstadt, Germany*

(Dated: 23 October 2017)

I. DILUTE SOLUTION ZERO SHEAR RATE VISCOSITY

Pan et al. [1] have previously determined the zero shear rate solution viscosity, η_0 , for dilute 25 kbp and T4 DNA solutions by least-square fitting the values of viscosity in the plateau region of very low shear rates, across a range of temperatures and concentrations below c^* , and extrapolating to zero shear rate. For details, see the supplementary information in Ref. [1]. The zero shear rate solution viscosity for λ -phage DNA has been determined here using the same procedure. Data for the all the three DNA samples, for various values of c/c^* and T , are displayed in Table I (with the data for the 25 kbp and T4 DNA solutions reproduced here from Ref. [1]).

Since the viscosity of the solvent for DNA solutions (containing 10 mM Tris, 1 mM EDTA, and 0.5 M NaCl), is almost identical to the viscosity of water at 20°C, the solvent viscosity at any other temperature was considered to be equal to that of the viscosity of water at that temperature. Water viscosities reported at https://www.thermexcel.com/english/tables/eau_atm.htm were used since they are tabulated at intervals of 1°C, for an extended range of temperatures. Note that where temperatures coincide, these values of viscosity are identical to those reported by Howe et al. [2]. Values of viscosity at intermediate temperatures were obtained by linear interpolation between the nearest two temperatures. The polymer contribution to steady state zero shear rate viscosity, $\eta_{p0} = \eta_0 - \eta_s$, for all the dilute and semidilute DNA solutions, can then be obtained.

The steady state solution shear viscosity, η , was measured by Hua and Wu [3] for solutions of four different molecular weights of polystyrene in dioctyl phthalate (denoted PS1 to PS4), for a range of temperatures. The zero shear rate viscosities η_0 at each temperature have been extracted (as in the case of DNA solutions) by least-square fitting the values of viscosity in the plateau region

of very low shear rates, and extrapolating to zero shear rate. The procedure for determining the solvent viscosity η_s as a function of temperature for the dioctyl phthalate solutions has been described in Appendix A of the main paper. Using these values, the polymer contribution to steady state zero shear rate viscosity, $\eta_{p0} = \eta_0 - \eta_s$, has been obtained for all the polystyrene solutions, and is displayed in Table II for various values of c/c^* (calculated as described in Appendix A of the main paper) and T .

II. SEMIDILUTE SOLUTION ZERO SHEAR RATE VISCOSITY

The steady state shear viscosities η of the three DNA solutions were measured for a variety of concentrations in the semidilute regime and across a temperature range of 15–35°C. Examples of the dependence of measured solution shear viscosity on shear rate $\dot{\gamma}$ are displayed in Figs. 1 (a) and (b). The former displays the viscosity of 25 kbp DNA at a fixed concentration $c = 0.441$ mg/ml and at various temperatures ranging from $T = 15.8$ to 44.6°C. Since c^* varies with temperature, this corresponds to values of c/c^* ranging from 2.12 to 8.65 (see Table III), all of which are in the semidilute regime. In Fig. 1 (b), the dependence of η on $\dot{\gamma}$ of T4 DNA at a fixed temperature $T = 25^\circ\text{C}$, is shown at various concentrations, varying from 0.059 to 0.214 mg/ml. This corresponds to a c/c^* range of 2.98 to 10.82, as displayed in Table III. As in the case of dilute polymer solutions, the zero shear rate viscosity η_0 was determined by least-square fitting the values of viscosity in the plateau region of very low shear rates, at each temperature and concentration, and extrapolating to zero shear rate. Details are given in our earlier work [4]. Values obtained in this way for the three DNA samples, across the range of concentrations and temperatures, are displayed in Table III, reproduced here from Ref. [4].

The steady state shear viscosities η were measured for the polystyrene solutions PS1.1M and PS15.4M across a range of concentrations and temperatures. Values of $\eta_{p,0}$ for these solutions have been determined identically as in

^{a)}Corresponding author: ravi.jagadeeshan@monash.edu

TABLE I. Steady state zero shear rate viscosities, η_0 (mPa.s) for 25 kbp, λ -phage, and T4 DNA at various concentrations c (mg/ml) and temperatures T ($^{\circ}$ C) in the dilute regime ($0 < c/c^* < 1$).

25 kbp				λ -phage				T4 DNA			
c	T	c/c^*	η_0	c	T	c/c^*	η_0	c	T	c/c^*	η_0
0.112	15	0.91	2.95 ± 0.01	0.05	15	0.56	2.35 ± 0.02	0.038	15	0.79	5.38 ± 0.13
	15	0.57	1.76 ± 0.01		18	0.78	2.14 ± 0.02		15.7	0.58	2.43 ± 0.01
0.07	18	0.74	1.75 ± 0.01		21	0.93	2.04 ± 0.02	0.023	17.3	0.72	2.33 ± 0.01
	21	0.85	1.72 ± 0.01	15	0.35	1.88 ± 0.01	19.4		0.85	2.23 ± 0.01	
	25	0.97	1.58 ± 0.02	18	0.49	1.75 ± 0.01	15.7	0.38	1.96 ± 0.01		
	15	0.36	1.53 ± 0.01	21	0.58	1.73 ± 0.01	17.3	0.47	1.86 ± 0.01		
0.0441	18	0.46	1.49 ± 0.01	0.0315	25	0.68	1.61 ± 0.01	0.015	19.4	0.56	1.79 ± 0.01
	21	0.54	1.43 ± 0.01		30	0.77	1.52 ± 0.01		22	0.65	1.68 ± 0.01
	25	0.61	1.31 ± 0.01		35	0.85	1.39 ± 0.01	24.5	0.71	1.6 ± 0.01	
	30	0.7	1.27 ± 0.01		15	0.22	1.52 ± 0.01	15	0.2	1.51 ± 0.01	
	35	0.76	1.2 ± 0.01	18	0.31	1.42 ± 0.01	20	0.36	1.48 ± 0.01		
0.028	15	0.23	1.38 ± 0.01	0.02	21	0.37	1.36 ± 0.01	0.0094	25	0.39	1.43 ± 0.01
	18	0.29	1.31 ± 0.01		25	0.43	1.28 ± 0.01		30	0.52	1.4 ± 0.01
	21	0.34	1.25 ± 0.01		30	0.49	1.15 ± 0.01	35	0.59	1.37 ± 0.01	
	25	0.39	1.15 ± 0.01		35	0.54	1.04 ± 0.01	15	0.12	1.36 ± 0.01	
	30	0.44	1.09 ± 0.01	15	0.14	1.39 ± 0.01	20	0.23	1.29 ± 0.01		
0.0175	35	0.48	1.01 ± 0.01	0.0125	18	0.2	1.28 ± 0.01	0.0059	25	0.25	1.22 ± 0.01
	15	0.14	1.29 ± 0.01		21	0.23	1.22 ± 0.01		30	0.33	1.16 ± 0.01
	18	0.18	1.2 ± 0.01		25	0.27	1.15 ± 0.01	35	0.37	1.09 ± 0.01	
	21	0.21	1.14 ± 0.01		30	0.3	1.04 ± 0.01	15	0.08	1.27 ± 0.01	
	25	0.24	1.05 ± 0.01	35	0.34	0.94 ± 0.01	20	0.14	1.18 ± 0.01		
0.008	30	0.28	0.98 ± 0.01	0.008	15	0.09	1.29 ± 0.01	0.0038	25	0.15	1.09 ± 0.01
	35	0.3	0.9 ± 0.01		18	0.13	1.21 ± 0.01		30	0.21	1.02 ± 0.01
	15	0.09	1.29 ± 0.01		21	0.15	1.13 ± 0.01	35	0.23	0.96 ± 0.01	
	18	0.13	1.21 ± 0.01		25	0.17	1.06 ± 0.01				
	21	0.15	1.13 ± 0.01		30	0.2	0.96 ± 0.01				
25	0.17	1.06 ± 0.01	35	0.22	0.87 ± 0.01						

the case of all the other solutions considered here, and are displayed in Table IV.

III. DEPENDENCE OF RELAXATION TIME λ_η ON TEMPERATURE

The temperature dependence of λ_η has been discussed in the main paper, with data indicating a linear relationship between λ_η and $1/T$. Additional data displaying similar behaviour, at other concentrations, is shown in Figs. 2 and Figs. 3, for the three DNA and for the

polystyrene solutions PS1.1M and PS15.4M, respectively.


- [1] S. Pan, D. Ahirwal, D. A. Nguyen, P. Sunthar, T. Sridhar, and J. R. Prakash. Viscosity radius in dilute polymer solutions: Universal behaviour from DNA rheology and Brownian dynamics simulations. *Macromolecules*, 47(21):7548–7560, 2014.
- [2] K.J. Howe, J.C. Crittenden, D.W. Hand, R.R. Trussell, and G. Tchobanoglous. *Principles of Water Treatment*. Wiley, 2012. ISBN 9780470405383. URL <https://books.google.com.au/books?id=igH0BWsyfb0C>.
- [3] C. C. Hua and M. S. Wu. Viscometric properties of dilute polystyrene/dioctyl phthalate solutions. *J. Polym. Sci. Part B Polym. Phys*, 44(5):787–794, 2006.
- [4] S. Pan, D. A. Nguyen, P. Sunthar, T. Sridhar, and J. R. Prakash. Universal solvent quality crossover of the zero shear rate viscosity of semidilute DNA solutions. *J. Rheol.*, 58(2):339–368, 2014.

TABLE II. Polymer contribution to steady state zero shear rate viscosity, $\eta_{p,0}$, at various temperatures, for the dilute polystyrene samples PS1 to PS4 used in Ref. [3].


Sample	Molecular weight M ($\times 10^6$ g/mol)	Concentration c (g/ml)	T ($^{\circ}\text{C}$)	c/c^*	$\eta_{p,0}$ (mPa.s)
PS1	0.55	0.0046	22	0.223	16.1 ± 0.1
			25	0.239	13.8 ± 0.1
			35	0.283	9.9 ± 0.1
			45	0.318	5.6 ± 0.04
PS2	0.68	0.0048	22	0.266	23.9 ± 0.3
			25	0.287	18.3 ± 0.4
			35	0.344	11.4 ± 0.01
			45	0.390	7.8 ± 0.2
PS3	0.93	0.0054	22	0.350	31.9 ± 0.9
			25	0.383	24.3 ± 0.1
			35	0.469	15.5 ± 0.2
			45	0.536	10.8 ± 0.1
PS4	2.0	0.0028	22	0.269	27.9 ± 0.4
			25	0.305	20.6 ± 0.2
			35	0.395	13.2 ± 0.2
			45	0.464	9.9 ± 0.01

TABLE III. Steady state zero shear rate viscosities (mPa.s) for 25 kbp, λ -phage, and T4 DNA at various concentrations, c (mg/ml) and temperatures, T ($^{\circ}\text{C}$) in the semidilute regime ($1 \leq c/c^* \leq 10$).

25 kbp				λ DNA				T4 DNA			
c	T	c/c^*	η_0	c	T	c/c^*	η_0	c	T	c/c^*	η_0
0.441	15.8	3.9	39.3 ± 0.5	0.315	21	5.83	61.4 ± 1.05	0.148	15	3.08	55.9 ± 0.7
	20	5.13	33.5 ± 0.2		25	6.85	57.9 ± 0.9		18	4.93	50.7 ± 0.5
	24.3	6.04	28.8 ± 0.2	15	2.25	16 ± 0.1	21		6.14	46.7 ± 0.5	
	30	7.0	23.5 ± 0.2	21	3.7	14.6 ± 0.3	25		7.48	42.5 ± 0.4	
	37.2	7.88	18.4 ± 0.1	0.2	25	4.35	12.3 ± 0.6		30	8.22	37.1 ± 0.2
	44.6	8.65	14.5 ± 0.1	30	4.88	11.3 ± 0.3	35		9.52	32.5 ± 0.3	
0.364	15.8	3.22	20.4 ± 0.1	35	5.41	10 ± 0.2	0.094	15	1.96	19.2 ± 0.6	
	20	4.23	17.7 ± 0.1	21	2.31	6.1 ± 0.1		18	3.13	17.6 ± 0.4	
	24.3	4.99	15.5 ± 0.1	25	2.72	5.6 ± 0.2		21	3.92	16.6 ± 0.1	
	30	5.78	12.8 ± 0.1	0.125	30	3.05		5 ± 0.1	25	4.75	14.6 ± 0.3
	37.2	6.5	10.5 ± 0.1	35	3.38	4.4 ± 0.1		30	5.22	12.9 ± 0.2	
	44.6	7.14	8.5 ± 0.01	21	1.48	3.4 ± 0.02		35	6.05	11.6 ± 0.2	
0.315	15.8	2.79	14.7 ± 0.04	25	1.74	3.1 ± 0.01	0.059	15	1.23	10.2 ± 0.2	
	20	3.66	12.7 ± 0.1	0.08	30	1.95		2.8 ± 0.01	18	1.97	9.6 ± 0.1
	24.3	4.32	11.2 ± 0.01	35	2.16	2.5 ± 0.03		21	2.46	8.9 ± 0.1	
	30	5	9.3 ± 0.03	25	1.09	1.9 ± 0.01		25	2.98	8.1 ± 0.03	
	37.2	5.63	7.7 ± 0.05	0.05	30	1.22		1.7 ± 0.01	30	3.28	7.3 ± 0.1
	44.6	6.18	6.6 ± 0.05	35	1.35	1.6 ± 0.02		35	3.79	6.6 ± 0.1	
0.112	18	1.18	2.7 ± 0.02	0.07	30	1.11	1.5 ± 0.01	0.023	18	1.27	4.9 ± 0.2
	21	1.37	2.5 ± 0.01		35	1.21	1.5 ± 0.01		21	1.58	4.6 ± 0.2
	25	1.56	2.3 ± 0.02		25	1.92	4.2 ± 0.2		25	1.92	4.2 ± 0.2
	30	1.78	2 ± 0.02		30	2.11	3.8 ± 0.2		30	2.11	3.8 ± 0.2
0.07	35	1.93	1.8 ± 0.01	35	2.44	3.3 ± 0.05	35	2.44	3.3 ± 0.05		
	22	1	2.1 ± 0.01	24.5	1.1	2 ± 0.01	22	1	2.1 ± 0.01		
	24.5	1.1	2 ± 0.01				24.5	1.1	2 ± 0.01		

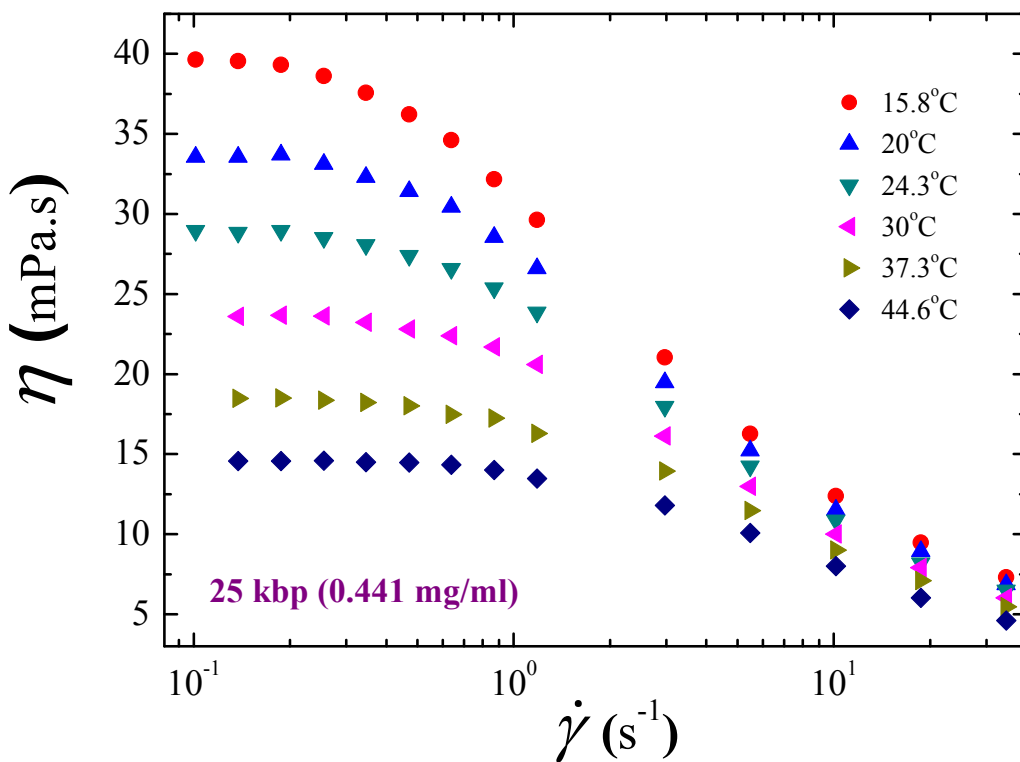

(a)

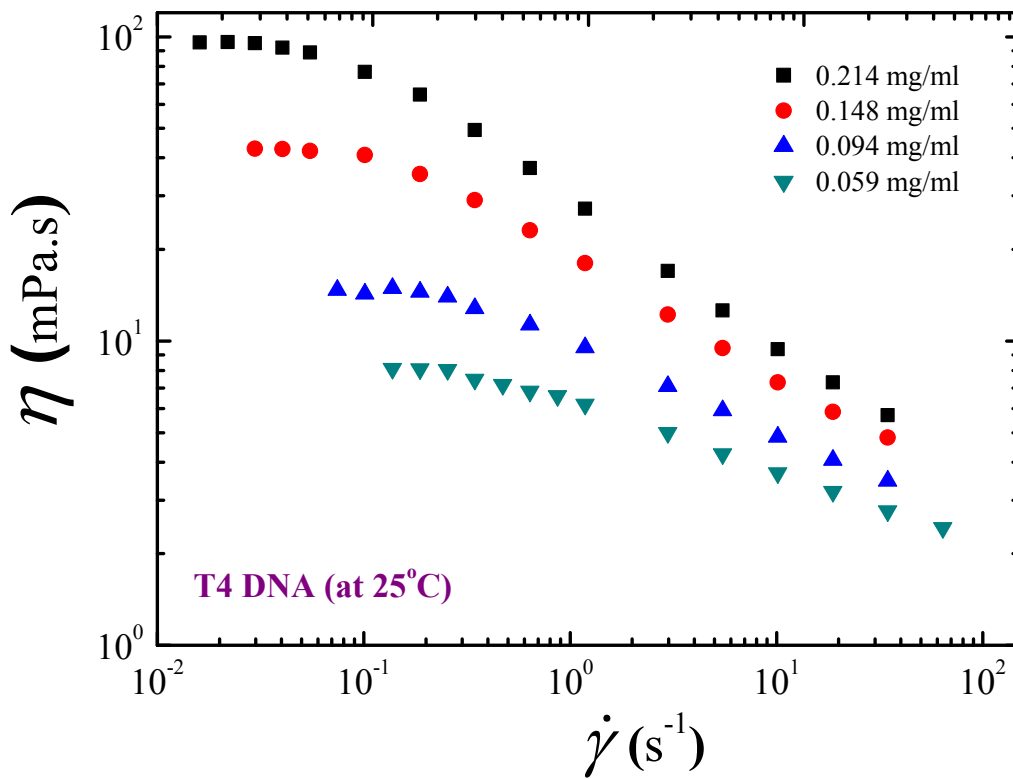

(b)

FIG. 1. (a) Shear rate dependence of the steady state shear viscosity for 25 kbp DNA at a fixed absolute concentration for different temperatures. (b) Shear rate dependence of the steady state shear viscosity for T4 DNA at a fixed temperature for different absolute concentrations.

TABLE IV. Steady state zero shear rate viscosities (mPa.s) for polystyrene solutions PS1.1M and PS15.4M at various concentrations, c (mg/ml) and temperatures, T ($^{\circ}\text{C}$) in the semidilute regime ($1 \leq c/c^* \leq 10$).

PS1.1M				PS15.4M			
c (g/ml)	T ($^{\circ}\text{C}$)	c/c^* (estimated)	η_0 (mPa.s)	c (g/ml)	T ($^{\circ}\text{C}$)	c/c^* (estimated)	η_0 (mPa.s)
0.036	22	2.59	1686.5 ± 1.3	0.0098	22	2.68	443.4 ± 2.8
	30	3.19	980.8 ± 2.1		30	4.50	291.7 ± 2.1
	35	3.48	721.6 ± 0.9		35	5.33	223.6 ± 0.2
0.0225	22	1.62	505.6 ± 0.6	0.0061	22	1.67	196.9 ± 0.6
	30	1.99	308.2 ± 0.6		30	2.80	133.6 ± 1.1
	35	2.18	238.6 ± 0.3		35	3.32	105 ± 0.6
0.0144	22	1.04	240.4 ± 0.2	0.0038	22	1.04	139.3 ± 0.4
	30	1.27	153.7 ± 0.3		30	1.75	91.7 ± 0.3
	35	1.39	118.3 ± 0.2		35	2.07	72.3 ± 0.3
0.0089	22			0.0027	22	< 1.0	
	30	< 1.0			30	1.24	74 ± 0.1
	35				35	1.47	58.3 ± 0.2

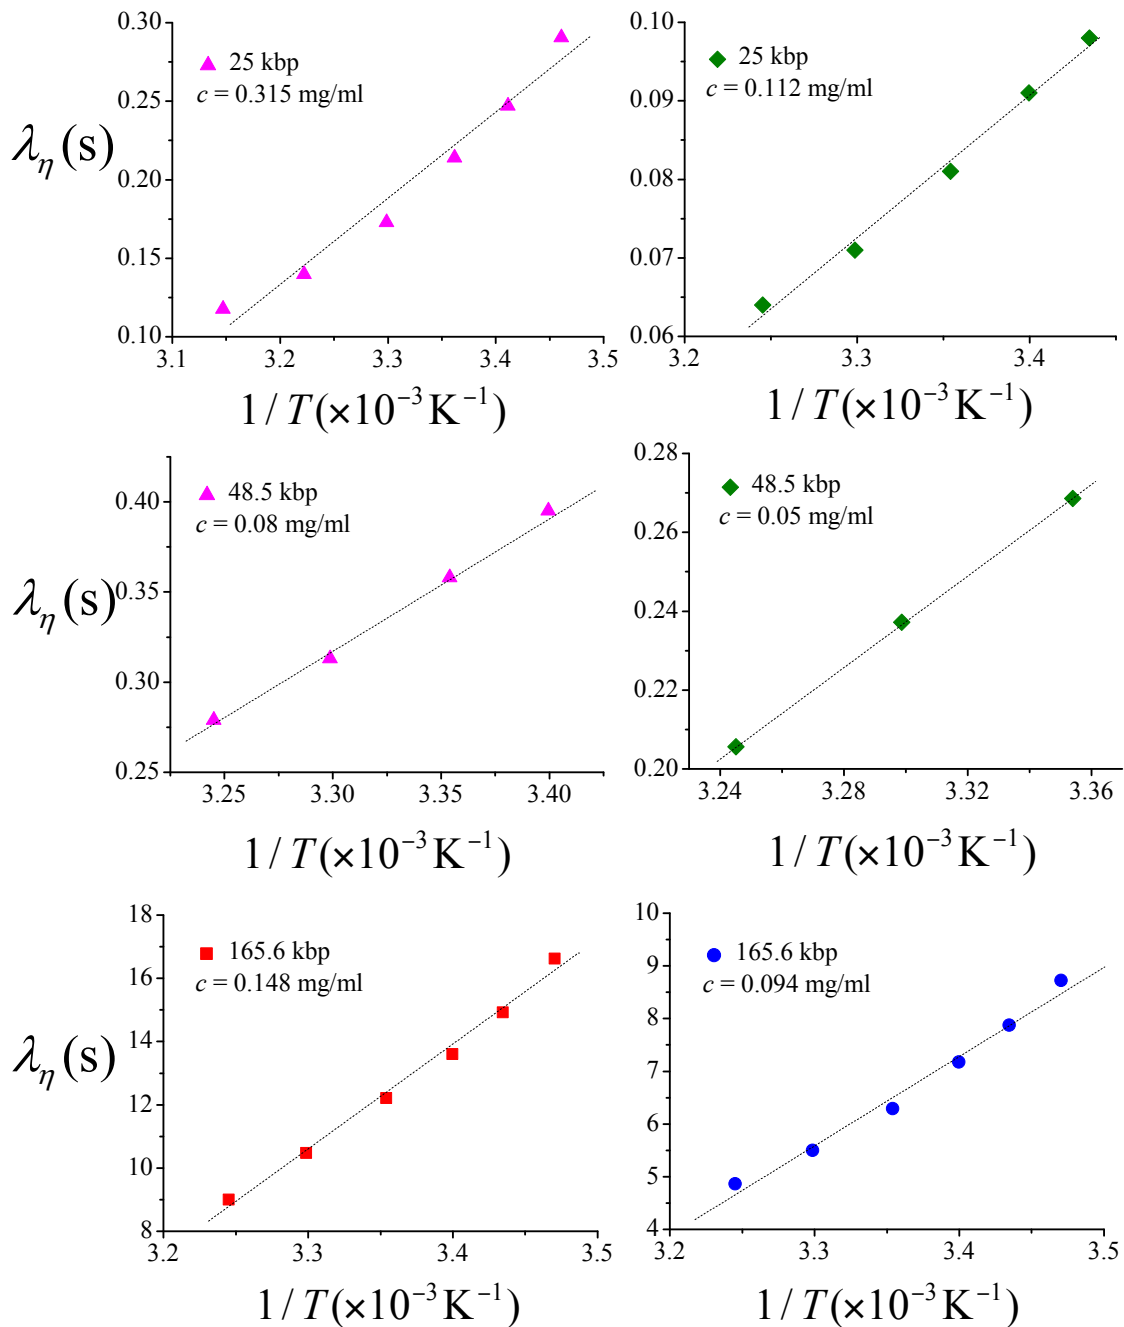


FIG. 2. Semidilute solution relaxation time λ_η vs $1/T$ at a fixed concentration c for 25 kbp, 48.5 kbp, and 165.6 kbp DNA. The lines are the linear least squares fit to the data.

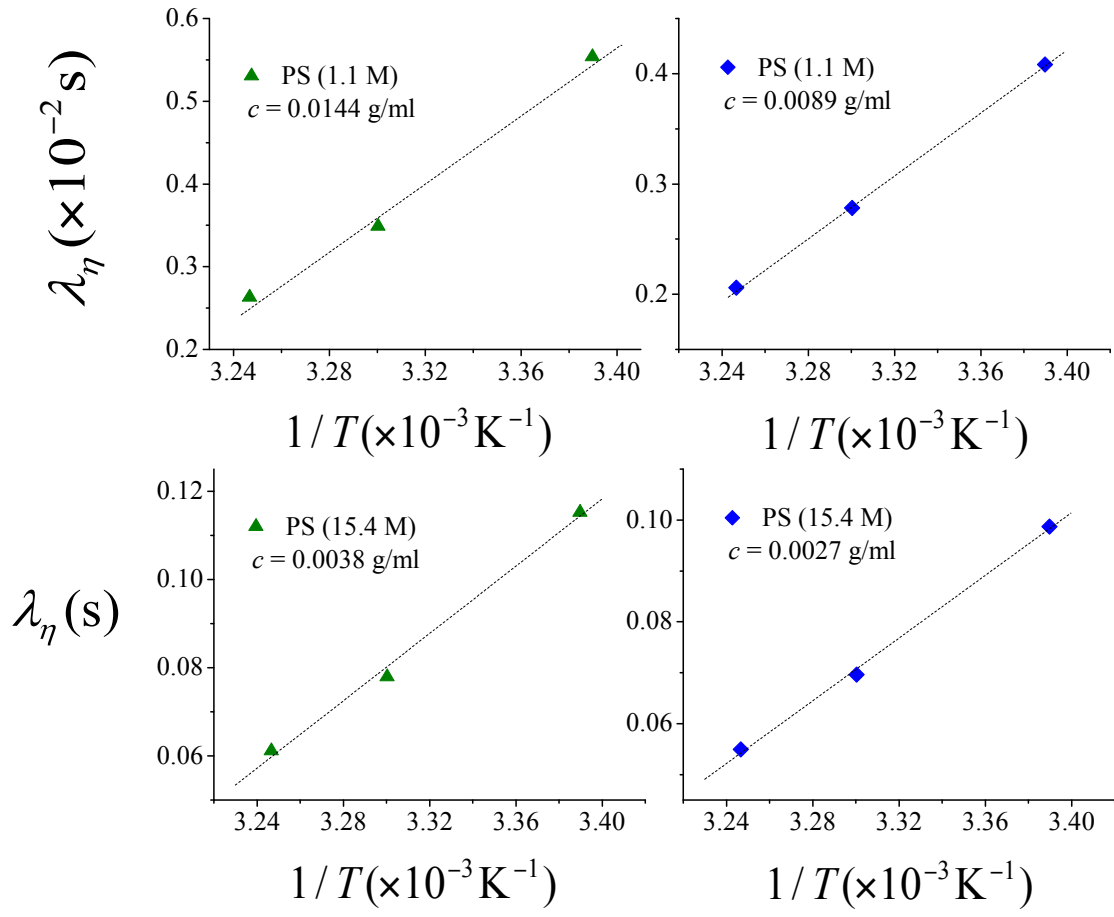


FIG. 3. Semidilute solution relaxation time λ_η vs $1/T$ at a fixed concentration c for polystyrene solutions PS1.1M and PS15.4M. The lines are the linear least squares fit to the data.