



# CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

## In situ observation of a phase transition in silicon carbide under shock compression using pulsed x-ray diffraction

S. J. Tracy, R. F. Smith, J. K. Wicks, D. E. Fratanduono, A. E. Gleason, C. A. Bolme, V. B. Prakapenka, S. Speziale, K. Appel, A. Fernandez-Pañella, H. J. Lee, A. MacKinnon, F. Tavella, J. H. Eggert, and T. S. Duffy

Phys. Rev. B **99**, 214106 — Published 17 June 2019

DOI: [10.1103/PhysRevB.99.214106](https://doi.org/10.1103/PhysRevB.99.214106)

# *In situ* observation of a phase transition in silicon carbide under shock compression using pulsed x-ray diffraction

S. J. Tracy,<sup>1,\*</sup> R. F. Smith,<sup>2</sup> J. K. Wicks,<sup>1,†</sup> D. E. Fratanduono,<sup>2</sup> A. E. Gleason,<sup>3</sup>  
C. A. Bolme,<sup>4</sup> V. B. Prakapenka,<sup>5</sup> S. Speziale,<sup>6</sup> K. Appel,<sup>7</sup> A. Fernandez-Pañella,<sup>2</sup>  
H. J. Lee,<sup>8</sup> A. MacKinnon,<sup>8,‡</sup> F. Tavella,<sup>8</sup> J. H. Eggert,<sup>2</sup> and T. S. Duffy<sup>1</sup>

<sup>1</sup>*Department of Geosciences, Princeton University, Princeton, New Jersey 08544, USA*

<sup>2</sup>*Lawrence Livermore National Laboratory, Livermore, California 94550 USA*

<sup>3</sup>*Stanford Institute for Materials and Energy Sciences,*

*SLAC National Accelerator Laboratory, Menlo Park, California 94025 USA*

<sup>4</sup>*Shock and Detonation Physics, Los Alamos National Laboratory,  
Los Alamos, New Mexico 87545 USA*

<sup>5</sup>*GeoSoilEnviroCARS University of Chicago, Argonne National Laboratory, Argonne, Illinois 60439 USA*

<sup>6</sup>*GFZ German Research Centre for Geosciences, Telegrafenberg, 14473 Potsdam, Germany*

<sup>7</sup>*European XFEL GmbH, Holzkoppel 4, D-22869 Schenefeld, Germany*

<sup>8</sup>*Linac Coherent Light Source, SLAC National Accelerator Laboratory,  
Menlo Park, California 94025 USA*

(Dated: June 4, 2019)

The behavior of silicon carbide, SiC, under shock compression is of interest due to its applications as a high-strength ceramic and for general understanding of shock-induced polymorphism. Here we used the Matter in Extreme Conditions beamline of the Linac Coherent Light Source to carry out a series of time-resolved pump-probe x-ray diffraction measurements on SiC laser-shocked as high as 206 GPa. Experiments on single crystals and polycrystals of different polytypes show a transformation from a low-pressure tetrahedral phase to the high-pressure rocksalt-type (B1) structure. We directly observe coexistence of the low- and high-pressure phases in a mixed-phase region and complete transformation to the B1 phase above 2 Mbar. The densities measured by x-ray diffraction are in agreement with both continuum gas-gun studies and a theoretical B1 Hugoniot derived from static-compression data. Time-resolved measurements during shock loading and release reveal a large hysteresis on unloading with the B1 phase retained to as low as 5 GPa. The sample eventually reverts to a mixture of polytypes of the low-pressure phase at late times. Our study demonstrates that x-ray diffraction is an effective means to characterize the time-dependent structural response of materials undergoing shock-induced phase transformations at megabar pressures.

## I. INTRODUCTION

Silicon carbide (SiC) is an important technological material with widespread mechanical, electronic and optical applications [1]. In particular, SiC plays a major role as a high-strength ceramic used in armoring and impact coatings [2, 3]. Characterizing the dynamic response of SiC is a long-sought-after goal to improve the design and performance of impact shielding. During ballistic impact conditions (< 20 GPa), SiC provides a rigid barrier to effectively break projectiles. However, at high-stress, SiC is observed to lose strength and undergo a phase transition [4, 5]. SiC is also found naturally in meteorites, impact sites, diamond inclusions, and in various terrestrial rock types [6, 7]. As a result, there has been long-standing interest in its behavior under dynamic loading [4, 5, 8–11]. SiC has also been studied extensively under static high pressures and temperatures [12, 13] and is often used as

a model system for understanding the B3 (zincblende) to B1 (rocksalt) phase transition under compression [14].

At ambient conditions, the crystal structure of SiC is a derivative of the diamond structure with Si and C atoms linked in an  $sp^3$  bonding network. The structure can be viewed as a framework of covalently bonded corner-linked tetrahedra. SiC exhibits a large number (>250) of polytypes based on different stacking sequences of Si-C bilayers. Major polytypes are designated 3C, 2H, 4H, and 6H. The cubic 3C polytype ( $F\bar{4}3m$ ) adopts the B3 or zincblende structure and is known as  $\beta$ -SiC. The hexagonal polytypes include 2H (wurtzite), 4H and 6H polytypes (all  $P6_3mc$ ) and are collectively known as  $\alpha$ -SiC. In addition, SiC readily incorporates defects and impurities [15].

Early x-ray diffraction (XRD) experiments identified a phase change under 300-K static compression to a rocksalt-type (B1) structure (space group  $Fm\bar{3}m$ ) near 100 GPa [16]. This structural transformation involves a change from four-fold to six-fold coordination and is accompanied by large volume collapse ( $\sim 16$ – $20\%$ ) [16–19]. Gas-gun shock-wave experiments on 6H SiC showed evidence for a similar phase transition near 100 GPa, with a mixed-phase region extending up to  $\sim 140$  GPa [4, 5]. By analogy with static experiments, the high-pressure

---

\* Present address: Geophysical Laboratory, Carnegie Institution for Science, Washington DC 20015, USA

† Present address: Department of Earth and Planetary Sciences, Johns Hopkins University, Baltimore, Maryland 21218 USA

‡ Present address: Livermore National Laboratory, Livermore, California 94550 US

phase was assumed to correspond to the B1 structure, but lattice-level structural information was not obtained. Density functional theory (DFT) calculations predict this phase transition occurs at lower pressure, around 60–70 GPa and 0 K [20–22]. In addition to equilibrium structure calculations, the transformation pathway from the ambient zincblende and wurtzite-type structures to the high-pressure rocksalt phase has been extensively investigated theoretically with multiple proposed mechanisms and transformation pathways [14, 23, 24].

Recently, new attention has been focused on SiC at high pressures due to its potential presence in extrasolar carbon-rich planets [25–27]. Using a laser-heated diamond anvil cell, the B3–B1 transformation was found to occur near 60–74 GPa and  $\sim 2000$  K with a negative Clausius-Clapeyron slope [17, 18]. The equation of state (EOS) of the B1 phase was also determined up to 200 GPa in static diamond anvil cell experiments [18, 19]. Additionally, evidence for the decomposition of SiC at high pressure and temperature has been reported [28].

Crystallographic phase transitions occur over a finite timescale, dictated by the transformation mechanism. Due to the nanosecond timescales of laser-driven shock experiments, kinetic effects can be important. In cases where the duration of the experiment approaches this timescale, a transition may not be observed or may require significant overpressure. As a result, there has been debate regarding the conditions under which reconstructive phase transitions involving coordination changes can be inhibited on shock timescales [29–31]. In static experiments, the B3–B1 transition in SiC is observed to be reversible, exhibiting a pronounced hysteresis, with the onset of the back transformation not occurring until 35 GPa on pressure release [16]. This hysteresis on back transformation and the overpressure required to achieve the transition in gas-gun studies indicate that both the low- and high-pressure phases can persist outside of their equilibrium stability field for some time. Coupling laser-drive compression with the sub-nanosecond time resolution an x-ray free electron laser probe provides a new opportunity to characterize time-dependent metastability.

In this study, the structural behavior of SiC was examined using laser-driven shock compression and *in situ* x-ray diffraction. Through a series of pump-probe experiments on both single crystals and polycrystals, we explore the behavior of SiC near and above the B1 phase transition. Our study provides the first direct information on the SiC structure under dynamic loading and release. Our results are compared to previous shock wave and static compression data to provide insights into phase stability, kinetics, and high-pressure phases in this fundamental material. More generally, our work also demonstrates the utility of laser-based shock compression combined with *in situ* x-ray diffraction for structural studies of materials at Mbar pressures.

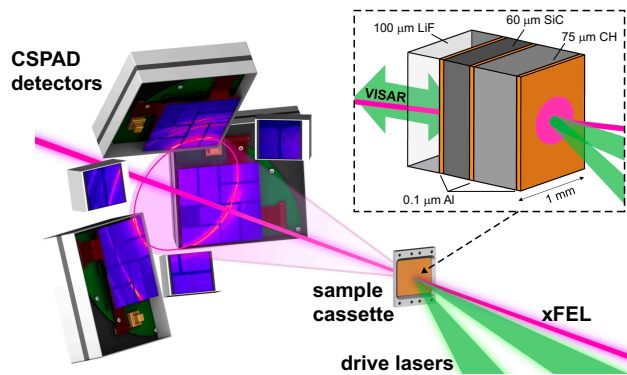


FIG. 1. Schematic illustration of the experimental setup. Samples were mounted in a translatable cassette. The x-ray beam was incident at  $15^\circ$  degrees relative to target normal and the two nanosecond laser arms were oriented at  $6^\circ$  and  $25^\circ$ . Diffracted x-rays were recorded on CSPAD detectors. The target package, illustrated on the right, shows the CH ablator, SiC sample, and LiF window. The VISAR was oriented normal to the sample, focused on the LiF-SiC interface.

## II. EXPERIMENTAL

Laser-driven shock compression experiments were carried out at the Matter in Extreme Conditions (MEC) end station of the Linac Coherent Light Source (LCLS) [38]. Samples consisted of polycrystalline SiC in the cubic 3C form (Mitsui Corp.) and  $\alpha$ -SiC (0001) single crystals of polytype 4H (MTI Corp). Both materials were grown by metal organic chemical vapor deposition. Samples were characterized at ambient conditions by XRD and Raman spectroscopy and the results were consistent with literature values (Supplementary Material, Figs. S1–S3 [32]).

The target package design is illustrated schematically in Figure 1. Samples were cut and polished to a thickness of 40–60  $\mu\text{m}$  and glued to polyimide (CH) ablaters ( $\sim 75$ - $\mu\text{m}$  thick) with an approximately 1- $\mu\text{m}$  thick epoxy layer. A subset of samples were prepared with 100- $\mu\text{m}$  thick LiF (100) windows glued to the rear surface of the SiC. A 0.1  $\mu\text{m}$ -thick Al coating was deposited on the ablation-side of the CH, the CH-SiC interface and the SiC-LiF interface. The samples were mounted on target plates with a common orientation for the single crystals.

Target packages were dynamically compressed using 30-J pulses from a 527-nm Nd:Glass laser system [39] focused to a diameter of 200–250  $\mu\text{m}$  (Fig. 1). The lasers were incident at 6 and 15 degrees from target normal and overlapped on the polyimide surface to generate ablation-driven compression waves that propagated through the target package. The laser pulses were 12–15 ns long and the pulse shape (quasi-flat-top) had a modest upward ramp to maintain a steady shock in the sample as the ablation plasma expands. Stress was controlled by tuning the laser spot size (200–250  $\mu\text{m}$ ). Experiments were performed both with and without phase plates. The reproducibility of the drive for a given laser energy and spot size was monitored by comparing measured pulse

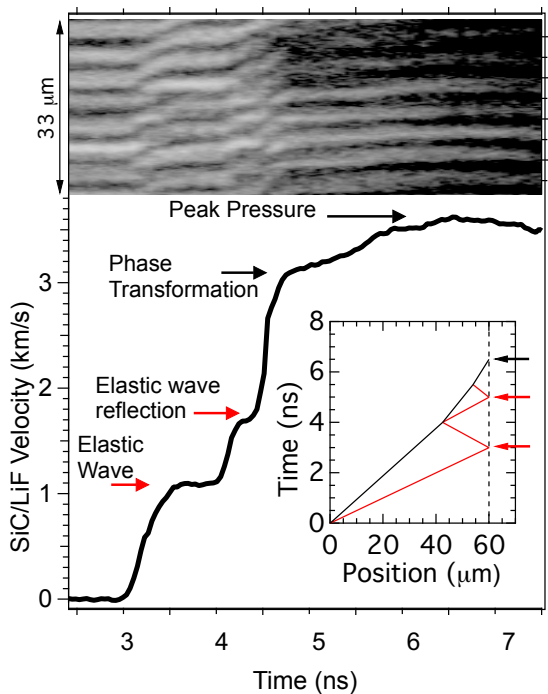


FIG. 2. Representative VISAR wave profile collected using drive conditions of the  $\sim 114$  GPa polycrystalline time series. Time axes is relative to shock entering SiC. The plateau associated with the phase transformation is at a SiC-LiF particle velocity of  $\sim 3.1$  km/s, consistent with SiC stress of  $\sim 100$  GPa. Inset shows a schematic wave diagram illustrating the elastic wave (red) arrival along with a second elastic reverberation due to an interaction between the elastic release from the LiF window and the oncoming plastic wave (black).

shapes (supplemental material Fig. S4 [32]).

A line-imaging VISAR (velocity interferometer system for any reflector) was used to monitor the free surface or SiC-LiF interface velocity history of the sample [35]. The VISAR had a  $300\text{-}\mu\text{m}$  field of view and a 20-ns sweep duration. For a given drive condition (laser power, focal spot size), the VISAR data from a shot using a target with a LiF window was used to determine the peak sample stress using the known equations of state of SiC and LiF (supplemental material Table S1 [32]) and standard impedance matching techniques [40]. The VISAR also provided information on x-ray timing and positioning as well as identifying any non-planarity of the load. A representative VISAR trace is shown in Fig. 2. This VISAR trace was collected using the drive conditions for the 114 GPa polycrystalline time series shown in Fig. 3b. The elastic precursor is evident and the plateau associated with the phase transformation is at a SiC-LiF particle velocity of  $\sim 3.1$  km/s, consistent with SiC stress of  $\sim 100$  GPa. The feature at  $\sim 1.6$  km/s is associated with a reverberation interaction between the elastic release from the LiF window and the oncoming plastic wave.

For the polycrystalline starting material, *in situ* x-ray

diffraction data were collected for two Hugoniot states at  $\sim 114$  GPa and  $\sim 206$  GPa, as determined from shots with LiF windows. For the single-crystal starting material, a Hugoniot state at  $\sim 175$  GPa was examined. For each compression state, a time series was collected by carrying out a sequence of shots on nominally identical samples (without LiF windows) using the same drive conditions as for the LiF-containing target, and collecting XRD patterns at different probe times after the shock entered the sample. Data were recorded up to 40 ns after release from the free surface. The sample was probed with 8.5-keV free electron x-rays focused to a  $30\text{-}\mu\text{m}$  diameter spot size near the center of the laser spot. The self-amplified spontaneous emission (SASE) mode x-rays were quasi-monochromatic (1%  $\Delta E/E$ ) and consisted of 80-fs pulses containing  $\sim 10^{12}$  photons. These short pulses enable snapshots of the compressed material allowing for the exploration kinetic effects.

The x-ray free electron laser (xFEL) beam makes an angle of 15 degrees to the sample normal (Fig. 1). Diffraction is carried out in transmission geometry and scattered x-rays are recorded on six Cornell-SLAC pixel array detectors (CSPADs) detectors [41] positioned for wide angular coverage. We used three large format ( $90\text{ mm}^2$ ) and three small format ( $43\text{ mm}^2$ ) CSPAD detectors at distances ranging from 90-190 mm from the sample allowing us to cover an approximately 15-90 degree two-theta range (Fig. S8). The CSPAD data were projected to a common reference plane and integrated azimuthally to obtain one-dimensional x-ray diffraction profiles. The CSPADs were calibrated using  $\text{CeO}_2$ ,  $\text{LaB}_6$ , and  $\text{Si}_3\text{N}_4$  standards.

Time series were collected by varying the time delay between the laser pulse and the probe x-rays. The time at which the shock enters the SiC can be identified by a drop in reflectivity, as seen in the VISAR data (supplemental material, Fig. S6 [32]). This is designated as  $t = 0$  ns. Owing to the transmission geometry of the experiment, at times before the shock wave reaches the SiC free surface the x-rays sample both compressed material and the remaining uncompressed material ahead of the shock. A Hugoniot elastic limit (HEL) of  $\sim 26\text{-}29$  GPa is determined from the measured wave profiles in Figs. 2 and S5. The elastic state is constrained to lie on the elastic Hugoniot from Vogler et. al [4]. We assume the partial release at the SiC-LiF interface follows the elastic Hugoniot. By comparison, the reported HEL from gas-gun studies ranges from 11.5 to 18.9 GPa [5, 9, 10, 42]. This enhancement of the elastic limit is consistent with reports of elevated elastic precursors in high-strain rate laser-drive experiments in other materials [43, 44].

The elastic precursor is not overdriven, and as a result data recorded before shock breakout include evidence of elastically compressed material. At times after the shock wave has broken out at the SiC free surface, the x-rays sample both compressed material and partially released material. The measured shock-wave transit times range from  $\sim 3\text{-}5$  ns, consistent with sample thickness of 40-

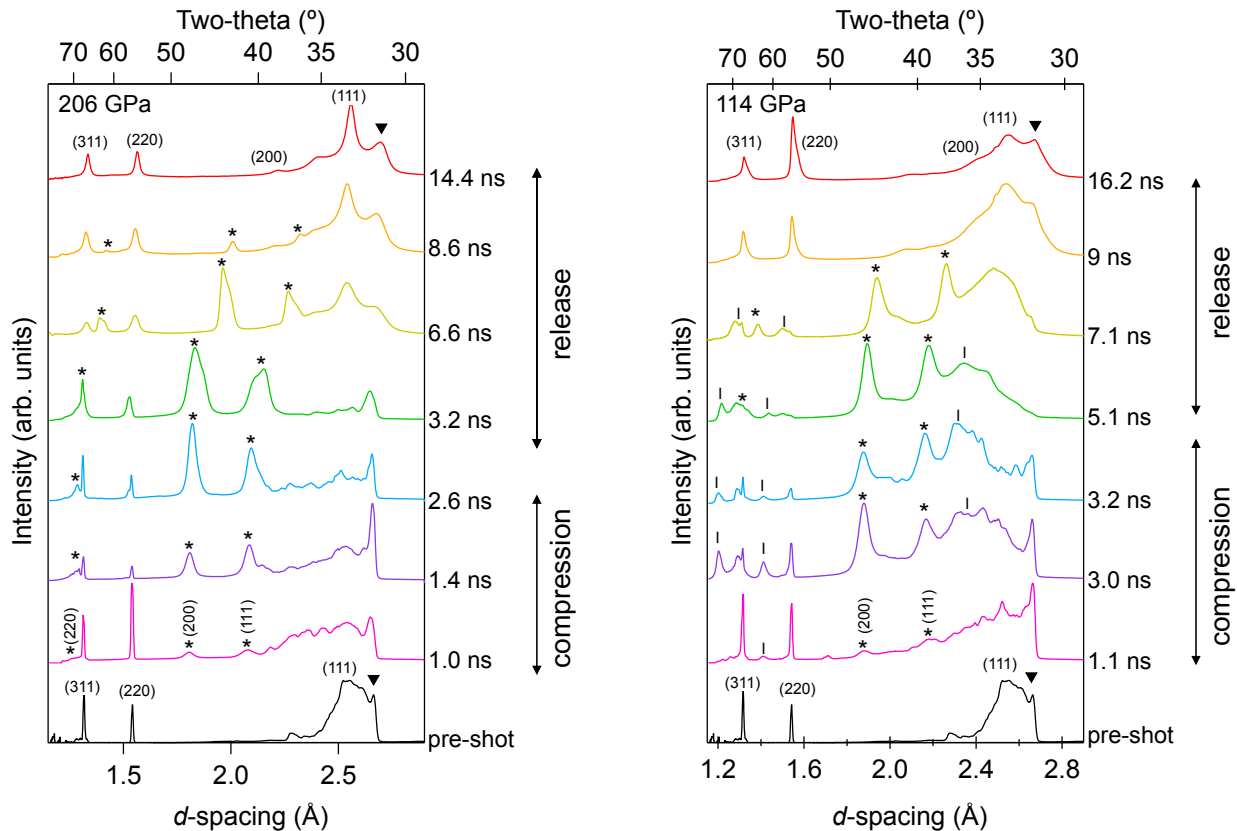


FIG. 3. **a)** Integrated x-ray diffraction patterns for time series collected at peak stress of  $\sim 206$  GPa for polycrystalline 3C starting material. X-ray probe times after the shock enters SiC are listed on the right. B1 peaks are marked with asterisks (\*). Ambient 3C peaks are indexed in the pre-shot pattern. The feature marked with a triangle ( $\blacktriangledown$ ) at  $2.66$  Å arises due to stacking fault disorder (Supplemental Material, S1 [32]). Peaks from the back-transformed 3C phase are indexed in the top pattern. **b)** Integrated diffraction patterns for time series collected for peak stress of  $\sim 114$  GPa. B1 peaks and compressed 3C peaks are marked with asterisks and vertical lines, respectively. X-ray probe times after shock enters SiC are listed to the right.

$60 \mu\text{m}$  and shock velocities determined by impedance matching. Experimental details for each shot are contained in supplemental material tables S3–S4 [32].

### III. RESULTS

Figure 3 shows a time series of x-ray diffraction patterns for the polycrystalline starting material. The diffraction patterns shown are a sum of the six azimuthally integrated CSPAD images, where the intensity of each pattern has been rescaled in order to correct for background differences between detectors. X-ray diffraction data were collected at variable probe times after the shock entered the SiC. The ambient 3C peaks are indexed in the pre-shot pattern.

Figure 3a shows a time series collected using drive conditions that produced a peak stress state of  $\sim 206$  GPa. At this stress, the shock transit time for the  $40\text{-}\mu\text{m}$  SiC was  $\sim 3$  ns. Three patterns were recorded between 1.0 and 2.6 ns after the shock enters the sample and hence during the compression phase before the shock breakout. As a

result, these patterns sample a uniform 206 GPa stress state along the Hugoniot. Peaks of the high-pressure B1 phase were observed at 1.0 ns after the shock entered the sample, the shortest delay time measured. This indicates that the 3C-B1 phase transition occurs rapidly under shock compression at this stress. We did not observe any evidence of peaks from the compressed 3C phase, indicating complete transformation to the B1 phase behind the shock front.

Figure 3a also shows 4 patterns recorded after breakout, at times ranging from 3.2 to 14.4 ns. As opposed to the patterns collected prior to breakout, the stress state on release is heterogeneous, evidenced by both peak splitting and broadened peak profiles. The effects include both longitudinal release from the free surface as well as release waves from the lateral edges of the sample, giving rise to complex wave-wave interactions and resulting in a heterogeneous stress state in the region of the sample probed by the xFEL.

Figure 3b shows a second time series of x-ray diffraction patterns collected for the polycrystalline starting material at a lower peak stress of  $\sim 114$  GPa. The wave

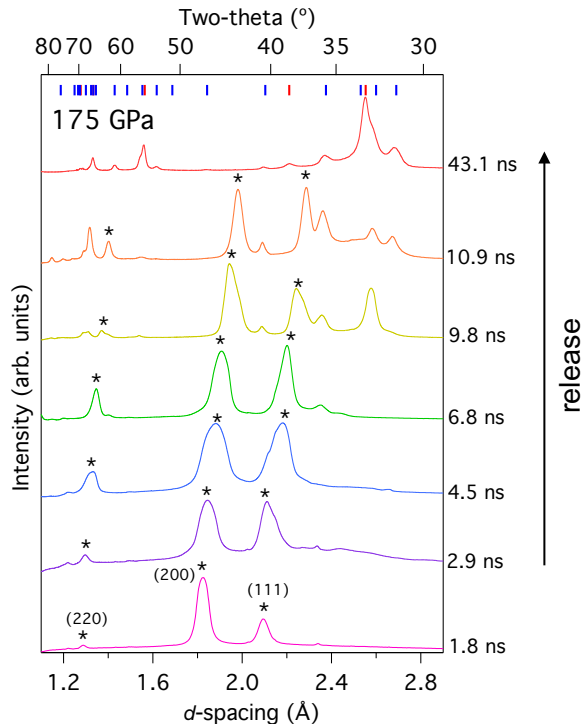


FIG. 4. Integrated diffraction patterns for time series collected at a peak stress of  $\sim 175$  GPa for single crystal  $\alpha$ -SiC starting material (4H). X-ray probe times after the shock enters SiC are listed on the right. B1 peaks are marked with asterisks (\*). For latest probe time (43.1 ns), the pattern can be indexed with a combination of 3C (red) and 4H (blue) peaks, indicated by tick marks above the pattern.

profile shown in Fig. 2 was collected using the drive conditions used for this series. The shock transit time for this series was  $\sim 5$  ns. Peaks from the transformed B1 phase as well as compressed 3C starting material are observed prior to breakout, indicating the material is being shocked into a mixed-phase state. During this scan, four patterns were collected on compression. After breakout, an additional three patterns were collected on release. The B1 phase is retained for to  $\sim 2$  ns after release and by 9 ns back transformation to ambient 3C phase and appears complete.

Figure 4 shows the results from a time series collected with a peak stress of  $\sim 175$  GPa for the single crystal  $\alpha$ -SiC starting material. Similar to the polycrystalline samples, the single crystal rapidly transforms to a B1 structure on loading. The samples were oriented such that there were no single-crystal diffraction spots from the ambient  $\alpha$ -SiC starting material recorded on the CSPAD detectors. As a result, no ambient diffraction is recorded during the compression phase for these shots. Here the transit time was  $\sim 3$  ns and the majority of the diffraction data were collected after breakout. Similar to the polycrystalline starting material, a large hysteresis is ob-

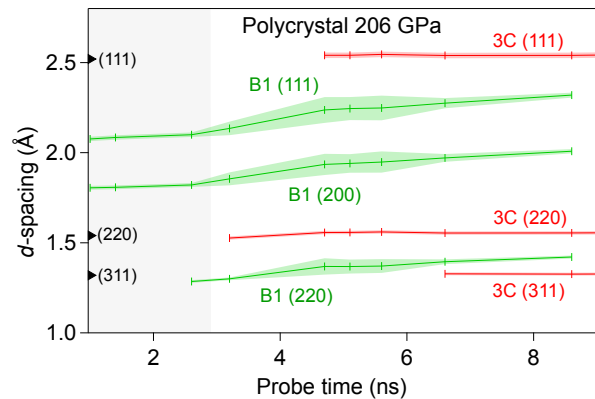


FIG. 5.  $d$ -spacings for polycrystalline SiC determined from fits to x-ray diffraction patterns for the time scan shown in Fig. 3a as a function of time after the shock has entered the SiC. The trends are the result of a linear extrapolation between the discrete probe times (hash marks). Shaded regions indicate the uncertainties in  $d$ -spacings and encompass the range of  $d$ -spacings that arise from sampling a non-homogenous stress state after breakout. The grey area contains results from shots collected on compression, prior to breakout. Ambient 3C peak positions are shown to left with black triangles.

served on back transformation, where the B1 phase is retained for nearly 10 ns after release. On release the pattern can be indexed as a combination of ambient 3C and 4H phases. A profile refinement was carried out for pattern collected at the latest probe time (43.1 ns) using the GSAS package [45, 46]. The refinement indicates that the sample released to ambient conditions consists of 48% 3C and 52% 4H polymorphs (Supplemental Material, Fig. S7 [32]).

#### IV. DISCUSSION

Figure 5 summarizes the evolution of  $d$ -spacings as a function of probe time, determined from fits to diffraction patterns for the time series shown in Fig. 3a. Figure 5 also contains results from additional shots not shown in Fig. 3a. Results for all shots are included in supplemental material, Table S3 [32]. In Fig. 5, The B1 (111) and (200) peaks appear at the earliest measured probe time (1 ns). The position of the B1 (220) peak can not be determined prior to breakout as a result of its relatively low intensity and overlap with uncompressed (311) 3C peak. The  $d$ -spacings for the transformed B1 phase remain unchanged up to the shock breakout time at 3 ns, after which the peaks shift to higher  $d$ -spacing as the pressure in the sample decreases. At these later times, the diffraction peaks exhibit both peak splitting as well as pronounced profile broadening (Fig. 3a). This reflects a stress distribution in the sample as a dispersive release wave propagates back from the free surface. In Fig. 5,



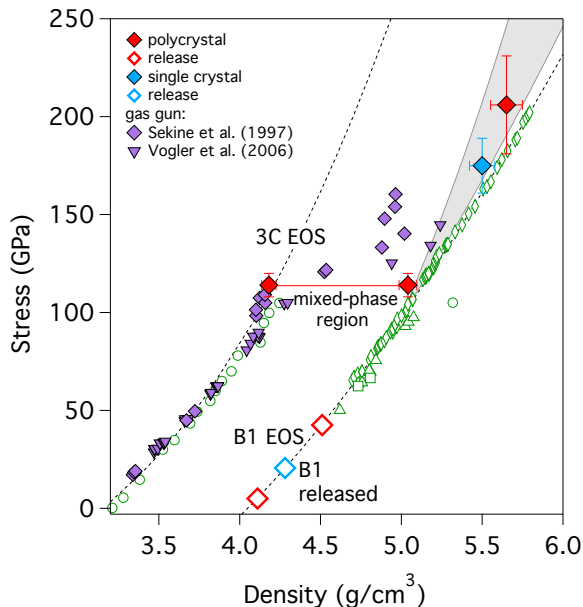


FIG. 6. The present results (red and blue symbols) are shown compared to continuum gas-gun results in purple [4, 5]. 300-K static studies are shown as open green symbols, where results by Yoshida et al. [16], Daviau et al. [17], Miozzi et al. [19], and Kidokuro et al. [18] are shown as circles, squares, diamonds and triangles, respectively. The present Hugoniot data are more consistent with the gas-gun results of Vogler et al. [4] than Sekine et al. [5] and lie close to the calculated theoretical Hugoniot (gray shaded region). The densities of the two components of the mixed-phase region lie close to the 3C Hugoniot curve and the calculated B1 Hugoniot. The 300-K B1 equation of state as well as the 3C EOS calculated from static compression data [19] are shown as dashed black curves.

the fan of  $d$ -spacings between 3-7 ns captures the range of peak positions spanned by the broadened B1 lines.

In addition to probing phases on the Hugoniot, the time resolution of our measurements allows us to directly observe a large hysteresis in the back transformation to the ambient four-coordinated structure(s). The B1 phase is retained for more than 5 nanoseconds after release before reversion to ambient 3C phase. In Fig 5, at  $\sim 7$ -8 ns, the B1 peaks resharpen, indicating the material has returned to a homogeneous stress state. This suggests the B1 phase is retained to near ambient pressure. At 8.6 ns, only a small trace of the high-pressure phase remains and by 14.4 ns back transformation is complete (Fig. 3a).

Figure 6 shows the densities determined by XRD under shock loading along with reported densities from previous gas-gun [4, 5] and diamond-anvil-cell studies at 300 K [16–19]. For the three time series discussed above (Figs. 3 and 4), the XRD densities (Fig. 6) were determined from data recorded prior to breakout and thus represent material compressed to a uniform stress state on the Hugoniot. Owing to a uniaxial compression geometry in our experiments, we measured longitudinal stress. Fig-

ure 6 also shows a 300-K EOS for the 3C and B1 phases, determined from diamond-anvil-cell data [19, 47].

Figure 6 includes a theoretical B1 Hugoniot calculated using a Mie-Grüneisen EOS (Supplemental Material, S3 [32]). A comparison of the calculated Hugoniot to the densities determined from x-ray diffraction demonstrates our results are consistent with the expected properties of the B1 phase along the Hugoniot. The thermodynamic parameters used to calculate the B1 Hugoniot in Fig. 6 are listed in the Supplemental Material, Table S2 [32]. The calculation incorporates a 3C-B1 transition energy from DFT calculations [20] along with the set of thermodynamic parameters determined from a fit to diamond-anvil cell results [19]. As the Grüneisen parameter ( $\gamma_0$ ) is not well constrained experimentally, the Hugoniot was calculated for a range between  $\gamma_0=0.5$ –2, giving rise to the gray field in Fig. 6. The stresses shown for the two time series collected above 150 GPa in Fig. 6 were determined assuming an extrapolation of the gas-gun Hugoniot data by Vogler et. al [4]. Further experimental studies are needed to better constrain the Hugoniot above 1 Mbar.

For the time series at 206 GPa and 175 GPa, the B1 densities from XRD are consistent with the calculated Hugoniot. For the polycrystalline time series at 114 GPa, we observed a coexistence of the compressed 3C phase and transformed B1 phase. The densities of these phases fall on the measured 3C Hugoniot and the theoretical B1 Hugoniot, respectively. The densities for the coexisting phases observed during compression, suggest a volume collapse of 16%, consistent with previous diamond anvil cell studies [13, 16, 17]. In Fig. 6, the coexisting compressed 3C and transformed B1 phase are both plotted at the peak stress of 114 GPa despite ambiguity as to whether the XRD samples a metastable mixed-phase assemblage or multiwave structure.

Figure 6 shows B1 densities from data collected on release (open symbols), corresponding to the last shot in a given time series for which B1 phase was observed (i.e. the lowest density B1 phase observed). The release densities have been placed on the B1 300-K EOS [19]. While the release pressure-temperature state is not well constrained experimentally, the relatively low thermal expansion of SiC [26] makes the 300-K isotherm a reasonable first-order approximation. A comparison of these release densities to the theoretical ambient volume of the B1 phase suggests the B1 phase is retained to pressures as low as 5 GPa. This requires a substantial volume expansion of the B1 unit cell to occur within nanoseconds. For the highest-stress shot, we observed a 38% volume expansion of B1 phase relative to its Hugoniot density on unloading prior to reversion to the ambient structure.

Under shock loading and release we observe a direct transformation to the B1 crystal structure followed by a reversion to the ambient phase on the nanosecond time scales of our measurements, with no evidence for the formation of any intermediate phases. Our results suggest the pathway through any transient structures must pro-

ceed on a sub-nanosecond timescale. This interpretation is consistent with *ab initio* molecular dynamics simulations that indicate the transition to the B1 phase occurs as quickly as 0.1 picosecond [48]. Accordingly, experiments targeted at probing intermediate structures experimentally require femtosecond x-ray diffraction techniques.

Our x-ray diffraction measurements provide crystallographic evidence for the phase transition from the four-coordinated 3C and 4H structures to the B1 phase under shock compression. Our results are consistent with the transition inferred from continuum gas-gun data, despite largely different time scales (ns versus 100s of ns). The densities determined from XRD are in reasonable agreement with continuum measurements and/or the theoretical Hugoniot derived from static measurements. Our study represents a significant extension of previous gas-gun and diamond anvil cell results, reaching stress states in excess of 2 Mbar while providing new details of the

hysteresis in the B1 transformation on unloading.

## ACKNOWLEDGMENTS

We thank Eran Greenberg (U. Chicago), Dongzhou Zhang (U. Hawaii) and the target fabrication team at Lawrence Livermore National Laboratory for experimental assistance. Gregory Stewart (SLAC) provided the graphic of the experimental configuration. Support for this research was provided from the DOE Office of Science - Fusion Energy Sciences Grant # DE-SC00016242, and performed under the auspices of the U.S. Department of Energy by Lawrence Livermore National Laboratory under Contract No. DE-AC52-07NA27344. Use of the Linac Coherent Light Source (LCLS), SLAC National Accelerator Laboratory, is supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences under Contract No. DE-AC02-76SF00515.

- 
- [1] H. O. Pierson, in *Handbook of Refractory Carbides and Nitrides*, edited by H. O. Pierson (William Andrew Publishing, Westwood, NJ, 1996).
- [2] K. A. Schwetz, in *Handbook of Ceramic Hard Materials*, edited by R. Riedel (Wiley-Blackwell, 2008) Chap. 5, pp. 683–748.
- [3] T. J. Holmquist and G. R. Johnson, *Journal of Applied Physics* **91**, 5858 (2002).
- [4] T. J. Vogler, W. D. Reinhart, L. C. Chhabildas, and D. P. Dandekar, *Journal of Applied Physics* **99**, 023512 (2006).
- [5] T. Sekine and T. Kobayashi, *Physical Review B* **55**, 8034 (1997).
- [6] R. M. Hough, I. Glimour, C. T. Pillinger, J. W. Arden, K. W. R. Gilkes, J. Yuan, and H. J. Milledge, *Nature* **378**, 41 (1995).
- [7] R. B. Trumbull, J.-S. Yang, P. T. Robinson, S. D. Pierro, T. Vennemann, and M. Wiedenbeck, *Lithos* **113**, 612 (2009).
- [8] W. H. Gust, A. C. Holt, and E. B. Royce, *Journal of Applied Physics* **44**, 550 (1973).
- [9] D. E. Grady, *Journal de Physique IV France* **04**, 385 (1994).
- [10] R. Feng, G. F. Raiser, and Y. M. Gupta, *Journal of Applied Physics* **83**, 79 (1998).
- [11] P. S. Branicio, J. Zhang, J. P. Rino, A. Nakano, R. K. Kalia, and P. Vashishta, *Applied Physics Letters* **112**, 111909 (2018).
- [12] K. Daviau and K. K. M. Lee, *Crystals* **8**, 217 (2018).
- [13] W. A. Bassett, M. S. Weathers, T. Wu, and T. Holmquist, *AIP Conference Proceedings* **309**, 145 (1994).
- [14] M. Catti, *Physical Review Letters* **87**, 035504 (2001).
- [15] P. Bogusławski and J. Bernholc, in *Encyclopedia of Materials: Science and Technology*, edited by K. J. Buschow, R. W. Cahn, M. C. Flemings, B. Ilshner, E. J. Kramer, S. Mahajan, and P. Veyssi ere (Elsevier, Oxford, 2001) pp. 7131 – 7139.
- [16] M. Yoshida, A. Onodera, M. Ueno, K. Takemura, and O. Shimomura, *Physical Review B* **48**, 10587 (1993).
- [17] K. Daviau and K. K. M. Lee, *Physical Review B* **95**, 134108 (2017).
- [18] Y. Kidokoro, K. Umamoto, K. Hirose, and Y. Ohishi, *American Mineralogist* **102**, 2230 (2017).
- [19] F. Miozzi, G. Morard, D. Antonangeli, A. N. Clark, M. Mezouar, C. Dorn, A. Rozel, and G. Fiquet, *Journal of Geophysical Research: Planets* **123**, 2295 (2018).
- [20] K. Karch, F. Bechstedt, P. Pavone, and D. Strauch, *Physical Review B* **53**, 13400 (1996).
- [21] Y.-P. Lu, D.-W. He, J. Zhu, and X.-D. Yang, *Physica B: Condensed Matter* **403**, 3543 (2008).
- [22] W. H. Lee and X. H. Yao, *Computational Materials Science* **106**, 76 (2015).
- [23] F. Shimojo, I. Ebbsj o, R. K. Kalia, A. Nakano, J. P. Rino, and P. Vashishta, *Physical Review Letters* **84**, 3338 (2000).
- [24] M. Catti, *Physical Review B* **65**, 224115 (2002).
- [25] H. F. Wilson and B. Militzer, *Astrophysical Journal* **793**, 34 (2014).
- [26] C. Nisr, Y. Meng, A. A. MacDowell, J. Yan, V. Prakapenka, and S.-H. Shim, *Journal of Geophysical Research: Planets* **122**, 124 (2017).
- [27] T. S. Duffy, N. Madhusudhan, and K. K. M. Lee, in *Treatise on Geophysics*, edited by G. Schubert (Elsevier, Oxford, 2015) 2nd ed., pp. 149 – 178.
- [28] K. Daviau and K. K. M. Lee, *Phys. Rev. B* **96**, 174102 (2017).
- [29] M. G. Gorman, A. L. Coleman, R. Briggs, R. S. McWilliams, D. McGonegle, C. A. Bolme, A. E. Gleason, E. Galtier, H. J. Lee, E. Granados, M. Śliwa, C. Sanloup, S. Rothman, D. E. Fratanduono, R. F. Smith, G. W. Collins, J. H. Eggert, J. S. Wark, and M. I. McMahon, *Scientific Reports* **8**, 16927 (2018).
- [30] P. Kalita, P. Specht, S. Root, N. Sinclair, A. Schuman, M. White, A. L. Cornelius, J. Smith, and S. Sinogeikin, *Phys. Rev. Lett.* **119**, 255701 (2017).



- [31] Y. Syono, K. Kusaba, T. Atou, and K. Fukuoka, in *Shock Waves*, edited by K. Takayama (Springer Berlin Heidelberg, Berlin, Heidelberg, 1992) pp. 121–128.
- [32] See Supplemental Material at [URL will be inserted by publisher], which includes Refs. [32 – 37], for details concerning experimental procedure, data reduction, and analysis.
- [33] S. Nakashima and H. Harima, *physica status solidi (a)* **162**, 39 (1997).
- [34] S. Nakashima, H. Makoto, M. Kouji, and T. Hidehiko, *Journal of the American Ceramic Society* **86**, 823 (2004).
- [35] P. M. Celliers, D. K. Bradley, G. W. Collins, D. G. Hicks, T. R. Boehly, and W. J. Armstrong, *Review of Scientific Instruments* **75**, 4916 (2004).
- [36] R. G. McQueen, S. P. Marsh, J. W. Taylor, J. N. Fritz, and W. J. Carter, in *High Velocity Impact Phenomena*, edited by R. Kinslow (Academic Press, New York, 1970) pp. 294–417.
- [37] Q. Liu, X. Zhou, X. Zeng, and S. N. Luo, *Journal of Applied Physics* **117**, 045901 (2015).
- [38] B. Nagler, B. Arnold, G. Bouchard, R. F. Boyce, R. M. Boyce, A. Callen, M. Campell, R. Curiel, E. Galtier, J. Garofoli, E. Granados, J. Hastings, G. Hays, P. Heimann, R. W. Lee, D. Milathianaki, L. Plummer, A. Schropp, A. Wallace, M. Welch, W. White, Z. Xing, J. Yin, J. Young, U. Zastrau, and H. J. Lee, *Journal of Synchrotron Radiation* **22**, 520 (2015).
- [39] S. B. Brown, A. Hashim, A. Gleason, E. Galtier, I. Nam, Z. Xing, A. Fry, A. MacKinnon, B. Nagler, E. Granados, and H. J. Lee, *Review of Scientific Instruments* **88**, 105113 (2017).
- [40] T. J. Ahrens, in *Geophysics, Methods in Experimental Physics*, Vol. 24, edited by G. H. Sammis and T. L. Henyey (Academic Press, New York, 1987) pp. 185–235.
- [41] H. T. Philipp, M. Hromalik, M. Tate, L. Koerner, and S. M. Gruner, *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment* **649**, 67 (2011).
- [42] N. Bourne, J. Millett, and I. Pickup, *Journal of Applied Physics* **81**, 6019 (1997).
- [43] R. F. Smith, R. W. Minich, R. E. Rudd, J. H. Eggert, C. A. Bolme, S. L. Brygoo, A. M. Jones, and G. W. Collins, *Phys. Rev. B* **86**, 245204 (2012).
- [44] R. F. Smith, J. H. Eggert, R. E. Rudd, D. C. Swift, C. A. Bolme, and G. W. Collins, *Journal of Applied Physics* **110**, 123515 (2011).
- [45] C. Larson and R. V. Dreele, *General Structure Analysis System (GSAS)*, Tech. Rep. Report LAUR 86-748 (Los Alamos National Laboratory, 1994).
- [46] B. H. Toby, *Journal of Applied Crystallography* **34**, 210 (2001).
- [47] K. K. Zhuravlev, A. F. Goncharov, S. N. Tkachev, P. Dera, and V. B. Prakapenka, *Journal of Applied Physics* **113**, 113503 (2013).
- [48] H. Y. Xiao, F. Gao, L. M. Wang, X. T. Zu, Y. Zhang, and W. J. Weber, *Applied Physics Letters* **92**, 241909 (2008).